

WELDING CONSUMABLES



(+90) 444 93 53
magmaweld.com
info@magmaweld.com

 (+90) 538 927 12 62



CORPORATE

Magmaweld is a manufacturer of Stick Electrodes, MIG/MAG & TIG Wires, Flux Cored Wires, Submerged-Arc Wires and Fluxes, Welding Machines, Welding Ancillary Products and Automation Systems in Turkey. Oerlikon Kaynak Elektroları ve Sanayi A.Ş. was founded in 1957 in order to manufacture stick electrodes as a licensee of Oerlikon-Buehrle AG.

In the year 1996, in order to reduce costs, to strengthen the leading position in Turkey and turn Magmaweld into a global brand, two old factories in Istanbul were moved to new, state of the art factory in Manisa, situated in the west of Turkey. In 2010 the second factory has been opened also in Manisa to produce high-tech welding equipment as well as to integrate robotic automation systems.

The MAGMAWELD brand came out as an analogy between the molten core of the earth, the MAGMA and the WELDPPOOL.

Magmaweld greatly values technical education and has been contributing to the training and education of thousands of welders through regular, free of charge courses since 1961. This service helps to increase consumer awareness and technical competence throughout the industry.

Magmaweld strives for customer satisfaction and process excellence. In order to satisfy customer needs, all questions and remarks about products, training, welding technologies, welding procedures, standards, work safety and automation are processed through the call center at +90 444WELD (4449353) or through live support from www.magmaweld.com where the relevant information is directed to Magmaweld's experts.



Welding Consumables Factory
Organize Sanayi Bölgesi 2. Kısım, Manisa, Turkey



Welding Machines and Automation Factory
Organize Sanayi Bölgesi 5. Kısım, Manisa, Turkey

CONTENTS

STICK ELECTRODES	1
Rutile, Basic ve High Efficiency Electrodes	7
Cellulosic Electrodes	15
Low Alloyed, High Strenght and Creep Resistance Steel Electrodes	17
Stainless Steel Electrodes	29
Aluminium Alloy Electrodes	41
Copper Alloy Electrode	43
Electrodes for Cast Irons	43
Nickel Alloy Electrodes	45
Hardfacing Electrodes	47
Cutting and Gouging Electrodes	55
GAS ARC TUNGSTEN (TIG) AND OXY-ACETYLENE WELDING RODS	57
Unalloyed Steel TIG and Oxy-Acetylene Welding Rods	59
Low-Alloyed, High Strength and Creep Resistant Steel Welding TIG Rods	61
Stainless Steel TIG Welding Rods	67
Aluminium Alloy TIG Welding Rods	75
Copper Alloy TIG Welding Rods	77
Nickel Alloy TIG Welding Rods	77
Hardfacing TIG Rods	79
GAS METAL ARC (MIG/MAG) WELDING WIRES	81
Unalloyed Steel MIG/MAG Welding Wires	83
Low-Alloyed, High Strength and Creep Resistant Steel MIG/MAG Welding Wires	85
Stainless Steel MIG Welding Wires	89
Aluminium Alloy MIG Welding Wires	95
Copper Alloy MIG Welding Wires	97
Nickel Alloy MIG Welding Wires	97
Hardfacing MIG/MAG Welding Wires	99

FLUX CORED WELDING WIRES 101

Unalloyed Steel Flux Cored Welding Wires	103
Low Alloyed, High Strength and Creep Resistant Steel Flux Cored Welding Wires	105
Hardfacing Flux Cored Wires	109
Hardfacing SAW Flux Cored Wires	121

SUBMERGED ARC WELDING (SAW) WIRES and FLUXES 125

Unalloyed and Low-Alloyed Steel SAW Wires	127
Unalloyed and Low-Alloyed Steel SAW Fluxes	132
Stainless Steel SAW Wires	141
Stainless Steel SAW Fluxes	147
Hardfacing SAW Fluxes	149

APPENDIX 153

Iron-Carbon Phase Diagram-Steel Section	153
Properties of Some Important Metals	154
The Effects of Alloy Elements on the Properties of Steels	154
Pre-Heating, Interpass Temperature And Cooling Rate	156
Carbon Equivalent (CE) And Pre-Heating Temperature	158
Schaeffler Diagram	159
Delong Diagram	159
Protective Gases - EN ISO 14175	160
Welding Positions - EN ISO 6947 – ASME Sec. IX	161
Symbols –Positions – Type of Current and Polarity	162
Hardness Conversion Table - EN 18265	163
Metric Conversion Coefficients	164
Packing Information	166
Alphabetic Product Index	170
Approvals and Certificates	172

STICK ELECTRODES

STICK ELECTRODES

Rutile, Basic ve High Efficiency Electrodes

Product Name	AWS / ASME SFA - 5.1/5.5	EN ISO 2560-A	TS EN ISO 2560-A	Page Number
ESR 11	E6013	E 38 0 RC 11	E 38 0 RC 11	7
ESR 12	E6012	E 38 0 RC 11	E 38 0 RC 11	7
ESR 13	E6013	E 42 0 RR 12	E 42 0 RR 12	7
ESR 14	E7014	E 42 0 RR 12	E 42 0 RR 12	7
ESA 20	E6027	E 38 2 RA 73	E 38 2 RA 73	9
ESR 30	E6013	E 38 A RR 12	E 38 A RR 12	9
ESR 35	E6013	E 38 2 RB 12	E 38 2 RB 12	9
ESB 40	E7016	E 42 3 B 32 H10	E 42 3 B 32 H10	9
ESB 42	E7016 H8	E 42 4 B 12 H10	E 42 4 B 12 H10	9
ESB 44	E7016 H8	E 38 2 B 12 H10	E 38 2 B 12 H10	11
ESB 45	E7015	E 42 4 B 22 H5	E 42 4 B 22 H5	11
ESB 48	E7018 H8	E 42 3 B 42 H10	E 42 3 B 42 H10	11
ESB 50	E7018 H8	E 42 3 B 42 H5	E 42 3 B 42 H5	11
ESB 52	E7018-1 H4R	E 42 5 B 42 H5	E 42 5 B 42 H5	11
ESH 160R	E7024	E 42 A RR 73	E 42 A RR 73	13
ESH 160B	E7028 H8	E 38 5 B 73 H10	E 38 5 B 73 H10	13
ESH 180R	E7024	E 38 A RR 73	E 38 A RR 73	13

Cellulosic Electrodes

Product Name	AWS / ASME SFA - 5.1/5.5	EN ISO 2560-A	TS EN ISO 2560-A	Page Number
ESC 60	E6010	E 42 2 C 21	E 42 2 C 21	15
ESC 61	E6011	E 35 2 C 21	E 35 2 C 21	15
ESC 70G	E7010-G	E 42 2 C 21	E 42 2 C 21	15
ESC 80G	E8010-G	E 42 3 1Ni C 21	E 42 3 1Ni C 21	15
ESC 90G	E9010-G	E 50 2 1NiMo C 21	E 50 2 1NiMo C 21	15

STICK ELECTRODES

Low Alloyed, High Strenght and Creep Resistance Steel Electrodes

Product Name	AWS / ASME SFA - 5.1/5.5	EN ISO 2560-A/ 18275--A/-B 3580-A/-B	TS EN ISO 2560-A/B 18275--A/B 3580-A/B	Page Number
EM 138	E7018-G H4	E 46 6 1Ni B 42 H5	E 46 6 1Ni B 42 H5	17
EM 140	E7018-G H4R	E 42 4 Z 1Ni B 42 H5	E 42 4 Z 1Ni B 42 H5	17
EM 150	E8018-C3	E 46 6 1Ni B 42	E 46 6 1Ni B 42	17
EM 150W	E8018-W2	E 50 6 Z 1Ni B 42	E 50 6 Z 1Ni B 42	17
EM 160	E8018-G H4	E 50 6 Mn1Ni B 42 H5	E 50 6 Mn1Ni B 42 H5	17
EM 165	E9018-G H4R	E 55 5 Mn1NiMo B 42 H5 E 55 5 Mn1NiMo B T 42 H5	E 55 5 Mn1NiMo B 42 H5 E 55 5 Mn1NiMo B T 42 H5	19
EM 170	E9018-G H4	E 50 6 Mn1Ni B 42 H5	E 50 6 Mn1Ni B 42 H5	19
EM 171	E8018-C1 H4	E 46 6 2Ni B 42 H5	E 46 6 2Ni B 42 H5	19
EM 172	E8018-C2	E 46 6 3Ni B 42	E 46 6 3Ni B 42	19
EM 175	E10018-G H4	E 69 4 Mn2NiCrMo B 42 H5	E 69 4 Mn2NiCrMo B 42 H5	19
EM 176	E9018-G	E 62 6 Mn2NiMo B 42	E 62 6 Mn2NiMo B 42	21
EM 180	E11018-G H4	E 69 6 Mn2NiCrMo B 42 H5	E 69 6 Mn2NiCrMo B 42 H5	21
EM 181	E11018-M	-	-	21
EM 201	E8013-G	E Mo R 12	E Mo R 12	21
EM 202	E7018-A1 H8	E Mo B 42 H5	E Mo B 42 H5	21
EM 203	E7018-A1 H4	E Mo B 42 H5	E Mo B 42 H5	23
EM 206	E9018-D1	E Z Mo B 42	E Z Mo B 42	23
EM 211	E8013-G	E CrMo1 R 12	E CrMo1 R 12	23
EM 212	E8018-B2 H4R	E CrMo1 B 42 H5	E CrMo1 B 42 H5	23
EM 222	E9018-B3	E CrMo2 B 42 H5	E CrMo2 B 42 H5	23
EM 223	E9016-B3	E CrMo2 B 12 H5	E CrMo2 B 12 H5	25
EM 235	E8015-B6 H4R	E CrMo5 B 42 H5	E CrMo5 B 42 H5	25
EM 243	E12018-G	-	-	25
EM 251	-	-	-	25
EM 253	E11018-G	-	-	25
EM 255	-	E CrMoV1 B 42 H10	E CrMoV1 B 42 H10	27
EM 285	E8015-B8 H4R	E (CrMo9) B 42 H5	E (CrMo9) B 42 H5	27
EM 295	E9015-B91 H4R	E (CrMo91) B 42 H5	E (CrMo91) B 42 H5	27
EM 298	E9018-B91 H4	E (CrMo91) B 42 H5	E (CrMo91) B 42 H5	27

STICK ELECTRODES

Stainless Steel Electrodes

Product Name	AWS / ASME SFA - 5.4	EN ISO 3581-A	TS EN ISO 3581-A	Page Number
EI 307R	~E307-16	E 18 8 Mn R 12	E 18 8 Mn R 12	29
EI 307B	~E307-15	E 18 8 Mn B 22	E 18 8 Mn B 22	29
EIS 307	~E307-26	E 18 8 Mn R 53	E 18 8 Mn R 53	29
EI 308L	E308L-16	E 19 9 L R 12	E 19 9 L R 12	29
EI 308LB	E308L-15	E 19 9 L B 22	E 19 9 L B 22	29
EI 308LRS	E308L-17	E 19 9 L R 12	E 19 9 L R 12	31
EI 308Mo	E308Mo-15	E 20 10 3 B 22	E 20 10 3 B 22	31
EI 308H	E308H-16	E 19 9 H R 12	E 19 9 H R 12	31
EIS 308	E308-26	E 19 9 R 53	E 19 9 R 53	31
EI 309L	E309L-16	E 23 12 L R 12	E 23 12 L R 12	31
EI 309LB	E309L-15	E 23 12 L B 22	E 23 12 L B 22	33
EI 309LRS	E309L-17	E 23 12 L R 12	E 23 12 L R 12	33
EI 309MoL	E309LMo-16	E 23 12 2 L R 12	E 23 12 2 L R 12	33
EIS 309	E309-26	E (22 12) R 53	E (22 12) R 53	33
EIS 309Mo	E309Mo-26	E Z 23 12 2 L R 53	E Z 23 12 2 L R 53	33
EI 310	E310-16	E 25 20 R 32	E 25 20 R 32	35
EI 310B	E310-15	E 25 20 B 12	E 25 20 B 12	35
EI 312	E312-16	E 29 9 R 12	E 29 9 R 12	35
EI 312RS	E312-17	E 29 9 R 12	E 29 9 R 12	35
EI 316L	E316L-16	E 19 12 3 L R 32	E 19 12 3 L R 32	35
EI 316LB	E316L-15	E 19 12 3 L B 42	E 19 12 3 L B 42	37
EI 316LRS	E316L-17	E 19 12 3 L R 32	E 19 12 3 L R 32	37
EIS 316	E316-26	E 19 12 2 R 53	E 19 12 2 R 53	37
EI 318	E318-16	E 19 12 3 Nb R 32	E 19 12 3 Nb R 32	37
EI 347	E347-16	E 19 9 Nb R 32	E 19 9 Nb R 32	37
EI 347B	E347-15	E 19 9 Nb B 12	E 19 9 Nb B 12	39
EI 385	E385-16	E 20 25 5 Cu N L R 12	E 20 25 5 Cu N L R 12	39
EIS 410	E410-15	E (13) B 42	E (13) B 42	39
EIS 410NiMo	E410NiMo-15	E 13 4 B 42	E 13 4 B 42	39
EIS 430	E430-15	E 17 B 62	E 17 B 62	39
EI 2209	E2209-16	E 22 9 3 N L R 12	E 22 9 3 N L R 12	41

STICK ELECTRODES

Aluminium Alloy Electrodes

Product Name	AWS / ASME SFA - 5.3	EN ISO 18273	TS EN ISO 18273	Page Number
EAL 1100	E1100	E Al 1080 A(Al 99.8)	E Al 1080 A(Al 99.8)	41
EAL 4043	E4043	E Al 4043 (AlSi 5)	E Al 4043 (AlSi 5)	41
EAL 4047	E4047	E Al 4047 (AlSi 12)	E Al 4047 (AlSi 12)	41

Copper Alloy Electrode

Product Name	AWS / ASME SFA - 5.6	Page Number
ECU Sn7	~ECuSn-C	43

Electrodes for Cast Irons

Product Name	AWS / ASME SFA - 5.15	EN ISO 1071	TS EN ISO 1071	Page Number
ENI 400 (Ni)	ENi-CI	E C Ni-CI 3	E C Ni-CI 3	45
ENI 402 (Ni)	ENi-CI	E C Ni-CI 3	E C Ni-CI 3	45
ENI 404 (Mo)	ENiCu-B	E C NiCu-B 3	E C NiCu-B 3	45
ENI 406 (Mo)	ENiCu-B	E C NiCu-B 3	E C NiCu-B 3	45
ENI 412	ENi-CI	E C Ni-CI 3	E C Ni-CI 3	45
ENI 416 (NiFe)	ENiFe-CI	E C NiFe-CI 3	E C NiFe-CI 3	47

Nickel Alloy Electrodes

Product Name	AWS / ASME SFA - 5.11	EN ISO 14172	TS EN ISO 14172	Page Number
ENI 422	ENiCrFe-3	E Ni 6182	E Ni 6182	43
ENI 424	~ENiCrMo-4	E Ni 6275	E Ni 6275	43
ENI 440	ENiCu-7	E Ni 4060	E Ni 4060	43

STICK ELECTRODES

Hardfacing Electrodes

Product Name	AWS / ASME SFA - 5.3	EN ISO 18273	TS EN ISO 18273	DIN 8555*	Page Number
EH 245	EFeMn-A	E Fe9	E Fe9	E 7-UM-200-KP	47
EH 247	EFeMn-C	E Z Fe9	E Z Fe9	~E 7-UM-200-KP	47
EH 250	~EFeMnCr	E Z Fe9	E Z Fe9	E 7-UM-250-KPR	47
EH 330	-	E Fe1	E Fe1	E 1-UM-300 P	49
EH 340	-	E Fe1	E Fe1	E 1-UM-400 P	49
EH 350	-	E Z Fe2	E Z Fe2	~E 2-UM-50-GP	49
EH 360R	-	E Fe8	E Fe8	E 6-UM-60-GPT	49
EH 360B	-	E Fe8	E Fe8	E 6-UM-60-GPT	49
EH 360Si	-	E Z Fe2	E Z Fe2	~E 2-UM-60-G	51
EH 380	E Fe6	E Fe4	E Fe4	E 4-UM-60-ST	51
EH 382	-	E Fe3	E Fe3	E 3-UM-45-ST	51
EH 384	-	E Fe3	E Fe3	E 3-UM-60-ST	51
EH 515	-	E Fe14	E Fe14	E 10-UM-60-CGRZ	51
EH 528	-	E Fe15	E Fe15	E 10-UM-65-GR	53
EH 531	-	E Fe15	E Fe15	E 10-UM-65-GR	53
EH 540	-	E Fe16	E Fe16	E 10-UM-65-GRZ	53
EH 801	ECoCr-C	E Co3	E Co3	E 20-UM-55-CSTZ	53
EH 806	ECoCr-A	E Co2	E Co2	E 20-UM-40-CTZ	53
EH 812	ECoCr-B	E Co3	E Co3	E 20-UM-50-CTZ	55

*This standard is no longer valid. Added for informational purposes.

Cutting and Gouging Electrodes

Product Name	Product Type	Page Number
EC 900	Gouging Electrode	55
ECUT	Cutting Electrode	55
ECUT - S	Cutting and Gouging Electrode	55

STICK ELECTRODES





Rutile, Basic ve High Efficiency Electrodes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>ESR 11</p> <p>AWS/ASME SFA - 5.1 E6013 EN ISO 2560 - A E 38 0 RC 11 TS EN ISO 2560 - A E 38 0 RC 11</p>	<p>Especially suitable for welding in sheets thinner than 5 mm, galvanized sheets and tubes, primer painted, painted and slightly rusty steels and in production of tanks and boilers, tube installations. Very easily operated in positional welding, including vertically-down. Good gap-bridging. Smooth arc, well suited for tack-welding due to its easy arc striking and re-striking properties. Possible to use equally well both with AC and DC. Welds are smooth, slightly concave and blending into base metal without undercutting. Slag is self-releasing.</p>	   If required 1 Hour
<p>ESR 12</p> <p>AWS/ASME SFA - 5.1 E6012 EN ISO 2560 - A E 38 0 RC 11 TS EN ISO 2560 - A E 38 0 RC 11</p>	<p>Especially suitable for welding in sheets thinner than 5 mm, galvanized sheets and tubes, primer painted, painted and slightly rusty steels and in production of tanks and boilers, tube installations. Very easily operated in positional welding, including vertically-down. Good gap-bridging even at wide root openings. Smooth arc, well suited for tack-welding due to its easy arc striking and re-striking properties. Possible to use equally well both with AC and DC. Welds are smooth and blending into base metal without undercutting.</p>	   If required 1 Hour
<p>ESR 13</p> <p>AWS/ASME SFA - 5.1 E6013 EN ISO 2560 - A E 42 0 RR 12 TS EN ISO 2560 - A E 42 0 RR 12</p>	<p>Suitable for joining and repair welding of light steel fabrications, iron works, wrought iron works, agricultural machines, boiler, chassis of vehicles. Used in all position except vertical-down. Particularly suited for the welding of horizontal fillets. Very smooth weld bead appearance, with easy arc striking and re-striking properties, quite and stable arc with fine-droplet metal transfer. Possible to use equally well both with AC and DC. Slag is completely self-releasing.</p>	   If required 1 Hour
<p>ESR 14</p> <p>AWS/ASME SFA - 5.1 E7014 EN ISO 2560 - A E 42 0 RR 12 TS EN ISO 2560 - A E 42 0 RR 12</p>	<p>Preferably used in mild steel fabrication, sheet metal and ornamental iron works on poor fit up joints. Due to its iron powder addition in covering, particularly suited for the welding of horizontal fillets grooves with higher speed. Suitable for all position welding except vertical-down. High current carrying capacity, low spatter. Quite, stable arc characteristics with fine and fast droplet metal transfer. Very easy arc striking and re-striking. Very smooth welds blending into base metal without undercuts. Slag is completely self-releasing. Possible to use equally well both with AC and DC.</p>	   If required 1 Hour

Typical Chemical Analysis of All-Weld Metal (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Dimension (mm)	Packing Weigth (kg) Box Type
C: 0.10	480	550	25	0°C: 55	2.00 x 300	1.00 kg - Cardboard / Plastic 2.50 kg - Cardboard 5.00 - 6.50 kg - Cardboard
Si: 0.45					2.00 x 350	
Mn: 0.70					2.50 x 300	
					2.50 x 350	
					3.25 x 350	
	4.00 x 350					
	4.00 x 450					
	5.00 x 350					
	5.00 x 450					
C: 0.10	470	540	26	0°C: 47	2.00 x 300	2.50 kg - Cardboard 5.00 - 6.50 kg - Cardboard
Si: 0.35					2.50 x 350	
Mn: 0.75					3.25 x 350	
					4.00 x 350	
					5.00 x 450	
	4.00 x 350					
	5.00 x 450					
	5.00 x 450					
C: 0.07	500	560	28	0°C: 50	2.00 x 300	1.00 kg - Cardboard / Plastic 2.50 kg - Cardboard 5.00 - 6.50 kg - Cardboard
Si: 0.45					2.00 x 350	
Mn: 0.60					2.50 x 350	
					3.25 x 350	
					4.00 x 350	
	4.00 x 450					
	5.00 x 350					
	5.00 x 450					
C: 0.07	480	560	28	-20°C: 40 0°C: 70	2.50 x 350	2.50 kg - Cardboard 5.00 - 6.50 kg - Cardboard
Si: 0.45					3.25 x 350	
Mn: 0.50					4.00 x 350	
					4.00 x 450	
					5.00 x 350	
	5.00 x 450					
	5.00 x 450					

STICK ELECTRODES





Rutile, Basic ve High Efficiency Electrodes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>ESA 20</p> <p>AWS/ASME SFA - 5.1 E6027 EN ISO 2560 - A E 38 2 RA 73 TS EN ISO 2560 - A E 38 2 RA 73</p>	<p>Acid-rutile coated, high efficiency electrode having a weld metal approx. 165 %. Especially designed for welding fillets and narrow angle grooves. Produces complete root fusion and equal-leg fillet welds. Suitable for welding of galvanized, primer painted and slightly rusted components. Due to its low Silicon (Si) content, weld metal is also suited for subsequent galvanizing, enameling and plastic coating after welding. Provides very smooth welds without undercut. Slag is easily released, even from narrow angles. Welds are of X-ray quality.</p>	   If required 1 Hour
<p>ESR 30</p> <p>AWS/ASME SFA - 5.1 E6013 EN ISO 2560 - A E 38 A RR 12 TS EN ISO 2560 - A E 38 A RR 12</p>	<p>Rutile type heavy coated electrode which is especially used in fabrication and repair welds of molten zinc bath made of Armco iron and very low carbon steels. Weld metal ensures high crack resistance against the effect of molten zinc. Possible to use equally well both with AC and DC.</p>	   If required 1 Hour
<p>ESR 35</p> <p>AWS/ASME SFA - 5.1 E6013 EN ISO 2560 - A E 38 2 RB 12 TS EN ISO 2560 - A E 38 2 RB 12</p>	<p>Rutile-basic type coated electrode, particularly suitable for welding root passes and positional welding in fabrication of pipes, boilers and tanks. Also suitable for depositing backing-up beads in submerged arc welding. Owing to its low Si-content, weld metal is suited for subsequent galvanizing and enamelling.</p>	   If required 1 Hour
<p>ESB 40</p> <p>AWS/ASME SFA - 5.1 E7016 EN ISO 2560 - A E 42 3 B 32 H10 TS EN ISO 2560 - A E 42 3 B 32 H10</p>	<p>Suitable for repair welding on difficult to weld steels and repair welding of steel with unknown composition. Heavy coated basic electrode produce high tensile strength weld metal with excellent toughness values makes this electrode suitable for welding restrained structural members and large weld cross sections. Also preferred for buffer layer applications on steels before hardfacing and for welding of cast irons with high preheat.</p>	   If required 2 Hour
<p>ESB 42</p> <p>AWS/ASME SFA - 5.1 E7016 H8 EN ISO 2560 - A E 42 4 B 12 H10 TS EN ISO 2560 - A E 42 4 B 12 H10</p>	<p>Multi-purpose electrode for assembly work, workshop and maintenance welding. Particularly used for repair welding of earthmoving equipment booms and approved for rail joint welding. Suitable for root passes as well as positional welding. Smooth and clean welds, merging into base metal without undercuts. Good gap bridging properties. Welds are of X-ray quality.</p>	   Gerektiginde 2 Saat

Typical Chemical Analysis of All-Weld Metal (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Dimension (mm)	Packing Weigth (kg) Box Type
C: 0.07						
Si: 0.45	450	530	24	20°C: 100 -20°C: 60	3.25 x 350 4.00 x 450 5.00 x 450	2.50 kg - Cardboard 5.00 - 6.50 kg - Cardboard
Mn: 1.15						
C: 0.02						
Si: 0.15	380	440	25	20°C: 70	2.50 x 350 3.25 x 350 4.00 x 350 5.00 x 350	2.50 kg - Cardboard 5.00 kg - Cardboard
Mn: 0.40						
C: 0.08						
Si: 0.20	480	530	23	-20°C: 50 0°C: 60 20°C: 100	2.50 x 350 3.25 x 350 4.00 x 350 5.00 x 450	2.50 kg - Cardboard 5.00 - 6.50 kg - Cardboard
Mn: 0.50						
C: 0.08						
Si: 0.30	500	570	28	-30°C: 100	2.50 x 350 3.25 x 350 4.00 x 350 5.00 x 450	2.50 kg - Cardboard 5.00 - 6.50 kg - Cardboard
Mn: 1.10						
C: 0.06						
Si: 0.35	480	550	28	-40°C: 70 -20°C: 120	2.50 x 350 3.25 x 350 4.00 x 350 4.00 x 450	2.50 kg - Cardboard 5.00 - 6.50 kg - Cardboard
Mn: 0.85						

STICK ELECTRODES










Rutile, Basic ve High Efficiency Electrodes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>ESB 44</p> <p>AWS/ASME SFA - 5.1 E7016 H8 EN ISO 2560 - A E 38 2 B 12 H10 TS EN ISO 2560 - A E 38 2 B 12 H10</p>	<p>Suitable for fabrication and repair welding of dynamically loaded steel constructions, machines and agricultural equipments, workshop and maintenance welding. Smooth and clean welds, blending into base metal without undercuts. Excellent gap bridging properties. The double covering of this electrode produces a stable, concentrated and directed arc, thus being ideally suited for root pass and positional welding and is suited for AC welding. Welds are of X-ray quality.</p>	   If required 2 Hour
<p>ESB 45</p> <p>AWS/ASME SFA - 5.1 E7015 EN ISO 2560 - A E 42 4 B 22 H5 TS EN ISO 2560 - A E 42 4 B 22 H5</p>	<p>Multi-purpose electrode for pipe joining, positional welding, multi-pass welding of difficult to weld steels, assembly work, workshop and maintenance welding. Especially used for repair welding of earthmoving equipment booms and joining of rails. Has a stable, concentrated arc and high penetration. Smooth and clean welds, merging into base metal without undercuts. Good gap bridging properties. Welds are of X-ray quality.</p>	   If required 2 Hour
<p>ESB 48</p> <p>AWS/ASME SFA - 5.1 E7018 H8 EN ISO 2560 - A E 42 3 B 42 H10 TS EN ISO 2560 - A E 42 3 B 42 H10</p>	<p>Suitable for welding fabrication of dynamically loaded steel constructions, bridge, shipbuilding, pipe-line, pressure vessels, tanks, boiler and machines where high toughness is required. Weld metal recovery is appx. 115 %. Smooth and clean welds merging into base metal without undercuts. Good gap bridging properties. Welds are of X-ray quality. It is suited for depositing buffer layers on higher carbon steels.</p>	   If required 2 Hour
<p>ESB 50</p> <p>AWS/ASME SFA - 5.1 E7018 H8 EN ISO 2560 - A E 42 3 B 42 H5 TS EN ISO 2560 - A E 42 3 B 42 H5</p>	<p>Suitable for welding fabrication of dynamically loaded heavy steel constructions, bridge, shipbuilding, pipe line, pressure vessels, tanks, boiler and machines where mechanical properties are required. Weld metal exhibits good toughness properties down to -50°C and produce tough and crack-free welded joints even on steels having a carbon content of up to 0.4%. Weld metal recovery amounts to approx. 120%. Welds are of X-ray quality. Electrode is suitable for depositing buffer layers on higher carbon steels.</p>	   If required 2 Hour
<p>ESB 52</p> <p>AWS/ASME SFA - 5.1 E7018-1 H4R EN ISO 2560 - A E 42 5 B 42 H5 TS EN ISO 2560 - A E 42 5 B 42 H5 CSA W48-14 E4918-1H4</p>	<p>Suitable for welding of steel constructions, bridge, dam, thermal power plants, petrochemical industry, shipbuilding, high strength pipe-lines, pressure vessels, tanks, which are dynamically loaded and require high mechanical properties. The weld metal has a very low hydrogen content and is resistant to ageing. Produces tough and crack-free welded joints, also suite for welding steels having a carbon content of up to 0.6 % and joining of rails. Good operating characteristic, also in root pass and positional welding. Very good gap bridging properties. Welds are of X-ray quality.</p>	   If required 2 Hour

Typical Chemical Analysis of All-Weld Metal (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Dimension (mm)	Packing Weigth (kg) Box Type
C: 0.06	450	550	25	-30°C: 55 -20°C: 70	2.00 x 350	1.00 kg - Cardboard / Plastic 2.50 kg - Cardboard 5.00 - 6.50 kg - Cardboard
Si: 0.65					2.50 x 350	
					3.25 x 350	
					3.25 x 450	
					4.00 x 350	
Mn: 1.00					4.00 x 450	
					5.00 x 450	
C: 0.04	480	550	28	-30°C: 70	2.50 x 350	2.50 kg - Cardboard 5.00 - 6.50 kg - Cardboard
Si: 0.40					3.25 x 350	
					4.00 x 350	
					4.00 x 450	
					5.00 x 350	
Mn: 1.00						
C: 0.08	460	560	28	-40°C: 90 -30°C: 140	2.00 x 350	1.00 kg - Cardboard / Plastic 2.50 kg - Cardboard / Vacuum 5.00 - 6.50 kg - Cardboard
Si: 0.40					2.50 x 350	
					3.25 x 350	
					3.25 x 450	
					4.00 x 350	
Mn: 1.10					4.00 x 450	
					5.00 x 350	
					5.00 x 450	
					6.00 x 450	
C: 0.07	470	560	29	-50°C: 60 -30°C: 100	2.00 x 300	2.50 kg - Cardboard / Vacuum 5.00 - 6.50 kg - Cardboard
Si: 0.35					2.00 x 350	
					2.50 x 350	
					3.25 x 350	
					3.25 x 450	
Mn: 1.45					4.00 x 350	
					4.00 x 450	
					5.00 x 450	
					6.00 x 450	
C: 0.07	460	550	28	-50°C: 100 -46°C: 110	2.00 x 300	2.50 kg - Cardboard / Vacuum 5.00 - 6.50 kg - Cardboard
Si: 0.40					2.00 x 350	
					2.50 x 350	
					3.25 x 350	
					3.25 x 450	
Mn: 1.20					4.00 x 350	
					4.00 x 450	
					5.00 x 450	
					6.00 x 450	

STICK ELECTRODES




Rutile, Basic ve High Efficiency Electrodes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>ESH 160R</p> <p>AWS/ASME SFA - 5.1 E7024 EN ISO 2560 - A E 42 A RR 73 TS EN ISO 2560 - A E 42 A RR 73</p>	<p>Suitable for welding of large sections and fillets in shipbuilding with it's 165% recovery. Produces very smooth, concave and clean welds, merging into base metal without undercuts. Suitable for welding prepainted plates. Easy arc striking and restriking. Slag is self-releasing in most cases.</p>	   If required 1 Hour
<p>ESH 160B</p> <p>AWS/ASME SFA - 5.1 E7028 H8 EN ISO 2560 - A E 38 5 B 73 H10 TS EN ISO 2560 - A E 38 5 B 73 H10</p>	<p>Suitable for welding of large sections and fillets with it's 165% recovery. Weld metal has high toughness and crack resistance. Produces very smooth and clean welds, merging into base metal without undercuts. Suitable for welding prepainted plates. Slag removal is easy. Welds are of X-ray quality.</p>	   If required 2 Hour
<p>ESH 180R</p> <p>AWS/ASME SFA - 5.1 E7024 EN ISO 2560 - A E 38 A RR 73 TS EN ISO 2560 - A E 38 A RR 73</p>	<p>Heavy coated, rutile type high-efficiency electrode having a weld metal recovery of approx. 180 %. It is suited to produce long fillet welds and economically filling-up large weld sections especially in shipbuilding. Suitable to use in pre-painted plates. Has a short burn-off time relatively at low current intensities. Easy arc striking and restriking. Slag is self-releasing in most cases.</p>	   If required 1 Hour

Typical Chemical Analysis of All-Weld Metal (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Dimension (mm)	Packing Weigth (kg) Box Type
C: 0.10						
Si: 0.65	530	580	24	20°C: 50	2.50 x 350 3.25 x 350 4.00 x 450 5.00 x 450 6.00 x 450	5.00 - 6.50 kg - Cardboard
Mn: 1.05						
C: 0.05						
Si: 0.50	450	520	24	-50°C: 60 -20°C: 85	3.25 x 450 4.00 x 450 5.00 x 450 6.00 x 450	6.50 kg - Cardboard
Mn: 1.10						
C: 0.07						
Si: 0.55	480	550	25	20°C: 50	2.50 x 350 3.25 x 450 4.00 x 450 5.00 x 450	5.00 - 6.50 kg - Cardboard
Mn: 0.80						

STICK ELECTRODES

Cellulosic Electrodes

Product Name and Standards		Applications and Properties	Polarity Welding Positions Re-drying Information
ESC 60 AWS/ASME SFA - 5.1 E6010 EN ISO 2560 - A E 42 2 C 21 TS EN ISO 2560 - A E 42 2 C 21		Medium coated, cellulosic electrode, especially designed for welding of pipes and plates in all positions at low welding currents. Due to its high penetration, particularly suitable for root pass and fill passes in vertical down direction. Used in pipe-line construction, shipbuilding, storage vessels and assembly works. DCEN (-) is ideal in root passes and DCEP (+) is recommended for fill and cap passes in vertical down position.	 Root Pass.  Fill Pass.   Not Applicable
ESC 61 AWS/ASME SFA - 5.1 E6011 EN ISO 2560 - A E 35 2 C 21 TS EN ISO 2560 - A E 35 2 C 21		Medium coated, cellulosic electrode, especially designed for use in AC, as well as in DC. Due to its high penetration, it is suitable for root pass and fill passes in vertical down direction. Used in shipbuilding, storage vessels, boilers, pipeline constructions, assembly and repair works in mild steels, steel casting, galvanized sheets and machinery parts. AC or DCEN (-) is ideal in root passes and AC or DCEP (+) is recommended for fill and cap passes in vertical down direction.	 Root Pass.  Fill Pass.   Not Applicable
ESC 70G AWS/ASME SFA - 5.5 E7010-G EN ISO 2560 - A E 42 2 C 21 TS EN ISO 2560 - A E 42 2 C 21		Medium coated and Ni (nickel) alloyed cellulosic type electrode, suitable for welding high strength steels, micro-alloyed and low alloyed steels and pipes. Due to its high penetration, it is suitable for root pass and fill passes in the vertical down direction. Well-suited for welding high strength unalloyed and low alloy steels in shipbuilding, storage vessels, boilers, pipe-line constructions and assembly works. DCEN (-) is ideal in root passes and DCEP (+) is recommended for fill and cap passes in vertical down position.	 Root Pass.  Fill Pass.   Not Applicable
ESC 80G AWS/ASME SFA - 5.5 E8010-G EN ISO 2560 - A E 42 3 1Ni C 21 TS EN ISO 2560 - A E 42 3 1Ni C 21		Medium coated and Ni (nickel) alloyed cellulosic type electrode for welding high strength and low alloyed steels and pipes. Due to its high penetration, it is suitable for root pass and fill passes in vertical down direction for use in pipe-line construction, shipbuilding, storage vessels and assembly works. DCEN (-) is ideal in root passes DCEP (+) is recommended for fill and cap passes in vertical down position.	 Root Pass.  Fill Pass.   Not Applicable
ESC 90G AWS/ASME SFA - 5.5 E9010-G EN ISO 2560-A E 50 2 1NiMo C 21 TS EN ISO 2560-A E 50 2 1NiMo C 21		Medium coated and nickel (Ni) and molybdenum (Mo) alloyed cellulosic type electrode for welding high strength steels and pipes. Due to its high penetration, it is suitable for root pass and fill passes in vertical down direction for use in pipe-line construction, shipbuilding, storage vessels and assembly works. DCEN (-) is ideal in root passes DCEP (+) is recommended for fill and cap passes in vertical down position.	 Root Pass.  Fill Pass.   Not Applicable

Typical Chemical Analysis of All-Weld Metal (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Dimension (mm)	Packing Weigth (kg) Box Type
C: 0.12						
Si: 0.20	470	530	25	-30°C: 40 -20°C: 60	2.50 x 350 3.25 x 350 4.00 x 350 5.00 x 350	2.50 kg - Cardboard 5.00 kg - Cardboard 8.00 kg - TIN
Mn: 0.60						
C: 0.12						
Si: 0.20	470	530	24	-20°C: 50	2.50 x 350 3.25 x 350 4.00 x 350 5.00 x 350	2.50 kg - Cardboard 5.00 kg - Cardboard 8.00 kg - TIN
Mn: 0.55						
C: 0.15						
Si: 0.30	500	560	26	-30°C: 60 -20°C: 70	2.50 x 350 3.25 x 350 4.00 x 350 5.00 x 350	2.50 kg - Cardboard 5.00 kg - Cardboard 8.00 kg - TIN
Mn: 1.30						
Ni: 0.20						
C: 0.15						
Si: 0.25	500	570	24	-30°C: 50 -20°C: 60	2.50 x 350 3.25 x 350 4.00 x 350 5.00 x 350	2.50 kg - Cardboard 5.00 kg - Cardboard 8.00 kg - TIN
Mn: 1.00						
Ni: 1.00						
C: 0.14						
Si: 0.30	540	650	21	-30°C: 45 -20°C: 55	2.50 x 350 3.25 x 350 4.00 x 350 5.00 x 350	2.50 kg - Cardboard 5.00 kg - Cardboard 8.00 kg - TIN
Mn: 1.20						
Ni: 0.60						
Mo: 0.30						

STICK ELECTRODES

Low Alloyed, High Strength and Creep Resistance Steel Electrodes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>EM 138</p> <p>AWS/ASME SFA - 5.5 EN ISO 2560 - A TS EN ISO 2560 - A</p> <p>E7018-G H4 E 46 6 1Ni B 42 H5 E 46 6 1Ni B 42 H5</p>	<p>Basic coated electrode, producing tough and crack-free welded joints. Suitable for welding of high strength and low alloyed steels and fine grained structural steels. Weld deposit is of extremely high metallurgical purity and has a very low hydrogen content. Owing to it's double coating, electrode features a stable and concentrated arc, making especially up to 3,25 mm, are well-suited for positional welding. Welds are of X-ray quality.</p>	<p>If required 2 Hour</p>
<p>EM 140</p> <p>AWS/ASME SFA - 5.5 EN ISO 2560 - A TS EN ISO 2560 - A</p> <p>E7018-G H4R E 42 4 Z 1Ni B 42 H5 E 42 4 Z 1Ni B 42 H5</p>	<p>Basic coated electrode, designed to resist to atmospheric corrosion and to provide high charpy impact energy down to -40°C. Suitable for welding steel constructions like bridge, off-shore platforms, stadium, which are made of weathering steels and thick sections of them. Especially 2,50 mm and 3,25 mm diameter well suited for positional welding. Welds are of X-ray quality.</p>	<p>If required 2 Hour</p>
<p>EM 150</p> <p>AWS/ASME SFA - 5.5 EN ISO 2560 - A TS EN ISO 2560 - A</p> <p>E8018-C3 E 46 6 1Ni B 42 E 46 6 1Ni B 42</p>	<p>Heavy coated basic type electrode, suitable for welding steel constructions, off-shore platforms, bridge, machinery, production and in their root pass applications where low high strength steels and fine grained structural steels used. Weld metal is high crack resistance under difficult operating conditions such as dynamic loads and especially low environmental temperatures.</p>	<p>If required 2 Hour</p>
<p>EM 150W</p> <p>AWS/ASME SFA - 5.5 EN ISO 2560 - A TS EN ISO 2560 - A</p> <p>E8018-W2 E 50 6 Z 1Ni B 42 E 50 6 Z 1Ni B 42</p>	<p>Heavy coated basic type electrode, designed for welding weathering steels, like COR-TEN steels, high strength steels, particularly copper containing steels which are resistant to atmospheric corrosion. Due to its high crack resistance under difficult operating conditions such as dynamic loads, high and low environmental temperatures, suitable to use in fabrication of steel constructions like bridge, stadium, off-shore platforms. Easy to use in root and fill passes. Welds are of X-ray quality.</p>	<p>If required 2 Hour</p>
<p>EM 160</p> <p>AWS/ASME SFA - 5.5 EN ISO 2560 - A TS EN ISO 2560 - A</p> <p>E8018-G H4 E 50 6 Mn1Ni B 42 H5 E 50 6 Mn1Ni B 42 H5</p>	<p>Heavy coated basic type electrode with high efficiency, which is for welding low alloy steels, fine grained structural steels and high strength pipes. Due to it's high crack resistance under difficult conditions such as dynamic loads and service temperatures between -60°C and 450°C, it is suitable for use in heavy steel structures, off-shore platform, heavy machinery, pressure vessels, tanks, boiler production, welding and repair jobs of pipes and in their root pass applications. Welds are of X-ray quality.</p>	<p>If required 2 Hour</p>

Typical Chemical Analysis of All-Weld Metal (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Dimension (mm)	Packing Weigth (kg) Box Type		
C: 0.06	As Welded							
Si: 0.30	460	530-680	20	20°C: 190	2.50 x 350 3.25 x 350 4.00 x 350 5.00 x 450	2.50 kg - Cardboard / Vacuum 5.00 -6.50 kg - Cardboard		
Mn: 1.20				-60°C: 70				
Ni: 0.95	After Heat Treatment (580°C 15 Hour)							
	420	500-640	25	20°C: 190 -60°C: 60				
C: 0.05								
Si: 0.30								
Mn: 0.90	460	580	26	-40°C: 70	2.50 x 350 3.25 x 350 4.00 x 450 5.00 x 450	2.50 kg - Cardboard / Vacuum 5.00 -6.50 kg - Cardboard		
Ni: 1.00				-20°C: 120				
Cu: 0.60								
C: 0.04								
Si: 0.20	530	600	25	-60°C: 60	2.50 x 350	2.50 kg - Cardboard / Vacuum 5.00 -6.50 kg - Cardboard		
Mn: 1.10					3.25 x 350			
Ni: 1.00	4.00 x 450							
	6.00 x 450							
C: 0.05								
Si: 0.60								
Mn: 1.10	580	690	22	-60°C: 55	2.50 x 350	2.50 kg - Cardboard / Vacuum 5.00 -6.50 kg - Cardboard		
Cr: 0.55					3.25 x 350			
Ni: 0.70	4.00 x 450							
Cu: 0.60	5.00 x 450							
C: 0.07								
Si: 0.60	600	680	22	-60°C: 55	2.00 x 300	2.50 kg - Cardboard / Vacuum 5.00 -6.50 kg - Cardboard		
Mn: 1.75					2.50 x 350			
Ni: 0.85	4.00 x 450							
	5.00 x 450							

Low Alloyed, High Strength and Creep Resistance Steel Electrodes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>EM 165</p> <p>AWS/ASME SFA-5.5 E9018-G H4R EN ISO 18275 - A E 55 5 Mn1NiMo B 42 H5 TS EN ISO 18275 - A E 55 5 Mn1NiMo B 42 H5 EN ISO 18275 - A E 55 5 Mn1NiMo B T 42 H5 TS EN ISO 18275 - A E 55 5 Mn1NiMo B T 42 H5</p>	<p>Heavy coated basic type electrode with high efficiency, which is for welding low alloy steels, fine grained structural steels and high strength steel pipes. Provides high crack resistance under difficult conditions such as dynamic loads, impact, pressure, vibration and service temperatures between -60°C and 450°C. Weld deposit is of extremely high metallurgical purity and very low hydrogen content. Especially 2,50 mm and 3,25 mm diameter well suited for easy positional welding which makes it suitable for joint welding and repair jobs of oil and gas pipes up to X70. Welds are of X-ray quality.</p>	<p></p> <p></p> <p></p> <p>If required 2 Hour</p>
<p>EM 170</p> <p>AWS/ASME SFA - 5.5 E9018-G H4 EN ISO 2560 - A E 50 6 Mn1Ni B 42 H5 TS EN ISO 2560 - A E 50 6 Mn1Ni B 42 H5</p>	<p>Heavy coated basic type electrode with high efficiency, for welding low alloy high strength steels, fine grained structural steels and high strength steel pipes. Provides high crack resistance under difficult conditions such as dynamic loads, impact, pressure, vibration and service temperatures between -60°C and 450°C. Weld deposit is of an extremely high metallurgical purity and very low hydrogen content. Especially 2,50 mm and 3,25 mm diameter electrodes feature stable and concentrated arc, rendering it well-suited for positional welding. Suitable for welding and repair jobs up to X70 oil and gas pipes. Weld are of X-ray quality.</p>	<p></p> <p></p> <p></p> <p>If required 2 Hour</p>
<p>EM 171</p> <p>AWS/ASME SFA - 5.5 E8018-C1 H4 EN ISO 2560 - A E 46 6 2Ni B 42 H5 TS EN ISO 2560 - A E 46 6 2Ni B 42 H5</p>	<p>Heavy coated basic type electrode for welding fine grained structural steels and especially cryogenic steels, subjected to low service temperatures up to -60°C. Electrode produces tough and crack-free welded joints. Weld deposit is of extremely high metallurgical purity and very low hydrogen content. Owing to high crack resistance under difficult conditions such as dynamic loads, impact, vibration and low service temperatures, it is suitable for use in welding of storage tanks and piping. Suitable for use in root passes and joints in pipes and equipments of cold storage rooms with service temperatures down to -60°C. Electrode features a stable and concentrated arc. Especially 2,50 mm and 3,25 mm diameters are well-suited for positional welding. Welds are X-ray quality.</p>	<p></p> <p></p> <p></p> <p>If required 2 Hour</p>
<p>EM 172</p> <p>AWS/ASME SFA - 5.5 E8018-C2 EN ISO 2560 - A E 46 6 3Ni B 42 TS EN ISO 2560 - A E 46 6 3Ni B 42</p>	<p>Heavy coated basic type electrode for welding fine grained structural steels and especially cryogenic steels. Electrode produces tough and crack-free welded joints. Weld deposit is of extremely high metallurgical purity and very low hydrogen content. Owing to high crack resistance under difficult conditions such as dynamic loads and low service temperatures up to -60°C. It is suitable for use in welding of storage tanks and piping which are subjected to low temperatures. Electrode features a stable and concentrated arc. Especially 2,50 mm and 3,25 mm diameters are well-suited for positional welding. Welds are of X-ray quality.</p>	<p></p> <p></p> <p></p> <p>If required 2 Hour</p>
<p>EM 175</p> <p>AWS/ASME SFA - 5.5 E10018-G H4 EN ISO 18275 - A E 69 4 Mn2NiCrMo B 42 H5 TS EN ISO 18275 - A E 69 4 Mn2NiCrMo B 42 H5</p>	<p>Heavy coated basic type electrode for welding fine grained structural steels which have yield strength up to 690N/mm². Suitable for welding high strength steels used in fabrication of cranes, earthmoving and similar heavy construction equipments. Weld deposit is of extremely high metallurgical purity and very low hydrogen content. Electrode features a stable and concentrated arc. Especially 2,50 mm and 3,25 mm diameter well suited for easy positional welding. Welds are of X-ray quality. Producing tough and crack-free welded joints. If normalizing is required after welding, EM 176 should be used.</p>	<p></p> <p></p> <p></p> <p>If required 2 Hour</p>

Typical Chemical Analysis of All-Weld Metal (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Dimension (mm)	Packing Weigth (kg) Box Type
C: 0.06	As Welded					
Si: 0.40	570	650	20	-60°C: 40 -50°C: 50	2.50 x 350 3.25 x 350 3.25 x 450 4.00 x 450	2.50 kg - Cardboard / Vacuum 5.00 -6.50 kg - Cardboard
Mn: 1.75	After Heat Treatment (590°C 1 Hour)					
Ni: 0.90	650	740	24	-60°C: 40 -50°C: 50	5.00 x 450 6.00 x 450	
Mo: 0.45						
C: 0.05						
Si: 0.40	570	650	25	-60°C: 60	2.50 x 350 3.25 x 350 3.25 x 450 4.00 x 350 4.00 x 450 5.00 x 350 5.00 x 450	2.50 kg - Cardboard / Vacuum 5.00 -6.50 kg - Cardboard
Mn: 1.70						
Ni: 1.00						
C: 0.05	As Welded					
Si: 0.30	490	580	27	-60°C: 100	2.50 x 350 3.25 x 350 4.00 x 450 5.00 x 450 6.00 x 450	2.50 kg - Cardboard / Vacuum 5.00 -6.50 kg - Cardboard
Mn: 1.00	After Heat Treatment (605°C 1 Saat)					
Ni: 2.40	470	550	29	-60°C: 120		
C: 0.05						
Si: 0.30	500	570	22	-60°C: 50	2.50 x 350 3.25 x 350 4.00 x 450	2.50 kg - Cardboard / Vacuum 5.00 -6.50 kg - Cardboard
Mn: 0.90						
Ni: 3.50						
C: 0.05						
Si: 0.30						
Mn: 1.60	730	820	19	-40°C: 85	2.50 x 350 3.25 x 350 4.00 x 450 5.00 x 450 6.00 x 450	2.50 kg - Cardboard / Vacuum 5.00 -6.50 kg - Cardboard
Cr: 0.45						
Ni: 2.30						
Mo: 0.40						

STICK ELECTRODES





Low Alloyed, High Strenght and Creep Resistance Steel Electrodes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>EM 176</p> <p>AWS/ASME SFA - 5.5 E9018-G EN ISO 18275 - A E 62 6 Mn2NiMo B 42 TS EN ISO 18275 - A E 62 6 Mn2NiMo B 42</p>	<p>Heavy coated basic type electrode for welding fine grained and low alloy steels which will be subsequently normalized or normalized + tempered after welding. Weld deposit is tough and crack-free and has a low hydrogen content. Especially 2,50 mm and 3,25 mm diameters well suited for easy positional welding. Welds are of X-ray quality.</p>	   If required 2 Hour
<p>EM 180</p> <p>AWS/ASME SFA - 5.5 E11018-G H4 EN ISO 18275 - A E 69 6 Mn2NiCrMo B 42 H5 TS EN ISO 18275 - A E 69 6 Mn2NiCrMo B 42 H5</p>	<p>Heavy coated basic type electrode for welding fine grained and high strength structural steels which have yield strength up to 690N/mm² and tensile strength to 850N/mm². Suitable for welding high strength steels used in fabrications of crane, earthmoving equipment, heavy machinery parts. Due to its high toughness, crack resistance even under difficult operating conditions such as dynamic loads, high and low environmental temperatures, it is suitable for use in steel constructions, pressure vessels, tanks, boilers and special fabrications and in their root pass applications with safety. Weld deposit is of extremely high metallurgical purity and very low hydrogen content. The electrode features a stable and concentrated arc. Especially 2,50 mm and 3,25 mm diameters well suited for easy positional welding. Welds are of ray quality.</p>	   If required 2 Hour
<p>EM 181</p> <p>AWS/ASME SFA - 5.5 E11018-M</p>	<p>Heavy coated basic type electrode for welding low alloy high strength steels, particularly fine grained structural steels. Due to its crack resistance even under difficult operating conditions such as dynamic loads, high and low environmental temperatures, it is suitable for use in steel constructions, pressure vessels, tanks, boiler and special fabrications such as submarines and ships where military specifications are required. It can also be used for root pass applications of these constructions with safety. Weld metal is tough, resistant to cracking and has X-ray.</p>	   If required 2 Hour
<p>EM 201</p> <p>AWS/ASME SFA - 5.5 E8013-G EN ISO 3580 - A E Mo R 12 TS EN ISO 3580 - A E Mo R 12</p>	<p>Rutile type, heavy coated electrode for welding creep resistant steels employed in the construction of pressure vessels, boilers and pipes, subjected to operating temperatures of up to 500°C. Due to its rutile covering, also possible to work in alternatig current (AC). Easy arc striking and re-striking. Very smooth and clean welds, blending into base without undercuts. Preheating, interpass temperature and post-weld heat treatment shall be done according to base metal used.</p>	   If required 1 Hour
<p>EM 202</p> <p>AWS/ASME SFA - 5.5 E7018-A1 H8 EN ISO 3580 - A E Mo B 42 H5 TS EN ISO 3580 - A E Mo B 42 H5</p>	<p>Basic type, heavy coated electrode for welding creep resistant steels employed in the fabrication of pressure vessels, boilers and pipes, subjected to operating temperatures of up to 500°C. Welds are of X-ray quality. Preheating, interpass temperature and post-weld heat treatment shall be done according to base metal used.</p>	   If required 2 Hour

Typical Chemical Analysis of All-Weld Metal (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Dimension (mm)	Packing Weigth (kg) Box Type
C: 0.05						
Si: 0.30						
Mn: 1.60	695	765	19	-60°C: 60	3.25 x 350 4.00 x 450 5.00 x 450	2.50 kg - Cardboard / Vacuum 5.00 -6.50 kg - Cardboard
Ni: 2.00						
Mo: 0.40						
C: 0.05						
Si: 0.30						
Mn: 1.60	775	890	18	-60°C: 50	2.50 x 350 3.25 x 350 4.00 x 450 5.00 x 450 6.00 x 450	2.50 kg - Cardboard / Vacuum 5.00 -6.50 kg - Cardboard
Cr: 0.40						
Ni: 2.20						
Mo: 0.45						
C: 0.05						
Si: 0.30						
Mn: 1.80	825	865	19	-50°C: 85	2.50 x 350 3.25 x 350 4.00 x 450 5.00 x 450	2.50 kg - Cardboard / Vacuum 5.00 -6.50 kg - Cardboard
Cr: 0.30						
Ni: 2.00						
Mo: 0.35						
C: 0.07	After Heat Treatment (620°C 1 Hour)					
Si: 0.35	540	620	23	20°C: 60	2.50 x 350 3.25 x 350 4.00 x 450 5.00 x 450	2.50 kg - Cardboard / Vacuum 5.00 -6.50 kg - Cardboard
Mn: 0.50						
Mo: 0.45						
C: 0.05	As Welded					
Si: 0.30	485	580	27	20°C: 175	2.50 x 350 3.25 x 350 4.00 x 450 5.00 x 450	2.50 kg - Cardboard / Vacuum 5.00 -6.50 kg - Cardboard
Mn: 0.65	After Heat Treatment (620°C 1 Hour)					
Mo: 0.50	500	575	26	20°C: 160		

STICK ELECTRODES

Low Alloyed, High Strength and Creep Resistance Steel Electrodes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>EM 203</p> <p>AWS/ASME SFA - 5.5 E7018-A1 H4 EN ISO 3580-A E Mo B 42 H5 TS EN ISO 3580-A E Mo B 42 H5</p>	<p>Basic type electrode for welding creep resistant steels subjected to operating temperatures of up to 350°C. Generally used for joining and maintenance of rotary oven plates in cement industry. Welds are of X-ray quality. Preheating, interpass temperature and post-weld heat treatment shall be done according to base metal used.</p>	<p></p> <p></p> <p></p> <p>If required 2 Hour</p>
<p>EM 206</p> <p>AWS/ASME SFA - 5.5 E9018-D1 EN ISO 3580 - A E Z Mo B 42 TS EN ISO 3580 - A E Z Mo B 42</p>	<p>Basic type electrode for welding creep resistant steels employed in the fabrication of pressure vessels, boilers and pipes, subjected to operating temperatures of up to 500°C and high strength steels with high impact resistance up to -50°C. Welds are of X-ray quality. Especially preferred for welding of thick sections where high mechanical properties, Charpy impact values and X-ray quality are required. Preheating, interpass temperature and post-weld heat treatment shall be done according to base metal used.</p>	<p></p> <p></p> <p></p> <p>If required 2 Hour</p>
<p>EM 211</p> <p>AWS/ASME SFA - 5.5 E8013-G EN ISO 3580 - A E CrMo1 R 12 TS EN ISO 3580 - A E CrMo1 R 12</p>	<p>Rutile type, heavy coated electrode for welding creep resistant steels employed in the fabrication of pressure vessels, boilers and pipes, subjected to operating temperatures of up to 570°C. Due to its rutile covering, also possible to work in alternating current (AC). Easy arc striking and restriking. Very smooth welds, blending into base metal without undercuts. For thick sections, basic covered EM 212 shall be preferred. Preheating, interpass temperature and post-weld heat treatment shall be done according to base metal used.</p>	<p></p> <p></p> <p></p> <p>If required 1 Hour</p>
<p>EM 212</p> <p>AWS/ASME SFA - 5.5 E8018-B2 H4R EN ISO 3580 - A E CrMo1 B 42 H5 TS EN ISO 3580 - A E CrMo1 B 42 H5</p>	<p>Basic type, heavy coated electrode for welding creep resistant steels employed in the fabrication of pressure vessels, boilers and pipes, subjected to operating temperatures of up to 570°C. Welds are of X-ray quality. Weld metal has a low diffusible hydrogen content (4ml/100g). Generally preferred in thick sections where high mechanical properties and X-ray quality are necessary. Preheating interpass temperature and post-weld heat treatment shall be done according to base metal used.</p>	<p></p> <p></p> <p></p> <p>If required 2 Hour</p>
<p>EM 222</p> <p>AWS/ASME SFA - 5.5 E9018-B3 EN ISO 3580 - A E CrMo2 B 42 H5 TS EN ISO 3580 - A E CrMo2 B 42 H5</p>	<p>Basic type, heavy coated electrode for welding creep resistant and high pressure hydrogen resistant steels used in construction of pressure vessels, boiler and piping subjected to operating temperatures up to 600°C. Generally preferred in thick sections with high mechanical properties and X-ray quality necessary. Has a stable arc, low spatter and smooth weld beads. Slag removal is easy. Weld metal has low diffusible hydrogen content (4ml/100g). Preheating, interpass temperature and post-weld heat treatment should be done in accordance with base metal to be welded.</p>	<p></p> <p></p> <p></p> <p>If required 2 Hour</p>

Typical Chemical Analysis of All-Weld Metal (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Dimension (mm)	Packing Weigth (kg) Box Type
C: 0.09						
Si: 0.45	510	600	26	20°C: 130	2.50 x 350	2.50 kg - Cardboard / Vacuum 5.00 -6.50 kg - Cardboard
Mn: 0.90					3.25 x 350	
					4.00 x 450	
					5.00 x 450	
Mo: 0.50						
C: 0.07						
Si: 0.50	620	700	23	-50°C: 65	2.50 x 350	2.50 kg - Cardboard / Vacuum 5.00 -6.50 kg - Cardboard
Mn: 1.40					3.25 x 350	
Ni: 0.50					4.00 x 450	
					5.00 x 450	
Mo: 0.35						
C: 0.06						
Si: 0.30	After Heat Treatment (690°C 1 Hour)					
Mn: 0.50	630	690	21	20°C: 80	2.50 x 350	2.50 kg - Cardboard / Vacuum 5.00 -6.50 kg - Cardboard
Cr: 1.05					3.25 x 350	
					4.00 x 450	
					5.00 x 450	
Mo: 0.50						
C: 0.06						
Si: 0.40	After Heat Treatment (690°C 1 Hour)					
Mn: 0.65	530	610	22	20°C: 140	2.50 x 350	2.50 kg - Cardboard / Vacuum 5.00 -6.50 kg - Cardboard
Cr: 1.25					3.25 x 350	
					4.00 x 350	
					4.00 x 450	
Mo: 0.55						
C: 0.06						
Si: 0.30	After Heat Treatment (690°C 1 Hour)					
Mn: 0.60	565	660	22	20°C: 160	2.50 x 350	2.50 kg - Cardboard / Vacuum 5.00 -6.50 kg - Cardboard
Cr: 2.20					3.25 x 350	
					4.00 x 350	
					4.00 x 450	
Mo: 1.00						

Low Alloyed, High Strenght and Creep Resistance Steel Electrodes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>EM 223</p> <p>AWS/ASME SFA - 5.5 E9016-B3 EN ISO 3580-A E CrMo2 B 12 H5 TS EN ISO 3580-A E CrMo2 B 12 H5</p>	<p>Basic type heavy coated electrode for welding creep resistant steels used in construction of pressure vessels, boiler and piping, subjected to high operating temperatures. Generally used in joining and maintenance jobs in power plants, chemical and petrochemical industries. Preheating, interpass temperature and post-weld heat treatment should be done in accordance with base metal to be welded.</p>	<p>If required 2 Hour</p>
<p>EM 235</p> <p>AWS/ASME SFA - 5.5 E8015-B6 H4R EN ISO 3580 - A E CrMo5 B 42 H5 TS EN ISO 3580 - A E CrMo5 B 42 H5</p>	<p>Basic type electrode for welding creep resistant steels. Weld metal matches the composition of steel grade 12CrMo19-5 featuring equal resistance to high-pressure hydrogen attack, creep resistance and creep rupture strength. Typical applications are : petrochemical process plants, hydrocrackers in chemical industries. Suitable to use in pressure vessels and boilers subject to operating temperatures up to 600°C. Weld metal has a low diffisuble hydrogen content (4ml/100g). Preheating, interpass temperature and post weld heat treatment should be done in accordance with base metal to be welded.</p>	<p>If required 2 Hour</p>
<p>EM 243</p> <p>AWS/ASME SFA - 5.5 E12018-G</p>	<p>Basic type electrode for welding cementation steels and 1% Cr, 2.5% Ni, 0.7% Mo containing steels and cast steels. Suitable to use in machine building and construction of apparatus, as well as for repair welding of components made of similar steels grades. Preheating, interpass temperature and post-weld heat treatment should be done in accordance with base metal to be welded.</p>	<p>If required 2 Hour</p>
<p>EM 251</p>	<p>Basic type electrode for welding and building of Cr-Ni-Mo- V containing steels and cast steels with similar composition. Suitable to use in machine building and construction of apparatus, as well as for repair welding of components made of similar steels grades. Preheating, interpass temperature and post-weld heat treatment should be done in accordance with base metal to be welded.</p>	<p>If required 2 Hour</p>
<p>EM 253</p> <p>AWS/ASME SFA - 5.5 E11018-G</p>	<p>Basic type electrode for welding hot work tool steels and cast steels with similar composition, which are subjected to high temperatures up to 550-600°C. Suitable for welding Cr, Mo, V, W containing low alloy steels and hot work tool steels. Also suitable for surfacing and hardfacing on machine parts, forging and drawing dies, shafts which were made of hot work tool steels and similiar compositions. Preheating, interpass temperature and post-weld heat treatment should be done in accordance with base metal to be welded.</p>	<p>If required 2 Hour</p>

Typical Chemical Analysis of All-Weld Metal (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Dimension (mm)	Packing Weigth (kg) Box Type
C: 0.07						
Si: 0.30	After Heat Treatment (690°C 1 Hour)					
Mn: 0.75	550	650	19	20°C: 50	3.25 x 350 4.00 x 450	2.50 kg - Cardboard / Vacuum 5.00 -6.50 kg - Cardboard
Cr: 2.30						
Mo: 1.00						
C: 0.07						
Si: 0.20	After Heat Treatment (740°C 1 Hour)					
Mn: 0.60	510	610	21	20°C: 120	2.50 x 350 3.25 x 350 4.00 x 450 5.00 x 450	2.50 kg - Cardboard / Vacuum 5.00 -6.50 kg - Cardboard
Cr: 5.30						
Mo: 0.50						
C: 0.04						
Si: 0.50						
Mn: 0.60	790	870	18	20°C: 60	2.50 x 350 3.25 x 350 4.00 x 450 5.00 x 450	2.50 kg - Cardboard / Vacuum 5.00 -6.50 kg - Cardboard
Cr: 1.10						
Ni: 2.40						
Mo: 0.75						
C: 0.09						
Si: 0.75						
Mn: 0.60						
Cr: 1.30	700	850	15	-	2.50 x 350 3.25 x 350 4.00 x 450 5.00 x 450	2.50 kg - Cardboard / Vacuum 5.00 -6.50 kg - Cardboard
Ni: 0.04						
Mo: 0.90						
V: 0.50						
Cu: 0.10						
C: 0.10						
Si: 0.90						
Mn: 1.05	Hardness 44 HRc					
Cr: 3.50	800	920	18	20°C: 45	2.00 x 300 2.50 x 350 3.25 x 350 4.00 x 450 5.00 x 450	2.50 kg - Cardboard / Vacuum 5.00 -6.50 kg - Cardboard
Mo: 0.70						
V: 0.55						
W: 0.60						

STICK ELECTRODES

Low Alloyed, High Strength and Creep Resistance Steel Electrodes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>EM 255</p> <p>EN ISO 3580 - A E CrMoV1 B 42 H10 TS EN ISO 3580 - A E CrMoV1 B 42 H10</p>	<p>Basic type, electrode for Cr-Mo-V type, designed for welding cast steels of identical composition, subjected to operating temperatures of up to 600°C. Suitable for joining and repair purposes on steam turbine parts, valves and seats, pumps, shafts and rolls. Observe specifications as to preheating and post-weld heat treatment to base metal.</p>	<p>If required 2 Hour</p>
<p>EM 285</p> <p>AWS/ASME SFA - 5.5 E8015-B8 H4R EN ISO 3580 - A E (CrMo9) B 42 H5 TS EN ISO 3580 - A E (CrMo9) B 42 H5</p>	<p>Basic type, covered electrode for welding high temperature creep resistant steels type 9Cr-1Mo steels with operating temperatures of up to 625°C. Suitable for welding of boilers and pipe fabrication.</p>	<p>If required 2 Hour</p>
<p>EM 295</p> <p>AWS/ASME SFA - 5.5 E9015-B91 H4R EN ISO 3580-A E (CrMo91) B 42 H5 TS EN ISO 3580-A E (CrMo91) B 42 H5</p>	<p>Basic type, covered electrode for welding high temperature creep resistant steels of type 9Cr-1Mo-V-Nb-N with operating temperatures of up to 650°C. Suitable for welding piping and components produced from P91, F91 and T91 steels. Can be used both in thin walled and thick walled pipes and casting successfully, especially in power plants, chemical and petrochemical industry. Welds are X-ray quality.</p>	<p>If required 2 Hour</p>
<p>EM 298</p> <p>AWS/ASME SFA - 5.5 E9018-B91 H4 EN ISO 3580-A E (CrMo91) B 42 H5 TS EN ISO 3580-A E (CrMo91) B 42 H5</p>	<p>Basic type electrode for welding high temperature creep, oxidation and fatigue resistant steels, 9Cr-1Mo-V-Nb-N steels with operating temperatures of up to 650°C. Suitable for welding in piping and equipment production from P91, F91 and T91 with thin and thick walled and casting successfully, especially in power plants, chemical and petrochemical industry. Welds are X-ray quality.</p>	<p>If required 2 Hour</p>

Typical Chemical Analysis of All-Weld Metal (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Dimension (mm)	Packing Weigth (kg) Box Type
C: 0.10						
Si: 0.55	After Heat Treatment (700°C 1 Hour)					
Mn: 0.90	550	630	18	20°C: 50	2.50 x 350 3.25 x 350 4.00 x 450 5.00 x 450	2.50 kg - Cardboard / Vacuum 5.00 - 6.50 kg - Cardboard
Cr: 1.20						
Mo: 1.00						
V: 0.20						
C: 0.07						
Si: 0.30	After Heat Treatment (740°C 1 Hour)					
Mn: 0.75	560	700	20	20°C: 65	2.50 x 350 3.25 x 350 4.00 x 450	2.50 kg - Cardboard / Vacuum 5.00 - 6.50 kg - Cardboard
Cr: 9.20						
Ni: 0.10						
Mo: 1.00						
C: 0.10						
Si: 0.20						
Mn: 0.75	After Heat Treatment (760°C 2 Hour)					
P: 0.01						
S: 0.01	620	730	20	20°C: 70	2.50 x 350 3.25 x 350 4.00 x 450 5.00 x 450	2.50 kg - Cardboard / Vacuum 5.00 - 6.50 kg - Cardboard
Cr: 9.25						
Ni: 0.55						
Mo: 1.00						
V: 0.20						
Nb: 0.04						
N: 0.04						
C: 0.10						
Si: 0.20						
Mn: 0.80	After Heat Treatment (760°C 2 Hour)					
P: 0.01						
S: 0.01	650	770	17	20°C: 50	2.50 x 350 3.25 x 350 4.00 x 450 5.00 x 450	2.50 kg - Cardboard / Vacuum 5.00 - 6.50 kg - Cardboard
Cr: 9.50						
Ni: 0.55						
Mo: 0.90						
V: 0.20						
Nb: 0.05						
N: 0.03						

STICK ELECTRODES

Stainless Steel Electrodes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>EI 307R</p> <p>AWS/ASME SFA - 5.4 ~E307-16 EN ISO 3581 - A E 18 8 Mn R 12 TS EN ISO 3581 - A E 18 8 Mn R 12 DIN M. No. 1.4370</p>	<p>Rutile coated electrode for joining dissimilar steels, depositing buffer layer before hardfacing and claddings on ferritic steels. The weld metal consists of austenitic Cr-Ni-Mn steel with possible small amounts of delta ferrite. The weld metal is highly crack resistant and therefore suited for joining difficult to weld steels and depositing stress relaxing buffer layers on crack sensitive base metal prior to hardfacing deposits. Weld metal work hardens by impact and pressure. Suitable for armour plates, high-manganese steels, rails, cross-overs, crane wheels, idlers, which are subjected to dynamically loading, pressure, impact and abrasion. It is non-scaling up to 850°C and highest operating temperature for dissimilar steel joints is 300°C. In the case of higher temperatures, use ENI 422 electrodes. Easy to use in positional welding and possible to use equally well both with AC and DC.</p>	   If required 2 Hour
<p>EI 307B</p> <p>AWS/ASME SFA - 5.4 ~E307-15 EN ISO 3581 - A E 18 8 Mn B 22 TS EN ISO 3581 - A E 18 8 Mn B 22 DIN M. No. 1.4370</p>	<p>Basic coated electrode for joining dissimilar steels and depositing buffer layer before hardfacing and claddings on ferritic steels. The weld metal consists of austenitic Cr-Ni-Mn steel with possible small amounts of delta ferrite. The weld metal is highly crack resistant and therefore suited to joining difficult to weld steels and depositing stress relaxing buffer layers on crack sensitive base metal prior hardfacing deposits. Weld metal work hardens by impact and pressure. Suitable for armour plates, rail, cross-over, crane wheels, idlers, which are subjected to dynamically loading, pressure, impact and abrasion. It is non-scaling up to 850°C and highest operating temperature for dissimilar steel joints is 300°C. In the case of higher temperatures, use ENI 422 electrodes. Used with DCEP (DC+).</p>	   If required 2 Hour
<p>EIS 307</p> <p>AWS/ASME SFA - 5.4 ~E307-26 EN ISO 3581 - A E 18 8 Mn R 53 TS EN ISO 3581 - A E 18 8 Mn R 53 DIN M. No. 1.4370</p>	<p>High efficiency (160 %) electrode for joining dissimilar steels and depositing buffer layer before hardfacing and claddings on ferritic steels. The weld metal consists of austenitic Cr-Ni-Mn steel with possible small amounts of delta ferrite. The weld metal is highly crack resistant and therefore suited for joining difficult to weld steels and depositing stress relaxing buffer layers on crack sensitive base metal prior to hardfacing deposits. Weld metal work hardens by impact and pressure. Suitable for armour plates, rail, cross-overs, crane wheels, idlers, which are subjected to dynamically loading, pressure, impact and abrasion. It is non-scaling up to 850°C and highest operating temperature for dissimilar steel joints is 300°C. In the case of higher temperatures, use ENI 422 electrodes. High current carrying capacity due to its low alloy steel core wire and possible to use equally well both with AC and DC.</p>	   If required 2 Hour
<p>EI 308L</p> <p>AWS/ASME SFA - 5.4 E308L-16 EN ISO 3581 - A E 19 9 L R 12 TS EN ISO 3581 - A E 19 9 L R 12 DIN M. No. 1.4316</p>	<p>Rutile coated electrode for welding austenitic stainless Cr-Ni steels or cast steels, having an extra low carbon content, as well as stainless or heat resisting chromium steels or cast steels. Suitable for welding stainless steel tanks, valves, pipes and linings in chemical, food, beverage, pharmaceutical industries. For operating temperatures of up to 350°C, non-scaling up to 800°C. Possible to use equally well both with AC and DC. Easy arc striking and re-striking. Fine metal droplet transfer, good fusion of joint faces, finely rippled bead surface, easily removable slag.</p>	   If required 2 Hour
<p>EI 308LB</p> <p>AWS/ASME SFA - 5.4 E308L-15 EN ISO 3581-A E 19 9 L B 22 TS EN ISO 3581-A E 19 9 L B 22 DIN M. No. 1.4316</p>	<p>Basic coated electrode for welding austenitic stainless Cr-Ni steels or cast steels, having an extra low carbon content, as well as stainless or heat resisting chromium steels or cast steels. Suitable for welding stainless steel tanks, valves, pipes and linings in chemical, petrochemical, energy, food, beverage, pharmaceutical industries. For operating temperatures of up to 350°C, non-scaling up to 800°C. Possible to use with DC. Fine metal droplet transfer, good fusion of joint faces, finely rippled bead surface, provides high strength weld metal.</p>	   If required 2 Hour

Typical Chemical Analysis of All-Weld Metal (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Dimension (mm)	Packing Weigth (kg) Box Type
C: 0.10	500	650	37	20°C: 80	2.50 x 300 3.25 x 300 3.25 x 350 4.00 x 350 5.00 x 350	1.75 - 2.50 kg - Vacuum 2.50 kg - Plastic
Si: 0.45						
Mn: 6.00						
Cr: 19.50						
Ni: 9.00						
C: 0.08	500	660	38	20°C: 70	2.50 x 250 2.50 x 300 3.25 x 300 3.25 x 350 4.00 x 350 5.00 x 350	1.75 - 2.50 kg - Vacuum 2.50 kg - Plastic
Si: 0.30						
Mn: 6.00						
Cr: 19.50						
Ni: 9.50						
C: 0.07	440	610	40	20°C: 70	2.50 x 350 3.25 x 350 4.00 x 350 5.00 x 350	2.00 kg - Vacuum 2.50 kg - Plastic
Si: 1.00						
Mn: 6.50						
Cr: 19.50						
Ni: 9.50						
C: 0.02	440	570	42	20°C: 70	2.00 x 250 2.00 x 300 2.50 x 250 2.50 x 300 2.50 x 350 3.25 x 300 3.25 x 350 4.00 x 350 5.00 x 350	1.00 kg - Plastic 1.25 - 2.25 kg - Vacuum 2.50 kg - Plastic 5.00 kg - Plastic
Si: 0.70						
Mn: 0.90						
Cr: 19.50						
Ni: 10.00						
C: 0.03	440	580	45	20°C: 70	2.50 x 300 3.25 x 300 3.25 x 350 4.00 x 350	1.00 - 2.00 kg - Vacuum
Si: 0.40						
Mn: 0.80						
Cr: 19.00						
Ni: 10.00						

STICK ELECTRODES

Stainless Steel Electrodes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>EI 308LRS</p> <p>AWS/ASME SFA - 5.4 E308L-17 EN ISO 3581 - A E 19 9 L R 12 TS EN ISO 3581 - A E 19 9 L R 12 DIN M. No. 1.4316</p>	<p>Rutile type electrode for welding austenitic stainless Cr-Ni steels or cast steels, having an extra low carbon content, as well as stainless or heat resisting chromium steels or cast steels. Suitable for welding stainless steel tanks, valves, pipes and linings in chemical, food, beverage, pharmaceutical industries. For operating temperatures of up to 350°C, non-scaling up to 800°C. Possible to use equally well both with AC and DC. Easy arc striking and re-striking. Fine metal droplet transfer, good fusion of joint faces, very finely rippled, flat and smooth bead surface especially in fillet welds, easily removable slag.</p>	<p>If required 2 Hour</p>
<p>EI 308Mo</p> <p>AWS/ASME SFA - 5.4 E308Mo-15 EN ISO 3581 - A E 20 10 3 B 22 TS EN ISO 3581 - A E 20 10 3 B 22 DIN M. No. 1.4343</p>	<p>Basic electrode, particularly designed for welding armour plates, dissimilar steels and for surfacing purposes. The weld metal consists of austenitic Cr-Ni-Mn-Mo stainless steel. It features high resistance to cracking caused by impact and high temperature and is therefore indicated for difficult to weld steels and depositing stress relaxing buffer layers on crack sensitive base metal or beneath hardfacing deposits. Use with DCEP. No pre-heat or post welding heat treatment is needed when welding armour plates. Interpass temperature should not exceed 120°C. Shall be used with shortest possible stick-out distance, at 90° angle to the work piece.</p>	<p>If required 2 Hour</p>
<p>EI 308H</p> <p>AWS/ASME SFA - 5.4 E308H-16 EN ISO 3581 - A E 19 9 H R 12 TS EN ISO 3581 - A E 19 9 H R 12 DIN M. No. 1.4302</p>	<p>Rutile type austenitic stainless steel electrode for welding especially 304H and similar austenitic stainless steels or cast steels and heat resistant steels, having high carbon content. Suitable for welding stainless steel tanks, valves, pipes and linings in chemical, food, beverage, pharmaceutical, fertilizer industries. Weld metal is suitable for use at high operating temperatures and it is also non-scaling. Possible to use equally well both with AC and DC. Easy arc striking and re-striking. Fine metal droplet transfer, good fusion of joint faces, finely rippled bead surface, easily removable slag.</p>	<p>If required 2 Hour</p>
<p>EIS 308</p> <p>AWS/ASME SFA - 5.4 E308-26 EN ISO 3581 - A E 19 9 R 53 TS EN ISO 3581 - A E 19 9 R 53 DIN M. No. ~1.4301</p>	<p>Rutile type stainless steel electrode with high recovery (160%) for welding 18Cr/8Ni austenitic stainless steels to mild steels and low alloyed steels and also for surfacing applications on such steels. Weld metal deposit is austenitic-ferritic stainless steels. Possible to use equally well both with AC and DC. High current carrying capacity, since core wire is not made of stainless steel.</p>	<p>If required 2 Hour</p>
<p>EI 309L</p> <p>AWS/ASME SFA - 5.4 E309L-16 EN ISO 3581-A E 23 12 L R 12 TS EN ISO 3581-A E 23 12 L R 12 DIN M. No. 1.4332</p>	<p>Electrode for joining dissimilar steels (austenitic steels to ferritic steels) and for austenitic claddings on ferritic steels. Weld metal consists of austenite with approx. 15% delta-ferrite. Claddings on unalloyed and low alloy steels are already corrosion resistant in the first layer. Highest operating temperature for joints between dissimilar steels is 300°C. In case of higher temperatures use ENI 422 electrodes. Fine metal droplet transfer, good fusion of joint faces, finely rippled bead surface, easy slag removal, easy arc striking and restriking.</p>	<p>If required 2 Hour</p>

Typical Chemical Analysis of All-Weld Metal (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Dimension (mm)	Packing Weigth (kg) Box Type
C: 0.02	440	570	42	20°C: 70	2.50 x 300 3.25 x 300 3.25 x 350 4.00 x 350	1.75 - 2.00 kg- Vacuum
Si: 0.70						
Mn: 0.90						
Cr: 19.50						
Ni: 10.00						
C: 0.08	440	690	40	20°C: 70	2.50 x 250 2.50 x 300 3.25 x 300 4.00 x 350 5.00 x 350	1.75 - 2.50 kg- Vacuum
Si: 0.55						
Mn: 1.80						
Cr: 20.00						
Ni: 11.50						
Mo: 2.50						
C: 0.06	440	600	45	20°C: 60	2.50 x 300 3.25 x 300 3.25 x 350 4.00 x 350	1.75 - 2.00 kg- Vacuum
Si: 0.70						
Mn: 1.00						
Cr: 20.00						
Ni: 10.50						
C: 0.04	460	600	37	20°C: 65	2.50 x 350 3.25 x 350 4.00 x 350	1.75 - 2.00 kg- Vacuum
Si: 0.80						
Mn: 0.80						
Cr: 19.00						
Ni: 10.50						
C: 0.03	450	570	40	20°C: 60	2.50 x 250 2.50 x 300 3.25 x 300 3.25 x 350 4.00 x 350 5.00 x 350	1.75 - 2.00 kg- Vacuum 2.50 kg - Plastic 5.00 kg - Plastic
Si: 0.90						
Mn: 1.10						
Cr: 23.00						
Ni: 12.50						

STICK ELECTRODES


Stainless Steel Electrodes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>EI 309LB</p> <p>AWS/ASME SFA - 5.4 E309L-15 EN ISO 3581-A E 23 12 L B 22 EN ISO 3581 - A E 23 12 L B 22 DIN M. No. 1.4332</p>	<p>Basic type electrode for joining dissimilar steels (austenitic steels to ferritic steels) and for austenitic claddings on ferritic steels. Weld metal consists of austenite with approx. 15% delta-ferrite. Claddings on unalloyed and low alloy steels are already corrosion resistant in the first layer. Higher operating temperature for joints between dissimilar steels is 300°C. Fine metal droplet transfer, good fusion of joint faces, finely ripped bead surface, easy slag removal.</p>	<p></p> <p></p> <p> If required 2 Hour</p>
<p>EI 309LRS</p> <p>AWS/ASME SFA - 5.4 E309L-17 EN ISO 3581 - A E 23 12 L R 12 TS EN ISO 3581 - A E 23 12 L R 12 DIN M. No. 1.4332</p>	<p>Rutile type electrode for joining dissimilar steels (austenitic steels to ferritic steels) and for austenitic claddings on ferritic steels. Weld metal consists of austenite with approx. 15% delta-ferrite. Claddings on unalloyed and low alloy steels are already corrosion resistant in the first layer. Higher operating temperature for joints between dissimilar steels is 300°C. Fine metal droplet transfer, good fusion of joint faces, finely ripped flat and smooth bead surface, especially in fillet welds. Easy slag removal of slag.</p>	<p></p> <p></p> <p> If required 2 Hour</p>
<p>EI 309MoL</p> <p>AWS/ASME SFA - 5.4 E309LMo-16 EN ISO 3581 - A E 23 12 2 L R 12 TS EN ISO 3581 - A E 23 12 2 L R 12 DIN M. No. 1.4459</p>	<p>Rutile type stainless electrode for joining dissimilar steels (austenitic steels to ferritic steels) and for austenitic claddings. Weld metal consists of austenite with approx. 15% delta-ferrite. Claddings on unalloyed and low-alloy steels are already corrosion resistant in the first layer, due to Mo (molibdenum) content. Higher operating temperature for joints between dissimilar steels is 300°C. In the cases of higher temperatures, use ENI 422 electrodes. Fine metal droplet transfer, good fusion of joint faces, finely ripped bead surface, easy slag removal, easy arc striking and restriking.</p>	<p></p> <p></p> <p> If required 2 Hour</p>
<p>EIS 309</p> <p>AWS/ASME SFA - 5.4 E309-26 EN ISO 3581 - A E (22 12) R 53 TS EN ISO 3581 - A E (22 12) R 53 DIN M. No. ~1.4833</p>	<p>Rutile type, high recovery (160%) stainless steel electrode for welding of heat resistant 22Cr/12-Ni austenitic stainless steels to mild steels and low alloyed steels and also for surfacing applications on such steels. Weld metal deposit is austenitic-ferritic stainless steels. Possible to use equally well both with AC and DC. High current carrying capacity, since core wire is not made of stainless steel.</p>	<p></p> <p></p> <p> If required 2 Hour</p>
<p>EIS 309Mo</p> <p>AWS/ASME SFA - 5.4 E309Mo-26 EN ISO 3581-A E Z 23 12 2 L R 53 TS EN ISO 3581-A E Z 23 12 2 L R 53 DIN M. No. 1.4332</p>	<p>Rutile type, high recovery (160%) stainless steel electrode for welding dissimilar steels ferritic to austenitic steels and depositing austenitic stainless claddings. The austenitic weld metal has a delta-ferrite content of approx. 15 %. Claddings on unalloyed steels are already corrosion resistant in the first layer, due to Mo (molibdenum) content. Highest operating temperature for dissimilar steel joints is 300°C. Possible to use equally well both with AC and DC. Easy arc striking and re-striking. Fine metal droplet transfer, good fusion of joint faces, finely ripped bead surface, easy slag removal. High current carrying capacity, since core wire is not made of stainless steel.</p>	<p></p> <p></p> <p> If required 2 Hour</p>

Typical Chemical Analysis of All-Weld Metal (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Dimension (mm)	Packing Weigth (kg) Box Type
C: 0.02	430	530	35	20°C: 60	2.50 x 300 3.25 x 300	1.75 kg - Vacuum
Si: 0.30						
Mn: 1.30						
Cr: 23.00						
Ni: 13.00						
C: 0.03	450	570	40	20°C: 60	2.50 x 300 3.25 x 350 4.00 x 350	1.75 - 2.00 kg - Vacuum
Si: 0.90						
Mn: 1.10						
Cr: 23.00						
Ni: 12.50						
C: 0.02	600	720	30	20°C: 50	2.00 x 300 2.50 x 300 3.25 x 300 3.25 x 350 4.00 x 350	1.75 - 2.00 kg - Vacuum
Si: 0.90						
Mn: 0.95						
Cr: 23.50						
Ni: 12.50						
Mo: 2.50						
C: 0.07	440	580	36	20°C: 70	2.00 x 300 2.50 x 350 3.25 x 350 4.00 x 350 5.00 x 350	1.75 - 2.00 kg - Vacuum
Si: 0.85						
Mn: 0.75						
Cr: 23.50						
Ni: 13.00						
C: 0.07	440	580	33	20°C: 50	2.00 x 300 2.50 x 350 3.25 x 350 4.00 x 350 5.00 x 350	1.75 - 2.00 kg - Vacuum
Si: 0.80						
Mn: 1.60						
Cr: 22.50						
Ni: 12.50						
Mo: 2.40						

STICK ELECTRODES

Stainless Steel Electrodes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>EI 310</p> <p>AWS/ASME SFA - 5.4 E310-16 EN ISO 3581 - A E 25 20 R 32 TS EN ISO 3581 - A E 25 20 R 32 DIN M. No. 1.4842</p>	<p>Rutile type stainless steel electrode for welding heat resisting chromium and chromium-nickel steels as well as cast steels. Weld metal deposit is fully austenitic stainless steel, containing 25% chromium and 20% nickel. Suitable for welding heat treatment and industrial furnaces and equipments which are subjected to service temperatures up to 1200°C. Weld metal is non-scaling up to 1250°C. Especially it is resistant to hot crack. Exhibits high charpy impact energy at low temperatures. Weld metal is not corrosion resistant to sulphurous combustion gases. Possible to use equally well both with AC and DC.</p>	 <p>If required 2 Hour</p>
<p>EI 310B</p> <p>AWS/ASME SFA - 5.4 E310-15 EN ISO 3581 - A E 25 20 B 12 TS EN ISO 3581 - A E 25 20 B 12 DIN M. No. 1.4842</p>	<p>Basic coated stainless steel electrode for welding heat resisting chromium and chromium-nickel steels as well as cast steels. Weld metal deposit is fully austenitic stainless steel, containing 25% chromium and 20% nickel. Suitable for welding heat treatment and industrial furnaces and equipments which are service temperatures up to 1200°C. Weld metal is non-scaling up to 1250°C. Especially high charpy impact energy at low temperatures. Weld metal is not corrosion resistant to sulphurous combustion gases. Used with DCEP.</p>	 <p>If required 2 Hour</p>
<p>EI 312</p> <p>AWS/ASME SFA - 5.4 E312-16 EN ISO 3581 - A E 29 9 R 12 TS EN ISO 3581 - A E 29 9 R 12 DIN M. No. 1.4337</p>	<p>Rutile type stainless steel electrode for joining dissimilar steels and depositing claddings on ferritic steels. The ferritic-austenitic Cr-Ni weld metal contains approximately 50% of delta-ferrite and is non-scaling up to 1100°C. It features high resistance to cracking and is therefore suited for joining difficult to weld steels and depositing stress-relaxing buffer layers on crack sensitive base metals. Especially used in crack repair and build-up of tool and die steels, rebuilding of worn or cracked gear teeth, buffer layer on cutting blades. Suitable for welding galvanized steel plates. Possible to use equally well both AC and DC. Easy arc striking and re-striking. Fine metal droplet transfer, good fusion of joints faces, finely rippled bead surface, easy slag removal.</p>	 <p>If required 2 Hour</p>
<p>EI 312RS</p> <p>AWS/ASME SFA - 5.4 E312-17 EN ISO 3581 - A E 29 9 R 12 TS EN ISO 3581 - A E 29 9 R 12 DIN M. No. 1.4337</p>	<p>Rutile type stainless steel electrode for joining dissimilar steels and depositing claddings on ferritic steels. The ferritic-austenitic Cr-Ni weld metal contains approximately 50% of delta-ferrite and is non-scaling up to 1100°C. It features high resistance to cracking and is therefore suited for joining difficult to weld steels and depositing stress-relaxing buffer layers on crack sensitive base metals. Especially used in crack repair and build-up of tool and die steels, rebuilding of worn or cracked gear teeth, buffer layer on cutting blades. Suitable for welding galvanized steel plates. Possible to use equally well both AC and DC. Easy arc striking and re-striking. Fine metal droplet transfer, good fusion of joints faces, finely rippled flat and smooth bead surface, especially in fillet welds. Easy slag removal of slag.</p>	 <p>If required 2 Hour</p>
<p>EI 316L</p> <p>AWS/ASME SFA - 5.4 E316L-16 EN ISO 3581-A E 19 12 3 L R 32 TS EN ISO 3581-A E 19 12 3 L R 32 DIN M. No. 1.4430</p>	<p>Rutile type stainless steel electrode for welding austenitic stainless Cr-Ni-Mo steels or cast steels, having an extra low carbon content. For operating temperatures of up to 400°C. Especially suitable for welding of stainless steel chemical tanks and pipes in chemical, textile, paint, paper industries. Possible to use equally well both with AC and DC. Easy arc striking and re-striking. Fine metal droplet transfer, good fusion of joint faces, finely rippled bead surface, easily removable slag.</p>	 <p>If required 2 Hour</p>

Typical Chemical Analysis of All-Weld Metal (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Dimension (mm)	Packing Weigth (kg) Box Type
C: 0.10	440	600	30	20°C: 70	2.00 x 300 2.50 x 300 3.25 x 300 4.00 x 350 5.00 x 350	1.00 kg - Plastic 1.75 - 2.50 kg - Vacuum 2.50 kg - Plastic
Si: 0.60						
Mn: 1.65						
Cr: 25.50						
Ni: 21.00						
C: 0.10	440	600	33	20°C: 60	2.50 x 300 3.25 x 300 4.00 x 350 5.00 x 350	1.75 - 2.00 kg - Vacuum
Si: 0.65						
Mn: 1.40						
Cr: 26.00						
Ni: 21.00						
C: 0.10	660	760	20	20°C: 50	2.00 x 300 2.50 x 300 3.25 x 300 3.25 x 350 4.00 x 350 5.00 x 350	1.00 kg - Plastic 1.75 - 2.00 kg - Vacuum 2.50 kg - Plastic
Si: 0.60						
Mn: 1.00						
Cr: 29.50						
Ni: 9.00						
C: 0.10	660	760	20	20°C: 50	3.25 x 300 4.00 x 350 5.00 x 350	1.75 - 2.00 kg - Vacuum 2.50 kg - Plastic
Si: 0.60						
Mn: 1.00						
Cr: 29.50						
Ni: 9.00						
C: 0.03	460	560	40	20°C: 70	2.00 x 250 2.00 x 300 2.50 x 250 2.50 x 300 2.50 x 350 3.25 x 300 3.25 x 350 4.00 x 350 5.00 x 350	1.00 kg - Plastic 1.75 - 2.25 kg - Vacuum 2.50 kg - Plastic 5.00 kg - Plastic
Si: 0.80						
Mn: 0.90						
Cr: 19.00						
Ni: 12.00						
Mo: 2.80						

STICK ELECTRODES

Stainless Steel Electrodes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>EI 316LB</p> <p>AWS/ASME SFA - 5.4 E316L-15 EN ISO 3581 - A E 19 12 3 L B 42 TS EN ISO 3581 - A E 19 12 3 L B 42 DIN M. No. 1.4430</p>	<p>Basic type stainless steel electrode for welding austenitic stainless Cr-Ni-Mo steels and cast steels, having a low carbon content. For operating temperatures up to 400°C. Especially suitable for welding of stainless steel chemical tanks and pipes made of low carbon austenitic 19Cr/12-Ni/2-3Mo stainless steels in chemical, textile, paint, paper industries. Used with DCEP.</p>	<p></p> <p></p> <p> If required 2 Hour</p>
<p>EI 316LRS</p> <p>AWS/ASME SFA - 5.4 E316L-17 EN ISO 3581 - A E 19 12 3 L R 32 TS EN ISO 3581 - A E 19 12 3 L R 32 DIN M. No. 1.4430</p>	<p>Rutile type stainless steel electrode for welding austenitic stainless Cr-Ni-Mo steels or cast steels, having an extra low carbon content. For operating temperatures of up to 400°C. Especially suitable for welding of stainless steel chemical tanks and pipes in chemical, textile, paint, paper industries. Possible to use equally well both with AC and DC. Easy arc striking and re-striking. Fine metal droplet transfer, good fusion of joint faces, finely rippled flat and smooth bead surface, especially in fillet welds. Easy slag removal of slag.</p>	<p></p> <p></p> <p> If required 2 Hour</p>
<p>EIS 316</p> <p>AWS/ASME SFA - 5.4 E316-26 EN ISO 3581 - A E 19 12 2 R 53 TS EN ISO 3581 - A E 19 12 2 R 53 DIN M. No. ~1.4443</p>	<p>Rutile type, high recovery (160%) stainless steel electrode for welding 19Cr/12Ni/2-3Mo austenitic stainless steels to mild steels and low alloyed steels and also for surfacing applications on such steels. Weld metal deposit is austenitic-ferritic stainless steels. Possible to use equally well both with AC and DC. High current carrying capacity, since core wire is not made of stainless steel.</p>	<p></p> <p></p> <p> If required 2 Hour</p>
<p>EI 318</p> <p>AWS/ASME SFA - 5.4 E318-16 EN ISO 3581 - A E 19 12 3 Nb R 32 TS EN ISO 3581 - A E 19 12 3 Nb R 32 DIN M. No. 1.4576</p>	<p>Rutile type stainless steel electrode for welding stabilized Cr-Ni-Mo austenitic stainless and cast steels. Suitable for using operating temperatures up to 400°C. Especially used for welding of stainless steels acid, salt and alkaline tanks, valves and pipes in chemical, textile, paint and paper industries. Possible to use equally well both with AC and DC. Easy arc striking and re-striking. Fine-droplet metal transfer, good wash-in of joint sides, easily removable slag.</p>	<p></p> <p></p> <p> If required 2 Hour</p>
<p>EI 347</p> <p>AWS/ASME SFA - 5.4 E347-16 EN ISO 3581-A E 19 9 Nb R 32 TS EN ISO 3581-A E 19 9 Nb R 32 DIN M. No. 1.4551</p>	<p>Rutile type stainless steel electrode for welding stabilized austenitic stainless Cr-Ni steels, and cast steels, as well as stainless or heat resisting chromium steels to cast steels. Stabilized with Nb (Niobium) and resistant to intergranular corrosion. Weld metal is suitable for operating temperatures up to 400°C, non-scaling up to 800°C. Especially suitable for welding of stainless steel tanks, valves and pipes in milk, beverage, food, chemical and petrochemical industries. Possible to use equally well both with AC and DC. Easy arc striking and re-striking. Fine metal droplet transfer, good fusion of joint faces, finely rippled bead surface, easily removable slag.</p>	<p></p> <p></p> <p> If required 2 Hour</p>

Typical Chemical Analysis of All-Weld Metal (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Dimension (mm)	Packing Weigth (kg) Box Type
C: 0.02	480	590	38	20°C: 70	2.50 x 300 3.25 x 350 4.00 x 350	1.75 - 2.00 kg - Vacuum
Si: 0.50						
Mn: 0.80						
Cr: 18.00						
Ni: 13.00						
Mo: 2.80						
C: 0.03	460	560	40	20°C: 70	3.25 x 300 3.25 x 350 4.00 x 350	1.75 - 2.00 kg - Vacuum 2.50 kg - Plastic
Si: 0.80						
Mn: 0.90						
Cr: 19.00						
Ni: 12.00						
Mo: 2.80						
C: 0.07	470	600	35	20°C: 50	2.00 x 300 2.50 x 350 3.25 x 350 4.00 x 350 5.00 x 350	1.75 - 2.00 kg - Vacuum
Si: 0.85						
Mn: 0.60						
Cr: 18.00						
Ni: 12.50						
Mo: 2.70						
C: 0.02	500	600	35	20°C: 70	2.00 x 300 2.50 x 300 2.50 x 350 3.25 x 300 3.25 x 350 4.00 x 350 5.00 x 350	1.75 - 2.25 kg - Vacuum
Si: 0.80						
Mn: 0.90						
Cr: 19.00						
Ni: 12.00						
Mo: 2.90						
Nb: 0.25						
C: 0.02	480	600	42	20°C: 70	2.00 x 250 2.00 x 300 2.50 x 250 2.50 x 300 3.25 x 300 3.25 x 350 4.00 x 350 5.00 x 350	1.00 kg - Plastic 1.75 - 2.50 kg - Vacuum 2.50 kg - Plastic
Si: 0.70						
Mn: 0.90						
Cr: 19.70						
Ni: 10.30						
Nb: 0.30						

STICK ELECTRODES

Stainless Steel Electrodes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>EI 347B</p> <p>AWS/ASME SFA - 5.4 E347-15 EN ISO 3581 - A E 19 9 Nb B 12 TS EN ISO 3581 - A E 19 9 Nb B 12 DIN M. No. 1.4551</p>	<p>Basic type stainless steel electrode for welding stabilized austenitic stainless Cr-Ni steels, and cast steels, as well as stainless or heat resisting chromium steels to cast steels. Stabilized with Nb (Niobium) and resistant to intergranular corrosion. Weld metal is suitable for operating temperatures up to 400°C, non-scaling up to 800°C. Especially suitable for welding of stainless steel tanks, valves and pipes in milk, beverage, food, chemical and petrochemical industries. Fine metal droplet transfer, good fusion of joint faces, finely rippled bead surface, easily removable slag.</p>	<p></p> <p></p> <p></p> <p>If required 2 Hour</p>
<p>EI 385</p> <p>AWS/ASME SFA - 5.4 E385-16 EN ISO 3581 - A E 20 25 5 Cu N L R 12 TS EN ISO 3581 - A E 20 25 5 Cu N L R 12 DIN M. No. 1.4539</p>	<p>Rutile type fully-austenitic stainless steel electrode for welding of unstabilized or stabilized corrosion resisting Cr-Ni-Mo alloyed stainless steels like 904L/1.4539. Especially used in flue gas desulphurization plants, fertilizer plants, sea water transfer fittings, in petrochemical, paper and pulp industries, etc. Due to high Ni, Mo and low C content, weld metal have high resistant to intergranular, pitting, crevice and stress corrosion types in chloride containing solutions, phosphorus-, sulphur-, formic acids and sea water. Possible to use equally well both AC and DC. Easy arc striking and re-striking. Fine metal droplet transfer, good fusion of joints faces, finely rippled flat and smooth bead surface, especially in fillet welds. Easy slag removal of slag.</p>	<p></p> <p></p> <p></p> <p>If required 2 Hour</p>
<p>EIS 410</p> <p>AWS/ASME SFA - 5.4 E410-15 EN ISO 3581 - A E (13) B 42 TS EN ISO 3581 - A E (13) B 42 DIN M. No. ~1.4009</p>	<p>Basic type stainless steel electrode with high recovery, which is used for welding of approx. 13% Cr containing stainless and heat resistant chromium steels or cast steels. Deposits martensitic stainless steel weld metal. Also suitable for corrosion and abrasion resistant surfacing of contact surfaces of gas, water and steam fan, fan blades and fittings subjected to operating temperatures up to 450°C. Weld metal is non-scaling up to 850°C. Use with DCEP. Depending on type of base metal and wall thickness, preheating and interpass temperatures from 100 to 400°C and tempering at 650 to 750°C are advisable.</p>	<p></p> <p></p> <p></p> <p>If required 2 Hour</p>
<p>EIS 410NiMo</p> <p>AWS/ASME SFA - 5.4 E410NiMo-15 EN ISO 3581 - A E 13 4 B 42 TS EN ISO 3581 - A E 13 4 B 42 DIN M. No. 1.4317</p>	<p>Basic type stainless steel electrode with high recovery, which is used for welding of 12-14% Cr and 3-4% Ni containing stainless and heat resistant chromium steels or cast steels. Deposits martensitic stainless steel weld metal. Also suitable for corrosion and abrasion resistant surfacing of contact surfaces of gas, water, sea water and steam fan, fan blades and fittings in hydro-electric plants and continuous casting rolls. Used with DCEP. For wall thickness over 10 mm preheating to max. 150°C and after welding tempering or normalizing + tempering are recommended. Especially in joint welding a buffer layer with EI 312 or EIS 307 electrode is advisable.</p>	<p></p> <p></p> <p></p> <p>If required 2 Hour</p>
<p>EIS 430</p> <p>AWS/ASME SFA - 5.4 E430-15 EN ISO 3581-A E 17 B 62 TS EN ISO 3581-A E 17 B 62 DIN M. No. ~1.4104</p>	<p>Basic type electrode which provides 17% Cr containing ferritic stainless steel weld metal. Generally used for joining of stainless steels with similar composition and surfacing of seating surfaces of steam, water and gas valves, which are made of stainless steels. Also used for corrosion resistant build-up, buffer or wear resistant surfaces on Cr containing steels and stainless steels. Preheating and interpass temperature shall be 200 - 300 °C and post weld heat treatment at 730 - 800 °C is necessary.</p>	<p></p> <p></p> <p></p> <p>If required 2 Hour</p>

Typical Chemical Analysis of All-Weld Metal (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Dimension (mm)	Packing Weigth (kg) Box Type
C: 0.03	490	620	38	20°C: 70	2.50 x 300 3.25 x 300 3.25 x 350 4.00 x 350	1.75 - 2.50 kg - Vacuum 2.50 kg - Plastic
Si: 0.40						
Mn: 1.50						
Cr: 20.00						
Ni: 10.00						
Nb: 0.70						
C: 0.02	420	590	35	20°C: 70	2.50 x 300 3.25 x 350 4.00 x 350	1.75 - 2.50 kg - Vacuum 2.50 kg - Plastic
Si: 0.70						
Mn: 1.25						
Cr: 20.50						
Ni: 25.00						
Mo: 5.00						
Cu: 1.60						
C: 0.06	-	After Heat Treatment (740°C 1 Hour)		20°C: 50	2.50 x 350 3.25 x 350 4.00 x 350	2.50 kg - Vacuum / Plastic 5.00 kg - Plastic
Si: 0.45						
Mn: 0.80		750	22			
Cr: 12.00		Hardness 375 HB				
Ni: 0.50						
C: 0.06	-	After Heat Treatment (600°C 1 Hour)		20°C: 47	2.50 x 350 3.25 x 350 4.00 x 350 5.00 x 350	2.50 kg - Vacuum / Plastic 5.00 kg - Plastic
Si: 0.40						
Mn: 0.80		850	17			
Cr: 12.00		Hardness 410 HB				
Ni: 4.00						
Mo: 0.50						
C: 0.08	475	After Heat Treatment (780°C 2 Hour)		20°C: 47	2.50 x 350 3.25 x 300 3.25 x 350 4.00 x 350 5.00 x 350	2.50 kg - Vacuum / Plastic 5.00 kg - Plastic
Si: 0.65						
Mn: 0.80		720	23			
Cr: 16.50		Hardness 220 HB				

STICK ELECTRODES

Stainless Steel Electrodes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>EI 2209</p> <p>AWS/ASME SFA - 5.4 E2209-16 EN ISO 3581 - A E 22 93 N L R 12 TS EN ISO 3581 - A E 22 93 N L R 12 DIN M. No. ~1.4462</p>	<p>Electrode for welding duplex (ferritic-austenitic) stainless Cr-Ni-Mo steels. Especially used in welding of acid tanks and pipes, in chemical, petrochemical, paper, shipbuilding and desalination industries. Suitable also for welding duplex stainless steels to carbon steels. The delta-ferrite content of the as-deposited weld metal amounts to approx. 25 to 35 %. The high-strength and ductile weld metal exhibits good resistance to pitting, crevice corrosion and stress corrosion cracking in chloride-bearing media. For operating temperatures of up to 250°C. Possible to use equally well both with AC and DC. Fine metal droplet transfer, good fusion of joint faces, finely rippled bead surface, easy arc striking, restriking and slag removal.</p>	<p></p> <p></p> <p></p> <p>If required 2 Hour</p>

Aluminium Alloy Electrodes




Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>EAL 1100</p> <p>AWS/ASME SFA - 5.3 E1100 EN ISO 18273 E AI 1080 A(AI 99,8) TS EN ISO 18273 E AI 1080 A(AI 99,8) TS 9604 EL-AI99.5 DIN M No. 3.0286</p>	<p>Special coated electrode for welding pure aluminium. Weld metal has good color matching with base metal and high electrical conductivity. Hold the electrode perpendicularly to workpiece, with a short arc length, during welding. If the thickness is greater than 10 mm or in large workpieces, preheating shall be applied between 150°C to 250°C. Since slag residues are corrosive, they must be completely removed from the weld bead. Electrode serves well as consumable in oxyacetylene welding. The covering being hygroscopic, electrodes must be stored in an absolutely dry location, or redried if required.</p>	<p></p> <p></p> <p></p> <p>If required 1 Hour</p>
<p>EAL 4043</p> <p>AWS/ASME SFA - 5.3 E4043 EN ISO 18273 E AI 4043 (AISI 5) TS EN ISO 18273 E AI 4043 (AISI 5) TS 9604 EL-AISI5 DIN M No. 3.2245</p>	<p>Special coated electrode for welding aluminium-silicon alloys and for joining dissimilar aluminium alloys. Suitable to use also in aluminium castings, containing up to 5% silicon. Used with DCEP. Hold the electrode perpendicularly to workpiece, with a short arc length, during welding. If the thickness is greater than 10 mm or in large workpieces, preheating shall be applied between 150°C to 250°C. Since slag residues are corrosive, they must be completely removed from the weld bead. Electrode serves well as consumable in oxyacetylene welding. The covering being hygroscopic, electrodes must be stored in an absolutely dry location, or redried if required.</p>	<p></p> <p></p> <p></p> <p>If required 1 Hour</p>
<p>EAL 4047</p> <p>AWS/ASME SFA - 5.3 E4047 EN ISO 18273 E AI 4047 (AISI 12) TS EN ISO 18273 E AI 4047 (AISI 12) TS 9604 EL-AISI12 DIN M No. 3.2585</p>	<p>Special coated electrode for aluminium-silicon and aluminium-magnesium-silicon castings. Suitable to use also in aluminium castings, containing up to 12% silicon. Used with DCEP. Hold the electrode perpendicularly to workpiece, with a short arc length, during welding. If the thickness is greater than 10 mm or in large workpieces, preheating shall be applied between 150°C to 250°C. Since slag residues are corrosive, they must be completely removed from the weld bead. Electrode serves well as consumable in oxyacetylene welding. The covering being hygroscopic, electrodes must be stored in an absolutely dry location, or redried if required.</p>	<p></p> <p></p> <p></p> <p>If required 1 Hour</p>

Typical Chemical Analysis of All-Weld Metal (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Dimension (mm)	Packing Weigth (kg) Box Type
C: 0.02	660	800	28	20°C: 47 -20°C: 35	2.50 x 300 2.50 x 350 3.25 x 350 4.00 x 350 5.00 x 350	1.75 -2.50 kg - Vacuum
Si: 0.70						
Mn: 1.00						
Cr: 22.50						
Ni: 9.80						
Mo: 3.20						
N: 0.10						










Typical Chemical Analysis of All-Weld Metal (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Dimension (mm)	Packing Weigth (kg) Box Type
Al: 99,80	55	85	25	-	2.50 x 350 3.25 x 350 4.00 x 350	2.00 kg - TIN
Si: 5.00	90	120	15	-	2.50 x 350 3.25 x 350	2.00 kg - TIN
Mn: 0.20						
Fe: 0.30						
Al: 94.50	80	200	8	-	2.50 x 350 3.25 x 350 4.00 x 350	2.00 kg - TIN
Si: 12.00						
Fe: 0.30						
Al: 87.70						

STICK ELECTRODES

Copper Alloy Electrode

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>ECU Sn7</p> <p>AWS/ASME SFA - 5.6 DIN 1733</p> <p>~ ECuSn-C EL-CuSn7</p>	<p>Electrode for joining and surfacing of pure copper and copper alloys and also surfacing of steels, cast steels, grey cast iron such as piston arms, sprockets, guides, turbine and centrifugal blades, ship screw propellers, motor collectors etc. For surfacing application, the initial runs should be welded at the lowest possible amperage. To obtain the typical mechanical properties, preheat the workpiece to 350°C and maintain this heat throughout the welding operation.</p>	<p></p> <p></p> <p></p> <p>If required 2 Hour</p>

Nickel Alloy Electrodes
















Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>ENI 422</p> <p>AWS/ASME SFA - 5.11 EN ISO 14172 TS EN ISO 14172 DIN M No.</p> <p>ENiCrFe-3 E Ni 6182 E Ni 6182 2.4620</p>	<p>Basic coated electrode with Ni-Cr-Fe type nickel base deposit. Used for repairing and joining of nickel alloys, 5 - 9% Nickel steels, cryogenic stainless steels down to -196°C, Incoloy 800 and other high temperature steels. Provides a weld metal which has a operating temperatures from -196°C to 800°C. Used for joining dissimilar materials as stainless steels/low alloyed steels, stainless steels/Nickel alloys, buffering of difficult to weld steels. Weld metal deposit is insensitive to cracks, has very good resistance to acids, salts and alkaline solutions, molten salt (e.g. cyanide) in oxidizing and carburization atmospheres (avoid a sulphurous atmosphere). Generally used for welding on oven parts, burners, heat treatment equipment, cement works, moulds, transport and storage tanks of liquid gas. Has a wide range of application in chemical industry, petrochemical industry, glassworks, civil engineering, repairing and maintenance workshops.</p>	<p></p> <p></p> <p></p> <p>If required 2 Hour</p>
<p>ENI 424</p> <p>AWS/ASME SFA - 5.11 EN ISO 14172 TS EN ISO 14172</p> <p>~ENiCrMo-4 E Ni 6275 E Ni 6275</p>	<p>Heavy coated, high recovery (170%) surfacing and hard surfacing electrode which gives Nickel-Chromium-Molibdenum alloy weld metal. Weld metal is resistant to abrasion, impact, corrosion and high temperatures. Especially used in welding of hot-work press tools which are subjected to above service conditions. Suitable to use in maintenance welding of hot-work press tools and hammers, forging and extrusion dies and parts, pressure casting pistons and dies, rolling rolls, hot-stripping tools, pump rotors and valves. Preheating to 400-500°C is required, depending on the size, shape and chemical analysis of the part to be welded. Has a stable arc, smooth weld bead surface and weld metal is free of cracks and porosity. Welding shall be performed with short stick-out distance, perpendicular to base metal and craters shall be filled well. Preferred to use with DC, electrode in positive (+) and possible to use also in AC.</p>	<p></p> <p></p> <p></p> <p>If required 2 Hour</p>
<p>ENI 440</p> <p>AWS/ASME SFA - 5.11 EN ISO 14172 TS EN ISO 14172 DIN M No.</p> <p>ENiCu-7 E Ni 4060 E Ni 4060 2.4366</p>	<p>Electrode having monel core wire, designed for joining and surfacing welds of Monel-clad steels. Suitable for joining Monel alloys to steel weld surfacing of steel with corrosion-resistant Monel coating. The weld metal is free of porosity and resistant to many chemicals. Suitable for applications with working temperatures from -196°C to 450°C. Weld groove preparation and cleaning should be done carefully. Generally welding should be done in horizontal position with short stick-out distance without weaving. Due to porosity risk of the weld metal, welding and striking shall be started on end plate. Possible to use with DCEP.</p>	<p></p> <p></p> <p></p> <p>If required 2 Hour</p>

Typical Chemical Analysis of All-Weld Metal (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Hardness (HB)	Dimension (mm)	Packing Weigth (kg) Box Type
Mn: 0.30	130	290	-	110	2.50 x 300 3.25 x 350 4.00 x 350 5.00 x 450	1.75 - 2.00 kg - Vacuum
Ni: 0.40						
Cu: 91.00						
Cr: 0.30						
Sn: 8.00						

Typical Chemical Analysis of All-Weld Metal (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Hardness (HB)	Dimension (mm)	Packing Weigth (kg) Box Type
C: 0.03	400	640	32	-196°C : 100 20°C : 120	-	2.50 x 300 3.25 x 350 4.00 x 350 5.00 x 450	2.50 kg - Cardboard / Plastic 5.00 - 6.50 kg - Cardboard / Plastic 1.75 - 2.50 kg - Vacuum
Si: 0.50							
Mn: 6.00							
Cr: 16.00							
Ni: 69.20							
Mo: 0.02							
Nb: 2.00							
Fe: 6.25							
Co: 2.00							
C: 0.02							
Si: 0.50	520	720	33	-	200 HB	2.50 x 300 2.50 x 350 3.25 x 300 3.25 x 350 4.00 x 400 5.00 x 350	1.00 kg - Plastic 1.75 - 2.25 kg - Cardboard / Plastic
Mn: 0.60							
Cr: 14.50							
Ni: 55.00							
Mo: 18.50							
Fe: 5.50							
W: 3.20							
C: 0.01	320	550	40	20°C: 120	-	2.50 x 300 3.25 x 300 4.00 x 400 5.00 x 400	1.00 kg - Plastic 1.75 - 2.25 kg - Cardboard / Vacuum
Mn: 1.00							
Ni: 65.00							
Cu: 30.00							
Fe: 2.50							

STICK ELECTRODES

Electrodes for Cast Irons

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>ENI 400 (Ni)</p> <p>AWS/ASME SFA - 5.15 ENi-CI EN ISO 1071 E C Ni-CI 3 TS EN ISO 1071 E C Ni-CI 3</p>	<p>Electrode having a pure nickel core wire, designed for the welding of cast iron with preheat. Suitable for welding grey cast iron, white and grey malleable cast iron, nodular cast iron. For repairing cracked and worn castings or joining cast iron parts to components made of steel, copper and nickel materials. Provides easy arc striking, restriking and stable arc. Weld metal is machinable. Weld short beads (approx. 30 to 50 mm long). For reducing weld residual stresses, hammer peen welds before cooling. Preferably used with DCEP but possible to use also with AC.</p>	   If required 1 Hour
<p>ENI 402 (Ni)</p> <p>AWS/ASME SFA - 5.15 ENi-CI EN ISO 1071 E C Ni - CI 3 TS EN ISO 1071 E C Ni - CI 3</p>	<p>Electrode having a pure nickel core wire for welding cast iron without or with low preheating (max. 300°C). Suitable for welding cast iron with lamellar graphite, white and black heart malleable and nodular cast iron. Used also for repair welding of cracked cast iron parts or joining components made of steel, copper or nickel materials to cast irons. Weld metal is machinable. Provides easy arc striking and restriking, stable arc and smooth bead surface. Weld short beads, about 30 to 50 mm long. In order to reduce weld residual stresses, hammer-peen welds slightly before cooling. Preferably used with DCEP but possible to use also with AC.</p>	   If required 1 Hour
<p>ENI 404 (Mo)</p> <p>AWS/ASME SFA - 5.15 ENiCu-B EN ISO 1071 E C NiCu-B 3 TS EN ISO 1071 E C NiCu-B 3</p>	<p>Electrode having a nickel-copper core wire for welding cast iron with preheating. Iron admixture from base metal should be kept low. Well-suited to welding cast iron with lamellar graphite, white, and black heart malleable cast iron, nodular cast iron. Weld metal closely matches colour of base metal. Thus electrode is preferably used for making filler and cover passes or for filling-up shrinkage cavities. Provides easy arc striking and restriking and stable arc. Weld metal is machinable. Weld short beads, about 30 to 50 mm long. In order to reduce weld residual stresses, hammer-peen welds slightly before cooling.</p>	   If required 1 Hour
<p>ENI 406 (Mo)</p> <p>AWS/ASME SFA - 5.15 ENiCu-B EN ISO 1071 E C NiCu-B 3 TS EN ISO 1071 E C NiCu-B 3</p>	<p>Electrode having a nickel-copper core wire for welding cast iron without or with low preheating (up to 300°C). Well-suited to welding cast iron with lamellar graphite, white and black heart malleable cast iron, nodular cast iron. Weld metal closely matches colour of base metal. Electrode is preferably used for making filler and cover passes of for filling-up shrinkage cavities. Weld metal is machinable. Provides easy arc striking and restriking, stable arc, smooth bead surface. Weld short beads, about 30 to 50 mm long. In order to reduce weld residual stresses, hammer-peen welds slightly before cooling.</p>	   If required 1 Hour
<p>ENI 412</p> <p>AWS/ASME SFA - 5.15 ENi-CI EN ISO 1071 E C Ni-CI 3 TS EN ISO 1071 E C Ni-CI 3</p>	<p>Electrode having a nickel core wire, for welding on grey cast iron with and without preheating. Suitable for welding joints as well as for surfacing of worn cast iron parts. Suitable to use in repair of machine frames, machine housings, machine parts and bearing blocks. The electrode has a very soft, regular fusion, and a quiet and steady arc. It is well suited for positional welding. Very little dilution with the parent metal takes place, resulting in good machinability of the transition area. Weld short beads, about 30 to 50 mm long. In order to reduce weld residual stresses, hammer-peen welds slightly before cooling. Preferably is used with DCEN but possible to use with also AC.</p>	   If required 1 Hour

Typical Chemical Analysis of All-Weld Metal (%)	Hardness (HB)	Dimension (mm)	Packing Weigth (kg) Box Type
C: 0.50	160	2.50 x 300 3.25 x 300 4.00 x 400 5.00 x 400	1.00 kg - Plastic 1.75 - 2.25 kg - Vacuum 2.50 kg - Plastic
Si: 0.25			
Mn: 0.25			
Fe: 1.00			
Ni: 98.00			
C: 0.40	160	2.50 x 300 3.25 x 300 4.00 x 400 5.00 x 400	1.00 kg - Plastic 1.75 - 2.25 kg - Vacuum 1.75 - 2.50 kg - Plastic
Si: 0.45			
Mn: 0.20			
Ni: 97.50			
Ti: 0.45			
Fe: 1.00			
C: 0.50	160	2.50 x 300 3.25 x 300 4.00 x 400 5.00 x 400	1.00 kg - Plastic 1.75 - 2.25 kg - Vacuum 2.50 kg - Plastic
Si: 0.20			
Mn: 0.80			
Fe: 3.50			
Ni: 64.00			
Cu: 31.00			
C: 0.50	160	2.50 x 300 3.25 x 300 4.00 x 400 5.00 x 400	1.00 kg - Plastic 1.75 - 2.25 kg - Vacuum 2.50 kg - Plastic
Si: 0.50			
Mn: 1.00			
Fe: 3.50			
Ni: 64.00			
Cu: 30.00			
Ti: 0.50			
C: 0.80	175	2.50 x 300 3.25 x 300 4.00 x 400	1.00 kg - Plastic 1.75 - 2.25 kg - Vacuum 2.50 kg - Plastic
Si: 0.80			
Mn: 0.20			
Ni: 97.00			
Al: 0.10			
Fe: 0.75			
Ti: 0.35			

STICK ELECTRODES

Electrodes for Cast Irons

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>ENI 416 (NiFe)</p> <p>AWS/ASME SFA - 5.15 ENiFe-CI EN ISO 1071 E C NiFe-CI 3 TS EN ISO 1071 E C NiFe-CI 3</p>	<p>Electrode having a nickel-iron core wire, for welding cast iron with or without preheating. The weld metal features a low coefficient of thermal expansion and as a result, little shrinkage. It has higher strength properties than pure nickel weld metal and is therefore preferably used for welding nodular cast iron, white and black heart malleable cast iron, as well as austenitic nodular cast iron or joining these metals to components made of steel, copper or nickel materials. Easy arc striking and restriking, stable arc, smooth bead. Weld metal is machinable. Weld short beads.</p>	<p></p> <p></p> <p></p> <p>If required 1 Hour</p>

Hardfacing Electrodes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>EH 245</p> <p>AWS/ASME SFA - 5.13 E FeMn-A EN ISO 14700 E Fe9 TS EN ISO 14700 E Fe9 DIN 8555 E 7-UM-200-KP</p>	<p>Basic covered, austenitic manganese steel electrode for wear resisting hardfacing deposits on high manganese (12-14%) steels. Weld metal will adopt high hardness by cold-working, it is therefore particularly suited for parts which are subjected mainly to wear caused by heavy impact and shock. During welding, the workpieces should not become too hot and if necessary, be allowed to cool down. When welding large workpieces made of austenitic manganese steel, such as crusher jaw plates, it is advisable to weld them in a water bath. Welding shall be done at low welding currents, with stringer and short bead lengths, to avoid the workpiece cool down. So, high welding currents and wide-weave beads must be avoided. When building up various layers, it is good practice depositing a buffer layer with E1 307 weld metal. When making joint welds on austenitic manganese steel, it is preferable to use E1 307B electrodes. Suitable for hardfacing and repair welding of wear resisting parts made of austenitic manganese steel, such as crusher jaw plates, crusher cones, rolls, pulverizing hammers, beating arms and others. Preferably used with DC, electrode in positive (+) pole and also possible to use with AC.</p>	<p></p> <p></p> <p></p> <p>If required 2 Hour</p>
<p>EH 247</p> <p>AWS/ASME SFA - 5.13 EFeMn-C AWS/ASME SFA - 5.13 ~EFeMn-A EN 14700 E Z Fe9 TS EN 14700 E Z Fe9 DIN 8555 ~E 7-UM-200-KP</p>	<p>High recovery (120%), austenitic manganese steel electrode for hardfacing and joining of high manganese steels. Due to its excellent impact resistance, particularly suited for parts which are subjected to heavy impact, shock and cavitation. The addition of Ni and Cr alloys, increases the resistance against cracks and abrasion. Weld metal work hardens by cold-working. During welding, the workpieces should not become too hot and it shall be cool down, when necessary. High welding currents and wide-weave beads must be avoided. Machining is possible with tungsten carbide tipped tools. Suitable for hardfacing and repair welding of dredge pumps, hydraulic press pistons, crane wheels, rail crossings, crusher jaws, excavator and grab teeth, mill hammers, rock crusher.</p>	<p></p> <p></p> <p></p> <p>If required 2 Hour</p>
<p>EH 250</p> <p>AWS/ASME SFA - 5.13 ~E FeMnCr EN 14700 E Z Fe9 TS EN 14700 E Z Fe9 DIN 8555 E 7-UM-250-KPR</p>	<p>High recovery (140%), austenitic manganese steel electrode for joining and hardfacing of high manganese steels which are subjected to very high pressure, shocks and abrasion. It is suitable to use as a buffer layer prior to hardfacing. Due to its 12% Cr content, weld metal has high crack resistance and abrasion resistance with respect to other manganese steel electrodes. Weld metal work hardens by cold-working. Workpiece shall not become too hot during welding and when necessary, it shall be cool down before next hardfacing passes. High welding currents and wide-weave beads must be avoided. When welding large workpieces made of austenitic manganese steels, it is advisable to weld them in a water bath. Suitable for hardfacing and repair welding of dredge pumps, hydraulic press pistons, crane wheels, rail crossings, crusher parts subjected to impact of soft minerals.</p>	<p></p> <p></p> <p></p> <p>If required 2 Hour</p>

**Typical
Chemical Analysis
of All-Weld Metal (%)**

**Hardness
(HB)**

**Dimension
(mm)**

**Packing Weigth (kg)
Box Type**

C: 0.45

Si: 1.60

Mn: 0.65

Ni: 52.00

Fe: 44.50

Al: 0.80

210

2.50 x 300
3.25 x 300
4.00 x 400

1.00 kg - Plastic
1.75 - 2.25 kg - Vacuum
2.50 kg - Plastic

**Typical
Chemical Analysis
of All-Weld Metal (%)**

**Hardness
(HB)**

**Dimension
(mm)**

**Packing Weigth (kg)
Box Type**

C: 0.60

Mn: 14.00

Ni: 2.70

Fe: 82.70

As Welded: 200 HB

Work Hardened: 450 HB

2.50 x 350
3.25 x 350
4.00 x 450
5.00 x 450

2.50 kg - Cardboard / Plastic
5.00 - 6.50 kg - Cardboard / Plastic

C: 0.70

Si: 0.40

Mn: 13.50

Cr: 3.30

Ni: 3.10

Fe: 79.00

As Welded: 225 HB

Work Hardened: 450 HB

3.25 x 350
4.00 x 450

2.50 kg - Cardboard / Plastic
5.00 - 6.50 kg - Cardboard / Plastic

C: 0.50

Si: 0.70

Mn: 16.00

Cr: 12.00

Fe: 70.80

As Welded: 230 HB

Work Hardened: 450 HB

3.25 x 350
4.00 x 450

2.50 kg - Cardboard / Plastic
5.00 - 6.50 kg - Cardboard / Plastic

STICK ELECTRODES


Hardfacing Electrodes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>EH 330</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>E Fe1 E Fe1 E 1-UM-300-P</p>	<p>Thick basic-covered electrode for producing hardfacing deposits of medium hardness, which can be machined by chip-forming. Particularly suited for wear resisting parts subjected to metal-to-metal wear, heavy impact and shock. EH 330 can be easily welded in all positions, except vertical-down. Weld metal is crack resistant and free of pores. Suitable for reconditioning of rails, rail crossings, switch points, sprockets and wearing parts, such as rope pulleys, tumblers, rollers, caterpillar track rollers and links, wheel flanges, stud links and others. DC, electrode in positive (+) is preferred and possible to use also in AC.</p>	<p>If required 2 Hour</p>
<p>EH 340</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>E Fe1 E Fe1 E 1-UM-400-P</p>	<p>Thick basic-covered electrode for producing highly wear resisting hardfacing deposits. It is particularly resistant to metal-to-metal wear, impact and shock. Suitable for reconditioning of rails, rail crossings and switch points, wearing parts such as dredger parts, polygon edges, bearing surfaces, striking tools, die tyres, wheel flanges, slide surfaces subject to heavy wear, reconditioning of lower dies, punches and others. Weld metal can be machined only by using sintered hard metal tipped tools. Even a large number of layers can be deposited without the need of intermediate buffer layers. A tough buffer layer using ESB 40 or EI 307B electrodes is solely required in case of very crack sensitive base metal. EH 340 can be welded in all positions, except vertical-down. Preferred to use with DC, electrode in positive (+) pole and also possible to use with AC.</p>	<p>If required 2 Hour</p>
<p>EH 350</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>E Z Fe2 E Z Fe2 ~E 2-UM-50-GP</p>	<p>Thick basic-covered electrode for producing wear resisting hardfacing deposits, which is particularly resistant to metal-to-metal wear, impact and abrasion. Suitable for reconditioning of rails, rail crossings and switch points, wearing parts such as dredger parts, polygon edges, bearing surfaces, striking tools, die tyres, wheel flanges, slide surfaces subject to heavy wear, reconditioning of lower dies, punches, cutting blades, table and rolling rolls. Weld metal can be machined only by using sintered hard metal tipped tools. A tough buffer layer using ESB 40 or EI 307B electrodes is solely required in case of very crack sensitive base metal. Can be welded in all positions, except vertical-down. Preferred to use with DC, electrode in positive (+) pole and also possible to use with AC.</p>	<p>If required 2 Hour</p>
<p>EH 360R</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>E Fe8 E Fe8 E 6-UM-60-GPT</p>	<p>Thick rutile-covered electrode for depositing tough and wear resisting hardfacing overlays. It is particularly resistant to high metal-to-metal wear, moderate impact and abrasion. The weld metal has sufficient red hardness up to 600°C. It is machinable only by grinding. Suitable hardfacing applications where wear resistance at higher temperatures is a prime concern, as in hot cut offs, dies for pressure castings, rolls, crushers excavator parts, bucket edges and bucket teeth, drilling bits, coal planes, conveyor screws. In case of crack sensitive base metals, a tough buffer layer made by ESB 40 or EI 307B electrodes, is required and a further one after every third hardfacing layer. The as-welded hardness of 59 HRC can be increased to 60-65 HRC by single or double tempering. Possible to use equally well both with AC and DC.</p>	<p>If required 2 Hour</p>
<p>EH 360B</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>E Fe8 E Fe8 E 6-UM-60-GPT</p>	<p>Thick basic-covered electrode for depositing tough and wear resisting overlays on structural members, subjected to severe wear. It is particularly resistant to high metal-to-metal wear, moderate impact and abrasion. The weld metal has sufficient red hardness up to 600°C. It can be machined only by grinding. Suitable hardfacing applications where wear resistance at higher temperatures is a prime concern, as in hot cut offs, dies for pressure castings, rolls, crushers excavator parts, bucket edges and bucket teeth, drilling bits, coal planes, conveyor screws. Multi-layers deposits will be free of cracks, even without depositing intermediate buffer layers. Only in case of very crack sensitive base metals, a tough buffer layer, made with ESB 40 or EI 307B electrodes, is required. Preferred to use with DC, electrode in positive (+) pole and also possible to use with AC.</p>	<p>If required 2 Hour</p>

Typical Chemical Analysis of All-Weld Metal (%)	Hardness (HB)	Dimension (mm)	Packing Weigth (kg) Box Type
C: 0.05	320 HB	2.50 x 350 3.25 x 350 4.00 x 450 5.00 x 450	2.50 kg - Cardboard / Plastic 5.00 - 6.50 kg - Cardboard / Plastic
Si: 0.80			
Mn: 0.65			
Cr: 3.40			
Fe: 95.10			
C: 0.15	42 HRc	3.25 x 350 4.00 x 450 5.00 x 450	2.50 kg - Cardboard / Plastic 5.00 - 6.50 kg - Cardboard / Plastic
Si: 0.80			
Mn: 0.60			
Cr: 2.80			
Fe: 95.65			
C: 0.20	50 HRc	3.25 x 350 4.00 x 450	2.50 kg - Cardboard / Plastic 5.00 - 6.50 kg - Cardboard / Plastic
Si: 0.85			
Mn: 1.30			
Cr: 5.40			
Fe: 92.25			
C: 0.50	58 HRc	2.50 x 350 3.25 x 350 4.00 x 450 5.00 x 450	1.00 kg - Plastic 2.50 kg - Cardboard / Plastic 5.00 - 6.50 kg - Cardboard / Plastic
Si: 0.65			
Mn: 0.60			
Cr: 9.00			
V: 0.40			
Fe: 88.85	59 HRc	2.50 x 350 3.25 x 350 4.00 x 350 4.00 x 450 5.00 x 450	2.50 kg - Cardboard / Plastic 5.00 - 6.50 kg - Cardboard / Plastic
C: 0.50			
Si: 0.80			
Mn: 0.60			
Mo: 0.50			
Cr: 8.00			
V: 0.65			
Fe: 88.95			

STICK ELECTRODES

Hardfacing Electrodes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>EH 360Si</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>E Z Fe2 E Z Fe2 ~E 2-UM-60-G</p>	<p>Thick basic-covered electrode for depositing wear resisting overlays on structural members subjected to severe abrasive wear. Weld metal can be machined only by grinding. Suitable for hardfacing applications of crushing and grinding of coal, mineral, soil, rocks, excavator parts, bucket edges and bucket teeth, drilling bits, coal planes, conveyor screws. In case of very crack sensitive base metals, a tough buffer layer, made with ESB 40 or EI 307B electrodes, is required, before hardfacing. Preferred to use with DC, electrode in positive (+) pole and also possible to use with AC.</p>	<p></p> <p></p> <p></p> <p>If required 2 Hour</p>
<p>EH 380</p> <p>AWS/ASME SFA - 5.13 EN 14700 TS EN 14700 DIN 8555</p> <p>E Fe6 E Fe4 E Fe4 E 4-UM-60-ST</p>	<p>Hardfacing electrode for manufacturing and repair welding of turning and planing chisels, reaming and shear blades, special spiral drills. Also suitable for manufacturing tools from unalloyed and low alloy steels and hardfacing the edges of cutting tools made of tool steel. Unalloyed and low alloy steels shall be preheated to 250-400°C before welding and postweld heat treatment at 400°C and then welded parts shall be cooled slowly. If buffer layer is needed, can be performed by EI 312 or EI 307B electrodes (max. 2,5 mm) and then hardfacing can be performed by EH 380 (max. 5 mm in height). Possible to use with DC, electrode in positive (+) pole and with AC.</p>	<p></p> <p></p> <p></p> <p>If required 2 Hour</p>
<p>EH 382</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>E Fe3 E Fe3 E 3-UM-45-ST</p>	<p>Basic coated electrode for build-up and hardfacing of parts subjected to high metal-or-metal wear, compression, impact at elevated temperatures. Weld metal is resistant to operating temperatures up to 550° C. Due to it's high strength, toughness and heat resistance ideally suited for hot and cold cutting tools, hot shears blades, forging dies, saddles, hammers, die cast moulds. Electrode can also be used for production of new hot and cold cutting tools and their edges, which are made of low alloy steels. Has a stable arc, good bead appearance and very easy slag removal.</p>	<p></p> <p></p> <p></p> <p>If required 2 Hour</p>
<p>EH 384</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>E Fe3 E Fe3 E 3-UM-60-ST</p>	<p>Rutile coated electrode for build-up and hardfacing of parts subjected to high metal-or-metal wear, compression, impact at elevated temperatures. Weld metal is resistant to operating temperatures up to 600° C, because of it's Cr, Mo, W, V content. Due to it's high strength, toughness and heat resistance ideally suited for hot forging dies, saddles, hammers, hot and cold cutting tools, hot shears blades and rolling mills. Electrode can also be used for production of new hot and cold cutting tools and their edges, which are made of low alloy steels. Has a stable arc, good bead appearance and very easy slag removal.</p>	<p></p> <p></p> <p></p> <p>If required 2 Hour</p>
<p>EH 515</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>E Fe14 E Fe14 E 10-UM-60-CGRZ</p>	<p>High recovery (160%), thick rutile-covered electrode depositing hypereutectic chromium hard metal. It is suitable for producing highly wear resisting deposits subject to abrasion by mineral particles. Suitable for hardfacing worn parts subject to mineral abrasion, such as, conveyor screws, mixer blades, concrete pump parts, slurry pumps, stirring and agitator parts, crusher parts, excavator bucket edges, coal planes and worn parts in petrochemical industry, which are subject to corrosion at elevated temperatures. The typical transverse cracks appearing in this hardfacing weld metal are not detrimental to abrasion resistance. Weld metal is machinable only by grinding. On difficult-to-weld steels, a buffer layer made with EIS 307 electrodes is required. Produces very smooth and clean weld beads with flat penetration. Possible to use both with AC and DC.</p>	<p></p> <p></p> <p></p> <p>If required 2 Hour</p>

Typical Chemical Analysis of All-Weld Metal (%)	Hardness (HB)	Dimension (mm)	Packing Weigth (kg) Box Type
C: 0.65	60 HRc	3.25 x 350 4.00 x 450 5.00 x 450	2.50 kg - Cardboard / Plastic 5.00 - 6.50 kg - Cardboard / Plastic
Si: 4.00			
Mn: 0.55			
Cr: 2.00			
Fe: 92.80			
C: 1.10	As Welded: 60 HRc Work Hardened: 64 HRc	2.50 x 350 3.25 x 350 4.00 x 350 5.00 x 350	2.00 kg - Cardboard / Plastic
Si: 1.40			
Mn: 1.30			
Cr: 3.50			
Mo: 9.00			
V: 2.20			
W: 1.90			
Fe: 79.60			
C: 0.20	48 HRc	2.50 x 350 3.25 x 350 4.00 x 350	2.50 kg - Cardboard / Plastic
Si: 0.40			
Mn: 0.60			
Mo: 4.00			
Cr: 5.00			
Fe: 89.80			
C: 0.40	60 HRc	2.50 x 350 3.25 x 350 4.00 x 350	2.50 kg - Cardboard / Plastic
Si: 0.40			
Mn: 0.60			
Mo: 0.50			
Cr: 1.40			
V: 0.50			
W: 9.00			
Co: 3.00			
Fe: 84.70	60 HRc	2.50 x 350 3.25 x 350 4.00 x 350 5.00 x 350	2.50 kg - Plastic 5.00 kg - Cardboard / Plastic
C: 3.70			
Si: 1.50			
Mn: 0.20			
Cr: 32.00			
Fe: 62.60			

STICK ELECTRODES




Hardfacing Electrodes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>EH 528</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>E Fe15 E Fe15 E 10-UM-65-GR</p>	<p>Basic type, high recovery (180%) electrode for depositing primary and eutectic Cr and Nb carbides in austenitic matrix. Suitable for hardfacing of parts, subjected to heavy abrasion with moderate impact. Service temperature is max. 450°C. Suitable to use in hardfacing of cement crushers, cement presses and brick conveyor screws, mixer blades, press screws in oil industry, bucket lips and teeths in earth moving equipments. The typical transverse cracks occurring in such a hard metal is not suitable for applications where impact and shock conditions prevail. Wear coefficient of one layer deposit is 0.5 % with SiO₂. The weld metal is machinable only by grinding. Weld with long arc length and shall not be welded more than 2 layers. Possible to use with both DC and AC.</p>	<p></p> <p></p> <p>If required 2 Hour</p>
<p>EH 531</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>E Fe15 E Fe15 E 10-UM-65-GR</p>	<p>Heavy coated, high recovery (235%) hardfacing electrode, depositing evenly distributed Cr and B-carbides in austenitic stainless steel matrix. Required hardness and abrasion resistance can be obtained in the first layer even on low alloy steels. Suitable for hardfacing of parts subjected to heavy abrasion with moderate impact. Particularly used in excavator teeth, leading edges of excavator buckets, mixer blades, gravel pumps, cement fans, conveyor worn-screws, conveyor belts. The typical transverse cracks occurring in such a hard metal is not suitable for applications where impact and shock conditions prevail. The hardfacing layers have a very smooth surface and machinable only by grinding. Possible to use with both DC and AC.</p>	<p></p> <p></p> <p>If required 2 Hour</p>
<p>EH 540</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>E Fe16 E Fe16 E 10-UM-65-GRZ</p>	<p>Basic type, high recovery (235%) hardfacing electrode for depositing primary and eutectic Cr, Nb, Mo, W and V-carbides in austenitic matrix. Suitable for hardfacing of parts subjected to heavy abrasion with moderate impact and service temperatures up to 600°C. Suitable for use in crushing and screening plants, sinter plant parts, wear bars and plates, scraper bars, blast furnace charging systems, cement furnaces, bucket teeth and lips. The typical transverse cracks occurring in such a hard metal is not suitable for applications where impact and shock conditions prevail. Wear coefficient of 1 layer deposit is 0,3% with SiO₂. The weld metal is machinable only by grinding. It has a quiet and regular fusion. Weld with long arc length and shall not be welded more than 4 layers. Possible to use with both DC and AC.</p>	<p></p> <p></p> <p>If required 1 Hour</p>
<p>EH 801</p> <p>AWS/ASME SFA - 5.13 EN 14700 TS EN 14700 DIN 8555</p> <p>E CoCr-C E Co3 E Co3 E 20-UM-55-CSTZ</p>	<p>Rutile-basic coated hardfacing electrode which deposits Co-Cr-W alloy weld metal. Suitable to use in hardfacing of parts subjected to either the single or combined effect of: heavy metal-to-metal wear or abrasion, high temperatures (ranging from 500°C to 900°C) and corrosive environments. Due to its very high hardness it is recommended for applications where shocks are low or moderate. Suitable for rolling mill guides, extrusion dies, valve seats, mechanical parts of steam turbines, pump tubing and shafts and mixer blades. Preferred to use with DC, electrode in positive (+) and possible to use with also AC.</p>	<p></p> <p></p> <p>If required 1 Hour</p>
<p>EH 806</p> <p>AWS/ASME SFA - 5.13 EN 14700 TS EN 14700 DIN 8555</p> <p>E CoCr-A E Co2 E Co2 E 20-UM-40-CTZ</p>	<p>Rutile-basic type coated hardfacing electrode which deposits Co-Cr-W alloy weld metal. Suitable to use in hardfacing of parts subjected to either the single or combined effect of: heavy metal-to-metal wear or abrasion, high temperatures (ranging from 500°C to 900°C) and corrosive environments. Due to its very higher toughness and shock resistance extends its use for service conditions involving mechanical impacts and thermal shocks. Suitable for blades for hot shearing, ingot tong ends, glass moulds, valves and valve seats, nozzles. Preferred to use with DC, electrode in positive (+) and possible to use with also AC.</p>	<p></p> <p></p> <p>If required 1 Hour</p>







Typical Chemical Analysis of All-Weld Metal (%)	Hardness	Dimension (mm)	Packing Weigth (kg) Box Type
C: 5.50	63 HRc	2.50 x 350 3.25 x 350 4.00 x 350 5.00 x 350	2.50 kg - Plastic 5.00 kg - Cardboard / Plastic
Si: 1.40			
Mn: 1.90			
Cr: 25.00			
Nb: 5.50			
Fe: 60.70			
C: 4.50	Tek Pasoda: 65 HRc	2.50 x 350 3.25 x 350 4.00 x 350 5.00 x 350	1.00 kg -Plastic 2.50 kg - Plastic 5.00 kg - Cardboard / Plastic
Si: 1.00			
Mn: 0.30			
Cr: 33.00			
B: 1.00			
Fe: 60.20			
C: 4.50	64 HRc	2.50 x 350 3.25 x 350 4.00 x 350 5.00 x 350	2.50 kg - Plastic 5.00 kg - Cardboard / Plastic
Si: 1.30			
Mn: 0.85			
Cr: 20.50			
Mo: 6.20			
V: 1.10			
Nb: 4.00			
W: 2.20			
Fe: 59.35			
Co: 48.60			
C: 2.20	55 HRc	3.25 x 350 4.00 x 350	2.50 kg - Plastic
Si: 1.20			
Mn: 1.00			
Ni: 2.50			
Cr: 30.00			
W: 12.50			
Fe: 2.00			
Co: 60.10	42 HRc	3.25 x 350 4.00 x 350	2.50 kg - Plastic
C: 1.00			
Si: 0.90			
Mn: 1.00			
Ni: 2.50			
Cr: 28.00			
W: 4.50			
Fe: 2.00			

STICK ELECTRODES

Hardfacing Electrodes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>EH 812</p> <p>AWS/ASME SFA - 5.13 ECoCr-B EN 14700 E Co3 TS EN 14700 E Co3 DIN 8555 E 20-UM-50-CTZ</p>	<p>Rutile-basic type coated hardfacing electrode which deposits Co-Cr-W alloy weld metal. Suitable to use in hardfacing of parts subjected to either the single or combined effect of: heavy metal-to-metal wear or abrasion, high temperatures (ranging from 500°C to 900°C) and corrosive environments. Due to its very higher toughness and shock resistance extends its use for service conditions involving mechanical impacts and thermal shocks. Suitable for plastic extrusion screws, tools to cut paper, cardboard floor coverings, roofing, wood, galvanizing baths. Preferred to use with DC, electrode in positive (+) and possible to use with also AC.</p>	<p></p> <p></p> <p> If required 1 Hour</p>

Cutting and Gouging Electrodes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>ECUT</p>	<p>Electrode used for cutting, bevelling and piercing works. Particularly suitable for cutting industrial metals like steels, cast irons, non-ferrous metals and also metals which are difficult or impossible to cut with oxyacetylene process. Suitable for cleaning faulty welding places and defective surfaces at high speed and in all positions. Electrode should be definitely not left to dry, but should contain certain amount of dampness. Possible to use in DCEN or DCEP. DCEN provides higher metal removal speed.</p>	<p></p> <p></p>
<p>ECUT-S</p>	<p>Electrode especially used for all cutting, gouging, bevelling and piercing purposes. Particularly suitable for cutting industrial metals like steels, cast irons, non-ferrous metals and also metals which are difficult or impossible to cut with oxyacetylene process. Resulted surface finish is very clean and smooth. ECUT-S should be definitely not left to dry, but should contain certain amount of dampness. DCEN provides higher metal removal speed.</p>	<p></p> <p></p>
<p>EC 900</p>	<p>Electrode used for gouging and piercing works. Suitable for cleaning faulty welding places, defective surfaces and back-gouging on steels, cast iron, non-ferrous metals. The depth of the groove cut at one gouging should not exceed the diameter of the electrode. For cutting deep gouges the operation should be repeated several times. Electrode should be definitely not left to dry, but should contain certain amount of dampness. Preferred to use in DCEN due to it's higher metal speed.</p>	<p></p> <p></p>

**Typical
Chemical Analysis
of All-Weld Metal (%)**

Hardness

**Dimension
(mm)**

**Packing Weigth (kg)
Box Type**

Co: 53.10

C: 1.40

Si: 1.00

Mn: 1.00

Ni: 2.50

Cr: 30.00

W: 8.50

Fe: 2.50

48 HRc

3.25 x 350
4.00 x 350

2.50 kg - Plastic

**Dimension
(mm)**

**Packing Weigth (kg)
Box Type**

3.25 x 350
3.25 x 450
4.00 x 450
5.00 x 450

5.00 - 6.50 kg - Cardboard

2.50 x 350
3.25 x 350
3.25 x 450
4.00 x 450
5.00 x 450

4.50 - 5.50 kg - Cardboard

3.25 x 350
3.25 x 450
4.00 x 450
5.00 x 450

3.30 - 4.00 kg - Cardboard

GAS ARC TUNGSTEN (TIG) AND OXY-ACETYLENE WELDING RODS

GAS ARC TUNGSTEN (TIG) AND OXY-ACETYLENE WELDING RODS

Unalloyed Steel TIG and Oxy-Acetylene Welding Rods

Product Name	AWS / ASME SFA - 5.2/5.18	EN ISO 636-A / EN 12536	TS EN ISO 636-A / TS EN 12536	Page Number
OG 1	R45	O I	O I	59
OG 2	R60	O II	O II	59
TG 1	ER70S-3	W 42 3 2Si	W 42 3 2Si	59
TG 2	ER70S-6	W 46 2 3Si1	W 46 2 3Si1	59
TG 3	ER70S-6	W 46 3 4Si1	W 46 3 4Si1	59
TG 102	ER70S-2	W 42 2 2Ti	W 42 2 2Ti	61

Low-Alloyed, High Strength and Creep Resistant Steel Welding TIG Rods

Product Name	AWS / ASME SFA - 5.28	EN ISO 636-A / 21952-A	TS EN ISO 636-A/ 21952-A	Page Number
TG 150	ER80S-Ni1	W 46 6 3Ni1	W 46 6 3Ni1	61
TG 171	ER80S-Ni2	W 42 9 2Ni2	W 42 9 2Ni2	61
TG 201	ER80S-G ER70S-A1	W MoSi	W MoSi	61
TG 201A	ER80S-D2	W Z MnMo	W Z MnMo	63
TG 211	ER80S-G	W CrMo1Si	W CrMo1Si	63
TG 211A	ER80S-B2	W 55 1CM	W 55 1CM	63
TG 222	ER90S-G	W CrMo2Si	W CrMo2Si	63
TG 222A	ER90S-B3	W 62 2C1M	W 62 2C1M	63
TG 235	ER80S-B6	W CrMo5Si	W CrMo5Si	65
TG 285	ER80S-B8	W CrMo9	W CrMo9	65
TG 295	ER90S-B9	W CrMo91	W CrMo91	65

Stainless Steel TIG Welding Rods

Product Name	AWS / ASME SFA - 5.9	EN ISO 14343-A/-B	TS EN ISO 14343-A/-B	Page Number
TI 307Si	~ER307	W 18 8 Mn	W 18 8 Mn	67
TI 308L	ER308L	W 19 9 L	W 19 9 L	67
TI308LSi	ER308LSi	W 19 9 LSi	W 19 9 LSi	67
TI 309L	ER309L	W 23 12 L	W 23 12 L	67
TI 309LSi	ER309LSi	W 23 12 LSi	W 23 12 LSi	67
TI 310	ER310	W 25 20	W 25 20	67
TI 312	ER312	W 29 9	W 29 9	67
TI 316L	ER316L	W 19 12 3 L	W 19 12 3 L	69
TI316LSi	ER316LSi	W 19 12 3 L Si	W 19 12 3 L Si	69
TI 318	ER318	W 19 12 3 Nb	W 19 12 3 Nb	69
TI 347	ER347	W 19 9 Nb	W 19 9 Nb	71
TI 385	ER385	W 20 25 5 Cu L	W 20 25 5 Cu L	71
TI 410	ER410	W 13	W 13	71
TI 630	ER630	SS630	SS630	73
TI 2209	ER2209	W 22 9 3 N L	W 22 9 3 N L	73
TI 2594	ER2594	W 25 9 4 N L	W 25 9 4 N L	73

GAS ARC TUNGSTEN (TIG) AND OXY-ACETYLENE WELDING RODS

Aluminium Alloy TIG Welding Rods

Product Name	AWS / ASME SFA - 5.10	EN ISO 18273-A	TS EN ISO 18273-A	Page Number
TAL 1100	ER1070 ~ER1100	S Al 1070 (Al99.7)	S Al 1070 (Al99.7)	75
TAL 4043	ER4043	S Al 4043 (AlSi5)	S Al 4043 (AlSi5)	75
TAL 4047	ER4047	S Al 4047A (AlSi12(A))	S Al 4047A (AlSi12(A))	75
TAL 5183	ER5183	S Al 5183 (AlMg4.5Mn0.7(A))	S Al 5183 (AlMg4.5Mn0.7(A))	75
TAL 5356	ER5356	S Al 5356 (AlMg5Cr(A))	S Al 5356 (AlMg5Cr(A))	75

Copper Alloy TIG Welding Rods

Product Name	AWS / ASME SFA - 5.7	EN ISO 24373-A	TS EN ISO 24373-A	Page Number
TCU Al8	ERCuAl-A1	S Cu 6100 (CuAl7)	S Cu 6100 (CuAl7)	77

Nickel Alloy TIG Welding Rods

Product Name	AWS / ASME SFA - 5.14	EN ISO 18274-A	TS EN ISO 18274-A	Page Number
TNI 422	ERNiCr-3	SNi 6082	SNi 6082	77
TNI 425	ERNiCrMo3	SNi 6625 (NiCr22Mo9Nb)	SNi 6625 (NiCr22Mo9Nb)	77

Hardfacing TIG Rods

Product Name	AWS / ASME SFA - 5.7	EN ISO 14700-A	TS EN ISO 14700-A	DIN 8555*	Page Number
TH 801	ERCoCr-C	T Co3	T Co3	WSG 20-GO-55-CSTZ	79
TH 806	ERCoCr-A	T Co2	T Co2	WSG 20-GO-40-CTZ	79
TH 812	ERCoCr-B	T Co3	T Co3	WSG 20-GO-45-CTZ	79
T CARBIDE 3000	-	T Ni20	T Ni20	G 21-UM-55-CG	79

*This standard is no longer valid. Added for informational purposes.

GAS ARC TUNGSTEN (TIG) AND OXY-ACETYLENE WELDING RODS



Unalloyed Steel TIG and Oxy-Acetylene Welding Rods

Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>OG 1</p> <p>AWS/ASME SFA - 5.2 R45 EN 12536 O I TS 3623 EN 12536 O I</p>	<p>Low carbon steel welding rod for oxy-acetylene welding. It is a general purpose rod for welding low carbon steels and wrought iron with the required tensile strength does not exceed 310 N/mm². Generally used for automotive repair works like tears and rips in the body or patching on badly damaged parts, joining steel sheets and plates, tubing and piping installation where and intense heat source is required for straightening, forming, preheating post weld heat treatment, regardless of the complexity and position in which welding has to be done. Weld metal has got good ductility and machinability. Welding shall be performed in neutral flame characteristics. It has got a fluid weld puddle.</p>	
<p>OG 2</p> <p>AWS/ASME SFA - 5.2 R 60 EN 12536 O II TS 3623 EN 12536 O II</p>	<p>Low carbon steel welding rod, for oxy-acetylene gas welding, containing slightly higher manganese. It is a general purpose welding rod with medium strength, used for welding carbon steels and low alloy steels with tensile strengths up to 410 N/mm². Commonly used for carbon steel pipe installation and repair works in power plants, process piping, machine and agricultural tool repair, joining steel plates and wrought irons, filling holes and edged on wrought iron, where an intense heat source is required for straightening, forming, preheating post weld heat treatment, regardless of the complexity and position in which welding has to be done. Welding shall be performed in neutral flame characteristics. It has got a fluid weld puddle.</p>	
<p>TG 1</p> <p>AWS/ASME SFA - 5.18 ER70S-3 EN ISO 636 - A W 42 3 2Si TS EN ISO 636 - A W 42 3 2Si DIN M. No. 1.5112</p>	<p>GTA (TIG) welding rod for unalloyed steels, fine grained steels and pipes. Particularly suitable for welding of galvanized and pre-painted steels, welding low alloy steels in pipe-lines, boilers and tank production. Used in root and cap passes in chemical, petrochemical, water, natural gas pipes joints safely. Suitable also welding in thin metal plates and repair welds. Characterized by a reduced slag formation and smooth welding deposit. Thin and homogeneous copper coating increase resistance to rusting.</p>	
<p>TG 2</p> <p>AWS/ASME SFA - 5.18 ER70S-6 EN ISO 636 - A W 46 2 3Si1 TS EN ISO 636 - A W 46 2 3Si1 DIN M. No. 1.5125</p>	<p>GTA (TIG) welding rod for unalloyed steels, fine grained steels and pipes. Particularly used in root and cap passes in chemical, petrochemical, water, natural gas pipes joints safely. Suitable also welding of thin metal plates, tanks, boilers and repair welds of them. Thin and homogeneous copper coating increase resistance to rusting.</p>	
<p>TG 3</p> <p>AWS/ASME SFA - 5.18 ER70S-6 EN ISO 636 - A W 46 3 4Si1 TS EN ISO 636 - A W 46 3 4Si1 DIN M. No. 1.5130</p>	<p>GTA (TIG) welding rod for unalloyed steels, fine grained steels and pipes. Provides high mechanical properties. Particularly used in root and cap passes in chemical, petrochemical, water, natural gas pipes joints safely. Suitable also welding of thin metal plates, tanks, boilers and repair welds of them. Thin and homogeneous copper coating increase resistance to rusting.</p>	







Typical Chemical Analysis of Welding Rod (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Shielding Gas	Dimension (mm)	Packing Weigth (kg) Box Type
C: 0.05							
Si: 0.05	280	450	20	20°C: 50	-	1.60 x 1000 2.00 x 1000 2.40 x 1000 3.20 x 1000 4.00 x 1000 5.00 x 1000	5.00 kg - Cardboard
Mn: 0.50							
C: 0.10							
Si: 0.30	300	440	20	20°C: 50	-	1.60 x 1000 2.00 x 1000 2.40 x 1000 3.20 x 1000 4.00 x 1000	5.00 kg - Cardboard
Mn: 1.00							
C: 0.05							
Si: 0.60	440	530	29	-30°C: 100	I1 (%100 Ar)	1.60 x 1000 2.00 x 1000 2.40 x 1000 3.20 x 1000 4.00 x 1000	5.00 kg - Cardboard / Plastic
Mn: 1.30							
C: 0.06							
Si: 0.80	480	560	28	-30°C: 80 -20°C: 95	I1 (%100 Ar)	1.60 x 1000 2.00 x 1000 2.40 x 1000 3.20 x 1000 4.00 x 1000	5.00 kg - Cardboard / Plastic
Mn: 1.45							
C: 0.07							
Si: 0.90	490	580	28	-30°C: 80	I1 (%100 Ar)	1.60 x 1000 2.00 x 1000 2.40 x 1000 3.20 x 1000	5.00 kg - Cardboard / Plastic
Mn: 1.65							

GAS ARC TUNGSTEN (TIG) AND OXY-ACETYLENE WELDING RODS

Unalloyed Steel TIG and Oxy-Acetylene Welding Rods

Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>TG 102</p> <p>AWS/ASME SFA - 5.18 ER70S-2 EN ISO 636 - A W 42 2 2Ti TS EN ISO 636 - A W 42 2 2Ti</p>	<p>Micro-alloyed, GTA (TIG) welding rod for unalloyed steels. Due to its titanium (Ti) and aluminum (Al) micro alloy contents, particularly suitable for single pass welding of galvanized, pre-painted, rusty and dirty steels, welding low alloy steels in pipe-lines, boilers and tank construction. Suitable also welding in thin metal plates and repair welds. Thin and homogeneous copper coating increase resistance to rusting.</p>	 

Low-Alloyed, High Strength and Creep Resistant Steel Welding TIG Rods

Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>TG 150</p> <p>AWS/ASME SFA - 5.28 ER80S-Ni1 EN ISO 636 - A W 46 6 3Ni1 TS EN ISO 636 - A W 46 6 3Ni1</p>	<p>Low alloyed GTA (TIG) welding rod for steels subjected to operating temperatures down to -60°C. Weld metal has high strength and high toughness. Suitable to use in petrochemical, chemical, oil/gas industries and off-shore platforms, especially used for root and fill passes of pipes, boilers, tanks and also valves, pumps which are made of cast or forged steels.</p>	 
<p>TG 171</p> <p>AWS/ASME SFA - 5.28 ER80S-Ni2 EN ISO 636 - A W 42 9 2Ni2 TS EN ISO 636 - A W 42 9 2Ni2</p>	<p>Low alloyed GTA (TIG) welding rod for steels subjected to operating temperatures down to -90°C. Produces high strength and tough welded joints. Suitable to use in petrochemical, chemical, oil/gas industries and off-shore platforms, especially root and fill passes of pipes, boilers, tanks and also valves, pumps which are made of cast or forged steels.</p>	 
<p>TG 201</p> <p>AWS/ASME SFA 5.28 ER80S-G AWS/ASME SFA - 5.28 ER70S-A1 EN ISO 21952 - A W MoSi TS EN ISO 21952 - A W MoSi DIN M. No. 1.5424</p>	<p>Low alloyed GTA (TIG) welding rod for Mo-alloyed creep resisting steels, subjected to operating temperatures up to 530°C. Particularly used in root and cap passes of steam generators joints, boilers, pressure vessels and pipes, where high X-ray quality is required. Also suitable for welding carbon steel parts subsequently heat treated after welding. Observe directions of pre- and post-weld heat treatment of base metal.</p>	 

Typical Chemical Analysis of Welding Rod (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Shielding Gas	Dimension (mm)	Packing Weigth (kg) Box Type
C: 0.05	520	620	23	-30°C: 60	I1 (%100 Ar)	1.60 x 1000 2.00 x 1000 2.40 x 1000 3.20 x 1000 4.00 x 1000	5.00 kg - Cardboard / Plastic
Si: 0.70							
Mn: 1.20							
Zr: 0.08							
Ti: 0.13							
Al: 0.10							

Typical Chemical Analysis of Welding Rod (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Shielding Gas	Dimension (mm)	Packing Weigth (kg) Box Type
C: 0.10	480	570	28	-60°C: 90	I1 (%100 Ar)	2.00 x 1000 2.40 x 1000 3.20 x 1000	5.00 kg - Cardboard / Plastic
Si: 0.60							
Mn: 1.10							
Ni: 0.90							
C: 0.09	As Welded			20°C: 200 -90°C: 47	I1 (%100 Ar)	2.40 x 1000	5.00 kg - Cardboard / Plastic
Si: 0.55	470	550	20				
Mn: 1.10	After Heat Treatment (620°C 1 Hour)						
Ni: 2.45	500	630	26	-90°C: 150			
C: 0.10	As Welded			-20°C: 60 20°C: 110	I1 (%100 Ar)	1.60 x 1000 2.00 x 1000 2.40 x 1000 3.20 x 1000	5.00 kg - Cardboard / Plastic
Si: 0.80	540	620	26				
Mn: 1.00	After Heat Treatment (620°C 1 Hour)						
Mo: 0.50	530	610	27				

GAS ARC TUNGSTEN (TIG) AND OXY-ACETYLENE WELDING RODS







Low-Alloyed, High Strength and Creep Resistant Steel Welding TIG Rods

Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>TG 201A</p> <p>AWS/ASME SFA - 5.28 ER80S-D2 EN ISO 21952 - A W Z MnMo TS EN ISO 21952 - A W Z MnMo</p>	<p>Low alloyed, GTA (TIG) welding rod for Mo-alloyed creep resisting steels, subjected to operating temperatures up to 530°C. Contains high level of deoxidizing (Mn and Si) elements to control porosity during welding. Particularly used in root and cap pass welding of steam generators joints, boilers, pressure vessels and pipes, where high X-ray quality is required. Also suitable for welding carbon steel parts subsequently heat treated after welding. Observe directions of pre- and post-weld heat treatment of base metal.</p>	 
<p>TG 211</p> <p>AWS/ASME SFA - 5.28 ER80S-G EN ISO 21952 - A W CrMo1Si TS EN ISO 21952 - A W CrMo1Si DIN M. No. 1.7339</p>	<p>Low alloyed GTA (TIG) welding rod for Cr-Mo alloyed creep resisting steels, subjected to operating temperatures up to 570°C. Particularly used in root and cap passes of steam generators joints, boilers, pressure vessels and pipes, where high X-ray quality is required. Also suitable for welding carbon steel parts subsequently heat treated after welding. Observe directions of pre- and post-weld heat treatment of base metal.</p>	 
<p>TG 211A</p> <p>AWS/ASME SFA - 5.28 ER80S-B2 EN ISO 21952 - B W 55 1CM TS EN ISO 21952 - B W 55 1CM</p>	<p>Low alloyed, GTA (TIG) welding rod for Cr-Mo alloyed creep resisting steels, subjected to operating temperatures up to 570°C. Contains high level of deoxidizing (Mn and Si) elements to control porosity during welding. Particularly used in root and cap pass welding of steam generators joints, boilers, pressure vessels and pipes, where high X-ray quality is required. Also suitable for welding carbon steel parts subsequently heat treated after welding. Observe directions of pre- and post-weld heat treatment of base metal.</p>	 
<p>TG 222</p> <p>AWS/ASME SFA - 5.28 ER90S-G EN ISO 21952 - A W CrMo2Si TS EN ISO 21952 - A W CrMo2Si DIN M. No. 1.7384</p>	<p>Low alloyed, GTA (TIG) welding rod for Cr-Mo alloyed creep resisting steels, subjected to operating temperatures up to 600°C. Particularly used in root and cap passes of steam generators joints, boilers, pressure vessels and pipes, where high X-ray quality is required. Also suitable for welding carbon steel parts subsequently heat treated after welding. Observe directions of pre- and post-weld heat treatment of base metal.</p>	 
<p>TG 222A</p> <p>AWS/ASME SFA - 5.28 ER90S-B3 EN ISO 21952 - B W 62 2C1M TS EN ISO 21952 - B W 62 2C1M</p>	<p>Low alloyed, GTA (TIG) welding rod for Cr-Mo alloyed creep resisting steels, subjected to operating temperatures up to 600°C. Contains high level of deoxidizing (Mn and Si) elements to control porosity during welding. Particularly used in root and cap pass welding of steam generators joints, boilers, pressure vessels and pipes, where high X-ray quality is required. Also suitable for welding carbon steel parts subsequently heat treated after welding. Observe directions of pre- and post-weld heat treatment of base metal.</p>	 

Typical Chemical Analysis of Welding Rod (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Shielding Gas	Dimension (mm)	Packing Weigth (kg) Box Type
C: 0.10							
Si: 0.70	540	620	26	-30°C: 65 20°C: 110	I1 (%100 Ar)	1.60 x 1000	5.00 kg - Cardboard / Plastic
Mn: 1.80						2.00 x 1000	
Mo: 0.45						2.40 x 1000	
						3.20 x 1000	
C: 0.10	As Welded						
Si: 0.60	510	620	23	-20°C: 50 20°C: 80			
Mn: 1.00	After Heat Treatment (680°C 1 Hour)				I1 (%100 Ar)	2.00 x 1000	5.00 kg - Cardboard / Plastic
Cr: 1.20	500	600	24	-20°C: 60 20°C: 90		2.40 x 1000	
Mo: 0.50						3.20 x 1000	
C: 0.10	As Welded						
Si: 0.60	550	650	21	20°C: 80			
Mn: 0.50	After Heat Treatment (620°C 2 Hour)				I1 (%100 Ar)	1.60 x 1000	5.00 kg - Cardboard / Plastic
Cr: 1.40	540	600	22	20°C: 100		2.00 x 1000	
Mo: 0.50						2.40 x 1000	
C: 0.08	As Welded						
Si: 0.60	560	650	22	20°C: 100			
Mn: 0.90	After Heat Treatment (720°C 1 Hour)				I1 (%100 Ar)	2.00 x 1000	5.00 kg - Cardboard / Plastic
Cr: 2.45	550	640	23	20°C: 110		2.40 x 1000	
Mo: 1.00						3.20 x 1000	
C: 0.10	As Welded						
Si: 0.50	After Heat Treatment (690°C 2 Hour)						
Mn: 0.50	560	650	22	20°C: 110	I1 (%100 Ar)	1.60 x 1000	5.00 kg - Cardboard / Plastic
Cr: 2.50						2.00 x 1000	
Mo: 1.00						2.40 x 1000	
						3.20 x 1000	

GAS ARC TUNGSTEN (TIG) AND OXY-ACETYLENE WELDING RODS

Low-Alloyed, High Strength and Creep Resistant Steel Welding TIG Rods

Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>TG 235</p> <p>AWS/ASME SFA - 5.28 ER80S-B6 EN ISO 21952 - A W CrMo5Si TS EN ISO 21952 - A W CrMo5Si DIN M. No. 1.7373</p>	<p>Medium-alloyed GTA (TIG) welding rod for Cr-Mo alloyed creep resisting steels, subjected to operating temperatures up to 650°C. Suitable for welding 12 CrMo19-5, P5 / T5 steels in power generation and petrochemical industries. Due to its high steam and hot hydrogen corrosion resistance, particularly used in root and cap passes of in steam generators, boilers, piping in refineries, where high X-ray quality is required. Observe directions of pre- and post-weld heat treatment of base metal.</p>	 
<p>TG 285</p> <p>AWS/ASME SFA - 5.28 ER80S-B8 EN ISO 21952 - A W CrMo9 TS EN ISO 21952 - A W CrMo9</p>	<p>9Cr- 1Mo alloyed GTA (TIG) welding rod for creep resisting steels, subjected to operating temperatures up to 600°C. Suitable for welding P9 / T9 steels in power generation and petrochemical industries. Due to its high steam and hot hydrogen corrosion resistance, particularly used in root and cap passes of in steam generators, boilers, pressure vessels and piping in refineries, where high X-ray quality is required. Observe directions of pre- and post-weld heat treatment of base metal.</p>	 
<p>TG 295</p> <p>AWS/ASME SFA - 5.28 ER90S-B9 EN ISO 21952 - A W CrMo91 TS EN ISO 21952 - A W CrMo91 DIN M. No. 1.4903</p>	<p>High-alloyed, GTA (TIG) welding rod for creep, oxidation and corrosion resistant Cr-Mo-V-Nb alloyed steels, subjected to operating temperatures in 650°C. Suitable for welding P91 and T91 steels used in steam generators, turbine rotors, boiler, piping in refineries, chemical industry and thermal power generation industry. Due to its high steam and hot hydrogen corrosion resistance, particularly used in root and cap passes of in steam generators, boilers, pressure vessels and piping in refineries, where high X-ray quality is required. Observe directions of pre- and post-weld heat treatment of base metal.</p>	 

Typical Chemical Analysis of Welding Rod (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Shielding Gas	Dimension (mm)	Packing Weigth (kg) Box Type
C: 0.10	As Welded						
Si: 0.40	580	660	23	20°C: 80			
Mn: 0.50	After Heat Treatment (740°C 2 Hour)				I1 (%100 Ar)	2.00 x 1000 2.40 x 1000	5.00 kg - Cardboard / Plastic
Cr: 6.00	570	650	24	20°C: 100			
Mo: 0.55							
C: 0.08	After Heat Treatment (740°C 2 Hour)						
Si: 0.40							
Mn: 0.60	610	700	20	20°C: 110	I1 (%100 Ar)	2.00 x 1000 2.40 x 1000	5.00 kg - Cardboard / Plastic
Cr: 9.00							
Ni: 0.20							
Mo: 1.00							
C: 0.10	After Heat Treatment (760°C 2 Hour)						
Si: 0.30							
Mn: 0.50							
Cr: 9.20	650	750	19	20°C: 100	I1 (%100 Ar)	2.00 x 1000 2.40 x 1000 3.20 x 1000	5.00 kg - Cardboard / Plastic
Ni: 0.65							
Mo: 0.95							
Cu: 0.02							
Nb: 0.05							
V: 0.20							

GAS ARC TUNGSTEN (TIG) AND OXY-ACETYLENE WELDING RODS

Stainless Steel TIG Welding Rods

Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>TI 307Si</p> <p>AWS/ASME SFA - 5.9 ~ER307 EN ISO 14343 - A W 18 8 Mn TS EN ISO 14343 - A W 18 8 Mn DIN M. No. 1.4370</p>	<p>Austenitic stainless steel wire rod for GTA (TIG) welding of dissimilar steels, difficult to weld steels, armour plates, high manganese steels, rails, crossovers. Suitable also for depositing stress relaxing buffer layers on crack sensitive base metals and hard surfacing jobs, e.g. crane wheels, cutting blades and dies where high degree of pressure and dynamical loads exists. Weld metal has a high degree of corrosion resistance and resistant to operating temperatures up to 300°C and non-scaling up to 850°C. Depending on chemical composition of base metal, proper welding procedure, preheating and interpass temperatures shall be applied by also avoiding high admixture of base metal.</p>	 
<p>TI 308L</p> <p>AWS/ASME SFA - 5.9 ER308L EN ISO 14343 - A W 19 9 L TS EN ISO 14343 - A W 19 9 L DIN M. No. 1.4316</p>	<p>Austenitic stainless steel welding rod for GTA (TIG) welding of unstabilized or stabilized corrosion resisting Cr-Ni steels. Used in tank, pipe, equipment welding in food, beverage, chemical and pharmaceutical industries. Resistant to intergranular corrosion up to 350°C. Non-scaling up to 800°C, in air or oxidizing combustion gases.</p>	 
<p>TI 308LSi</p> <p>AWS/ASME SFA - 5.9 ER308LSi EN ISO 14343 - A W 19 9 LSi TS EN ISO 14343 - A W 19 9 LSi</p>	<p>Austenitic stainless steel welding rod for GTA (TIG) welding of unstabilized or stabilized corrosion resisting Cr-Ni steels. Used in tank, pipe, equipment welding in food, beverage, chemical and pharmaceutical industries. Therefore, the increased Silicon (Si) promotes weld pool fluidity and smoother weld bead appearance. Resistant to intergranular corrosion up to 350°C. Non-scaling up to 800°C, in air or oxidizing combustion gases.</p>	 
<p>TI 309L</p> <p>AWS/ASME SFA - 5.9 ER309L EN ISO 14343 - A W 23 12 L TS EN ISO 14343 - A W 23 12 L DIN M. No. 1.4332</p>	<p>Austenitic-ferritic wire electrode for GTA (TIG)-welding of stainless steels to unalloyed or low-alloyed steels, subject to operating temperatures up to 300°C. Low carbon content increases resistance to intergranular corrosion. Suitable to use also as buffer layer on carbon steel before welding with 308 and 308 L to reach 304 and 304L surface layer.</p>	 
<p>TI 309LSi</p> <p>AWS/ASME SFA - 5.9 ER309LSi EN ISO 14343 - A W 23 12 LSi TS EN ISO 14343 - A W 23 12 LSi DIN M. No. 1.4332</p>	<p>Austenitic-ferritic wire electrode for GTA (TIG)-welding of stainless steels to unalloyed or low-alloyed steels, subject to operating temperatures up to 300°C. Low carbon content increases resistance to intergranular corrosion. Suitable to use also as buffer layer on carbon steel before welding with 308 and 308 L to reach 304 and 304L surface layer. The higher silicon content improves the welding properties, such as wetting and smoother weld bead appearance.</p>	 

Typical Chemical Analysis of Welding Rod (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Shielding Gas	Dimension (mm)	Packing Weigth (kg) Box Type
C: 0.07							
Si: 0.80							
Mn: 7.00	470	630	42	20°C: 150 -60°C: 100	I1 (%100 Ar)	2.40 x 1000	5.00 kg - Cardboard / Plastic
Cr: 18.00							
Ni: 8.00							
C: 0.02							
Si: 0.45							
Mn: 1.80	460	620	39	20°C: 195 -196°C: 50	I1 (%100 Ar)	1.20 x 1000 1.60 x 1000 2.00 x 1000 2.40 x 1000 3.20 x 1000	5.00 kg - Cardboard / Plastic
Cr: 19.75							
Ni: 10.50							
C: 0.02							
Si: 0.80							
Mn: 1.80	420	560	36	20°C: 195 -196°C: 50	I1 (%100 Ar)	1.60 x 1000 2.00 x 1000 2.40 x 1000 3.20 x 1000	5.00 kg - Cardboard / Plastic
Cr: 19.75							
Ni: 10.50							
C: 0.02							
Si: 0.35							
Mn: 1.75	550	670	30	-30°C: 90 -196°C: 62	I1 (%100 Ar)	1.60 x 1000 2.00 x 1000 2.40 x 1000 3.20 x 1000	5.00 kg - Cardboard / Plastic
Cr: 23.50							
Ni: 13.50							
C: 0.02							
Si: 0.80							
Mn: 1.75	440	575	35	-30°C: 90 -196°C: 62	I1 (%100 Ar)	2.40 x 1000	5.00 kg - Cardboard / Plastic
Cr: 23.50							
Ni: 13.50							

GAS ARC TUNGSTEN (TIG) AND OXY-ACETYLENE WELDING RODS







Stainless Steel TIG Welding Rods

Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>TI 310</p> <p>AWS/ASME SFA - 5.9 ER310 EN ISO 14343 - A W 25 20 TS EN ISO 14343 - A W 25 20 DIN M. No. 1.4842</p>	<p>Fully austenitic welding rod for GTA (TIG) welding of heat resisting steels containing approximately 25% chromium and 20% nickel which are used in heat treatment and industrial furnaces and equipments, like cement and steel industries. Also suited for welding heat resisting and non-scaling ferritic chromium steels, provided that corrosion attack by reducing sulphur bearing combustion gases is not to be expected. Non-scaling up to 1200°C. Weld metal exhibits good toughness values down to -196°C.</p>	 
<p>TI 312</p> <p>AWS/ASME SFA - 5.9 ER312 EN ISO 14343 - A W 29 9 TS EN ISO 14343 - A W 29 9 DIN M. No. 1.4337</p>	<p>Austenitic-ferritic stainless steel wire electrode for TIG welding of dissimilar steels and depositing buffer layers on ferritic steels. It features high resistance to cracking and toughness, is therefore suited for joining difficult to weld steels and depositing stress-relaxing buffer layers on crack sensitive base metals. Weld metal is non-scaling up to 1100°C. Especially used in die and tool repair, crack repairs in difficult to weld steels, gear teeth repair and rebuilding, buffer layer application on cutting blades. Suitable also for welding galvanized steel plates.</p>	 
<p>TI 316L</p> <p>AWS/ASME SFA - 5.9 ER316L EN ISO 14343 - A W 19 12 3 L TS EN ISO 14343 - A W 19 12 3 L DIN M. No. 1.4430</p>	<p>Austenitic stainless steel welding rod for GTA (TIG) welding of unstabilized or stabilized high corrosion resisting Cr-Ni-Mo stainless steels. Due to its low C (carbon) content, resistant to intergranular corrosion up to 400°C. Especially used in welding chemical tanks, pipes and equipments which are used in chemical, petrochemical, paint, paper and shipbuilding industries, etc.</p>	 
<p>TI 316LSi</p> <p>AWS/ASME SFA - 5.9 ER316LSi EN ISO 14343 - A W 19 12 3 L Si TS EN ISO 14343 - A W 19 12 3 L Si</p>	<p>Austenitic stainless steel welding rod for GTA (TIG) welding of unstabilized or stabilized high corrosion resisting Cr-Ni-Mo stainless steels. Due to its low C (carbon) content, resistant to intergranular corrosion up to 400°C. Especially used in welding chemical tanks, pipes and equipments which are used in chemical, petrochemical, paint, paper and shipbuilding industries, etc. The higher silicon content improves the welding properties, such as wetting and smoother weld bead appearance.</p>	 
<p>TI 318</p> <p>AWS/ASME SFA - 5.9 ER318 EN ISO 14343 - A W 19 12 3 Nb TS EN ISO 14343 - A W 19 12 3 Nb DIN M. No. 1.4576</p>	<p>Austenitic stainless steel welding rod for GTA (TIG) welding of unstabilized or stabilized corrosion resisting Cr-Ni-Mo steels. Stabilized with Nb (Niobium) and resistant to intergranular corrosion up to 400°C. Especially used in welding of chemical tanks, pipes and equipments which are used in chemical, petrochemical, paper, paint, shipbuilding industries.</p>	 

Typical Chemical Analysis of Welding Rod (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Shielding Gas	Dimension (mm)	Packing Weigth (kg) Box Type
C: 0.10	450	580	36	20°C: 150 -60°C: 100	I1 (%100 Ar)	1.20 x 1000 1.60 x 1000 2.00 x 1000 2.40 x 1000 3.20 x 1000	5.00 kg - Cardboard / Plastic
Si: 0.40							
Mn: 1.60							
Cr: 26.00							
Ni: 21.00							
C: 0.10	700	770	21	20°C: 60	I1 (%100 Ar)	2.00 x 1000 2.40 x 1000	5.00 kg - Cardboard / Plastic
Si: 0.40							
Mn: 1.80							
Cr: 30.00							
Ni: 9.00							
C: 0.02	510	630	35	-20°C: 120 -196°C: 90	I1 (%100 Ar)	1.20 x 1000 1.60 x 1000 2.00 x 1000 2.40 x 1000 3.20 x 1000	5.00 kg - Cardboard / Plastic
Si: 0.35							
Mn: 1.75							
Cr: 18.50							
Ni: 11.50							
Mo: 2.75							
C: 0.02	400	550	37	-20°C: 120 -196°C: 90	I1 (%100 Ar)	1.60 x 1000 2.00 x 1000 2.40 x 1000 3.20 x 1000	5.00 kg - Cardboard / Plastic
Si: 0.80							
Mn: 1.75							
Cr: 18.50							
Ni: 11.50							
Mo: 2.75							
C: 0.04	480	640	32	20°C: 130	I1 (%100 Ar)	1.20 x 1000 1.60 x 1000 2.00 x 1000 2.40 x 1000 3.20 x 1000	5.00 kg - Cardboard / Plastic
Si: 0.40							
Mn: 1.70							
Cr: 19.50							
Ni: 11.50							
Mo: 2.60							
Nb: 0.70							

GAS ARC TUNGSTEN (TIG) AND OXY-ACETYLENE WELDING RODS







Stainless Steel TIG Welding Rods

Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>TI 347</p> <p>AWS/ASME SFA - 5.9 ER347 EN ISO 14343 - A W 19 9 Nb TS EN ISO 14343 - A W 19 9 Nb DIN M. No. 1.4551</p>	<p>Stabilized austenitic stainless steel welding rod for GTA (TIG) welding of unstabilized and stabilized corrosion resisting Cr-Ni steels. Generally used for welding pipes, tanks and equipments in food, beverage, chemical and pharmaceutical industries. Stabilized with Nb (Niobium) and resistant to intergranular corrosion. Weld metal is suitable for operating temperatures of up to 400°C, non-scaling up to 800°C, in air and oxidizing combustion gases.</p>	 
<p>TI 385</p> <p>AWS/ASME SFA - 5.9 ER385 EN ISO 14343 - A W 20 25 5 Cu L TS EN ISO 14343 - A W 20 25 5 Cu L DIN M. No. ~1.4539</p>	<p>Fully-austenitic stainless steel rod for GTA (TIG)-welding of unstabilized or stabilized corrosion resisting Cr-Ni-Mo alloyed stainless steels like 904L/1.4539. Especially used in flue gas desulphurization plants, fertilizer plants, sea water transfer fittings, petrochemical, paper and pulp industries, etc. Due to high Ni, Mo and low C content, weld metal have high resistant to intergranular, pitting, crevice and stress corrosion types in chloride containing solutions, phosphorus-, sulphur-, acetic-, formic acids, sea water.</p>	 
<p>TI 410</p> <p>AWS/ASME SFA - 5.9 ER410 EN ISO 14343 - A W 13 TS EN ISO 14343 - A W 13 DIN M. No. ~1.4009</p>	<p>Martensitic stainless steel rod for GTA (TIG) welding of martensitic stainless steels, heat resistant steels and cast steels which contain approx. 13% chromium. Suitable for joining and surfacing of gas, water and steam fan, fan blades and fittings subjected corrosion, erosion and operating temperatures up to 450°C. Depending on type of base metal composition and thickness, preheating between 200 and 300°C, keeping the interpass temperature during welding and tempering between 700 and 750°C after welding are advisable.</p>	 

Typical Chemical Analysis of Welding Rod (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Shielding Gas	Dimension (mm)	Packing Weigth (kg) Box Type
C: 0.04	460	650	36	-20°C: 70	I1 (%100 Ar)	1.60 x 1000 2.00 x 1000 2.40 x 1000 3.20 x 1000	5.00 kg - Cardboard / Plastic
Si: 0.35							
Mn: 1.35							
Cr: 19.50							
Ni: 9.50							
Nb: 0.60							
C: 0.01	440	580	32	-196°C: 170	I1 (%100 Ar)	2.00 x 1000 2.40 x 1000	5.00 kg - Cardboard / Plastic
Si: 0.40							
Mn: 1.80							
Cr: 20.00							
Ni: 25.00							
Mo: 4.50							
Cu: 1.50							
C: 0.12	As Welded			0°C: 170	I1 (%100 Ar)	1.60 x 1000 2.40 x 1000	5.00 kg - Cardboard / Plastic
Si: 0.45	450	600	20				
Mn: 0.50	After Heat Treatment (760°C 1 Hour)			0°C: 180 -20°C: 100			
Cr: 12.50	530	660	23				

GAS ARC TUNGSTEN (TIG) AND OXY-ACETYLENE WELDING RODS











Stainless Steel TIG Welding Rods

Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>TI 630</p> <p>AWS/ASME SFA - 5.9 ER630 EN ISO 14343 - B SS630 TS EN ISO 14343 - B SS630 DIN M. No. 1.4542</p>	<p>GTA (TIG) welding rod for welding of 17Cr/4 Ni containing, 630 (1.4542) and similar precipitation hardening-martensitic stainless steels. Especially used in hydraulic equipment components, impellers, pump shafts, valves which are exposed to high corrosion in petrochemical industry, chemical plants. In order to gain precipitation hardening martensitic steel properties of the weld metal after welding, solution heat treatment shall be done at 1052°C (±28°C) to have austenite matrix, then quenching to 149-93°C to transform the matrix to martensite and then precipitation/aging heat treatment at 482-621°C for 4 hours. After precipitation hardening heat treatment, weld metal has very high mechanical strength and high toughness, as well as very good corrosion and oxidation resistance.</p>	 
<p>TI 2209</p> <p>AWS/ASME SFA - 5.9 ER2209 EN ISO 14343 - A W 22 9 3 N L TS EN ISO 14343 - A W 22 9 3 N L DIN M. No. ~1.4462</p>	<p>Dublex (ferritic-austenitic) stainless steel welding rod for GTA (TIG) welding of dublex Cr-Ni-Mo stainless steels. Especially used in welding of acid tanks and pipes, in chemical, petrochemical, paper, shipbuilding and desalination industries. Suitable also for welding dublex stainless steels to carbon steels. The high-strength and ductile weld metal exhibits good resistance to pitting, crevice corrosion and stress corrosion cracking in chloride-bearing media. Suitable for operating temperatures of up to 250°C.</p>	 
<p>TI 2594</p> <p>AWS/ASME SFA - 5.9 ER2594 EN ISO 14343 - A W 25 9 4 N L TS EN ISO 14343 - A W 25 9 4 N L DIN M. No. ~1.4417</p>	<p>Super dublex (ferritic-austenitic) stainless steel GTA (TIG) welding rod for welding Cr-Ni-Mo containing super dublex (ferritic-austenitic) stainless steels. Suitable for welding acid tanks and piping in chemical, petrochemical, paper, shipbuilding, sea water desalination industries and offshore platforms. It is also suitable for root pass welding of 22%Cr containing dublex stainless steels and joining of 13%Cr containing martensitic steels. Weld metal with high mechanical strength with high ductility and also generally has also high stress corrosion resistance, especially in chloride containing media. PREN:40 value provides high resistance to pitting corrosion.</p>	 

Typical Chemical Analysis of Welding Rod (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Shielding Gas	Dimension (mm)	Packing Weigth (kg) Box Type
C: 0.02							
Si: 0.40							
Mn: 0.40	After Heat Treatment (1050°C 1 Hour)						
Cr: 16.25	980	1020	17	0°C: 100 -20°C: 70	I1 (%100 Ar)	2.00 x 1000 2.40 x 1000	5.00 kg - Cardboard / Plastic
Ni: 4.70							
Cu: 3.40							
Nb: 0.22							
C: 0.01							
Si: 0.45							
Mn: 1.45							
Cr: 23.00	640	810	20	20°C: 150 -40°C: 120 -60°C: 100	I1 (%100 Ar)	1.60 x 1000 2.00 x 1000 2.40 x 1000	5.00 kg - Cardboard / Plastic
Ni: 8.50							
Mo: 3.25							
N: 0.15							
C: 0.02							
Si: 0.40							
Mn: 0.60							
Cr: 25.00	690	850	28	-40°C: 200	I1 (%100 Ar)	1.60 x 1000 2.00 x 1000 2.40 x 1000	5.00 kg - Cardboard / Plastic
Ni: 9.20							
Mo: 4.00							
N: 0.25							

GAS ARC TUNGSTEN (TIG) AND OXY-ACETYLENE WELDING RODS





Aluminium Alloy TIG Welding Rods

Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>TAL 1100</p> <p>AWS/ASME SFA - 5.10 ER1070 AWS/ASME SFA - 5.10 ~ER1100 EN ISO 18273 S AI 1070 (Al99.7) TS 6204 EN ISO 18273 S AI 1070 (Al99.7) DIN M. No. 3.0259</p>	<p>Pure aluminium GTA(TIG) welding of unalloyed aluminium base metals. It has got good colour matching with the aluminium base metals. High corrosion resistance and excellent electrical conductivity.</p>	 
<p>TAL 4043</p> <p>AWS/ASME SFA - 5.10 ER4043 EN ISO 18273 S AI 4043 (AlSi5) TS EN ISO 18273 S AI 4043 (AlSi5) DIN M. No. 3.2245</p>	<p>5% Silicon containing aluminium welding rod for GTA (TIG) welding of aluminium and aluminium alloys. Suitable for welding aluminium castings containing up to 7% silicon and Al-Mg-Si alloys which are containing up to 2 % Magnesium as alloying elements.</p>	 
<p>TAL 4047</p> <p>AWS/ASME SFA - 5.10 ER4047 EN ISO 18273 S AI 4047A (AlSi12(A)) TS EN ISO 18273 S AI 4047A (AlSi12(A)) DIN M. No. 3.2585</p>	<p>Aluminium-Silicon alloy filler metal used both for brazing and GTA (TIG) welding of aluminium alloys. Suitable for welding Al-Si and Al-Si-Mg cast aluminium alloys, having silicon content of > 7%. Very good capillary flow in brazing and brazed joints are matching structure and colour of aluminium alloys. Suitable for brazing of rolled and cast aluminium alloys. Excess acetylene flame has to be used during brazing. Widely used in production of kettle, frier, solar heaters. Used in combination with BF14 flux in brazing applications.</p>	 
<p>TAL 5183</p> <p>AWS/ASME SFA - 5.10 ER5183 EN ISO 18273 S AI 5183 (AlMg4.5Mn0.7(A)) TS EN ISO 18273 S AI 5183 (AlMg4.5Mn0.7(A)) DIN M. No. 3.3548</p>	<p>5% Mg (Magnesium) and Mn (Manganese) containing aluminium alloy welding rod for GTA (TIG) welding of Al-alloys with high tensile strength requirements. Suitable for welding Al-Mg alloys and Al-Mg-Mn alloys.</p>	 
<p>TAL 5356</p> <p>AWS/ASME SFA - 5.10 ER5356 EN ISO 18273 S AI 5356 (AlMg5Cr(A)) TS EN ISO 18273 S AI 5356 (AlMg5Cr(A)) DIN M. No. 3.3556</p>	<p>5% Mg (Magnesium) containing aluminium welding rod for GTA (TIG) welding of Al-Mg (Aluminium- Magnesium) alloys and Al-Mg-Si (Aluminium-Magnesium-Silicon) alloys. Gives colour match with base metal after anodizing process. Has excellent ductility and very good corrosion resistance especially in sea water.</p>	 



Typical Chemical Analysis of Welding Rod (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Shielding Gas	Dimension (mm)	Packing Weigth (kg) Box Type
Al: 99.50	50	70	35	-	I1 (%100 Ar)	1.60 x 1000 2.00 x 1000 2.40 x 1000	2.50 kg - Cardboard / Plastic
Si: 5.00							
Mn: 0.05	80	150	12	-	I1 (%100 Ar)	1.60 x 1000 2.00 x 1000 2.40 x 1000 3.20 x 1000 4.00 x 1000	2.50 kg - Cardboard / Plastic
Al: 94.95							
Si: 12.00							
	80	170	5	-	I1 (%100 Ar)	2.00 x 1000 2.40 x 1000 3.20 x 1000	2.50 kg - Cardboard / Plastic
Al: 88.00							
Mg: 4.75							
Mn: 0.60	130	260	17	-	I1 (%100 Ar)	2.00 x 1000 2.40 x 1000 3.20 x 1000	2.50 kg - Cardboard / Plastic
Ti: 0.10							
Al: 94.55							
Mg: 4.75							
Cr: 0.10	120	270	28	-	I1 (%100 Ar)	1.60 x 1000 2.00 x 1000 2.40 x 1000 3.20 x 1000 4.00 x 1000	2.50 kg - Cardboard / Plastic
Al: 95.15							

GAS ARC TUNGSTEN (TIG) AND OXY-ACETYLENE WELDING RODS

Nickel Alloy TIG Welding Rods

Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>TNI 422</p> <p>AWS/ASME SFA-5.14 EN ISO 18274-A TS EN ISO 18274-A DIN M. No.</p> <p>ERNiCr-3 SNI 6082 SNI 6082 2.4806</p>	<p>Ni-Cr-Fe alloyed GTA (TIG) welding rod, depositing Ni-20Cr3Mn2,5Nb weld metal. Especially used for welding of highly creep resistant, heat and corrosion resistant Ni-Cr alloys, like Incoloy 800, 5-9% Ni containing steels, cryogenic stainless steels down to -196°C. Also suitable for joining dissimilar materials as stainless steels to low alloyed steels, stainless steels to nickel alloys, buffering of difficult to weld steels cladding on steels and repair welds of them. Weld metal deposit is insensitive to cracks, has very good resistance to acids, salts and alkaline solutions, molten salt (e.g. cyanide) in oxidizing and carburization atmospheres. In sulphurous atmospheres the weld metal can be used up to 500°C. Generally used for welding on LPG and LNG processing and storing plants, oven parts, burners, heat treatment equipment, cement works, moulds, transport and storage tanks of liquid gases in chemical, petrochemical industries, glassworks, civil engineering, repairing and maintenance workshops.</p>	 
<p>TNI 425</p> <p>AWS/ASME SFA-5.14 EN ISO 18274-A TS EN ISO 18274-A DIN M. No.</p> <p>ERNiCrMo-3 SNI 6625 (NiCr22Mo9Nb) SNI 6625 (NiCr22Mo9Nb) 2.4831</p>	<p>Ni-Cr-Mo alloyed GTA (TIG) welding rod, depositing Ni-22Cr9Mo3,5Nb weld metal. TNI 425 is used for welding of highly corrosion resistant Ni-Cr-Mo alloys, like Alloy 625, 825 and similar alloys. Due to its good cryogenic toughness down to -196°C, preferred for welding of cryogenic nickel alloys, e.g. X1NiCrMoCuN25-20-7. In sulphur free atmospheres the weld metal is non-scaling 1200°C, in sulphurous atmospheres the weld metal can be used in service temperatures up to 500°C. It is also highly resistant stress corrosion cracking and pitting corrosion in phosphoric acid, organic acids, sea water and polluting environments. Weld metal is insensitive to cracking and very resistant to thermal shocks. Used for joining of dissimilar nickel alloys, joining dissimilar stainless steels, low alloyed steels to stainless steels or to nickel alloys, buffering of difficult to weld steels and repair welding of them.</p>	 

Copper Alloy TIG Welding Rods










Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>TCU AI8</p> <p>AWS/ASME SFA - 5.07 EN ISO 24373 TS EN ISO 24373 DIN M. No.</p> <p>ERCuAl-A1 S Cu 6100 (CuAl7) S Cu 6100 (CuAl7) 2.0921</p>	<p>Aluminium bronze welding rod for GTA (TIG) welding of aluminium bronzes, high strength brass and surfacing of steel, gray cast iron used in machine building and in the chemical industry, as well as in shipbuilding. Alloy showing resistance to corrosion and erosion to sea water, with a very good metal to metal sliding properties. Suitable for also welding joints on corrosion resistant aluminium bronze or high strength brass pipes. Joining copper tubing to steel. Surface build-up on ship propellers, skid rails, bearing surfaces, bearings, valves, slide gates, fittings.</p>	 

Typical Chemical Analysis of Welding Rod (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Shielding Gas	Dimension (mm)	Packing Weigth (kg) Box Type
C: 0.03	500	700	40	20°C: 170 -196°C: 160	I1 (%100 Ar)	1.60 x 1000 2.40 x 1000	5.00 kg - Cardboard / Plastic
Si: 0.10							
Mn: 3.00							
Cr: 20.00							
Ni: 72.50							
Nb: 2.40							
Ti: 0.30							
Fe: 1.30							
C: 0.01	570	760	39	20°C: 135 -196°C: 130	I1 (%100 Ar)	1.60 x 1000 2.40 x 1000	5.00 kg - Cardboard / Plastic
Si: 0.04							
Mn: 0.02							
Cr: 22.25							
Ni: 65.00							
Mo: 8.70							
Nb: 3.70							
Ti: 0.20							
Fe: 0.30							

Typical Chemical Analysis of Welding Rod (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Shielding Gas	Dimension (mm)	Packing Weigth (kg) Box Type
Mn: 0.20	Hardness: 100 HB			20°C: 135 -196°C: 130	I1 (%100 Ar)	2.40 x 1000 3.20 x 1000	5.00 kg - Cardboard / Plastic
Ni: 0.30	200	430	40				
Cu: 91.50							
Al: 8.00							

GAS ARC TUNGSTEN (TIG) AND OXY-ACETYLENE WELDING RODS

Hardfacing TIG Rods

Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>TH 801</p> <p>AWS/ASME SFA - 5.21 EN 14700 TS EN 14700 DIN 8555</p> <p>ERCoCr-C T Co3 T Co3 WSG 20-G0-55-CSTZ</p>	<p>Co-Cr-W alloy GTA (TIG) welding rod for hardfacing applications. Weld metal has got high resistance to metal-to-metal wear, corrosion and high temperatures from 500°C to 900°C. Resistant to low and medium level of mechanical and thermal shocks, due to its high hardness. Widely used for hardfacing of wire guides, rolling mill guides, extrusion dies and screws, valve seats, mechanical parts of steam turbines, cement screws, continuous casting dies and parts, pump tubing and shafts, mixes blades, wood saws.</p>	 
<p>TH 806</p> <p>AWS/ASME SFA - 5.21 EN 14700 TS EN 14700 DIN 8555</p> <p>ERCoCr-A T Co2 T Co2 WSG 20-G0-40-CTZ</p>	<p>Co-Cr-W alloy GTA (TIG) welding rod for hardfacing applications. Weld metal has got high resistance to metal-to-metal wear, corrosion and high temperatures from 500°C to 900°C. Due to weld metal toughness, it is resistant to mechanical and thermal shocks. Widely used for hardfacing of hot shearing blades, ingot tong ends, valves and valve seats, nozzles and glass dies.</p>	 
<p>TH 812</p> <p>AWS/ASME SFA - 5.21 EN 14700 TS EN 14700 DIN 8555</p> <p>ERCoCr-B T Co3 T Co3 WSG 20-G0-45-CTZ</p>	<p>Co-Cr-W alloy TIG welding rod for hardfacing applications. Weld metal has got high resistance to metal-to-metal wear, corrosion and high temperatures from 500°C to 900°C. Due to weld metal toughness, it is resistant to mechanical and thermal shocks. Widely used for hardfacing of tools for cutting and machining of paper, cardboard, floor coverings, roofing and wood, extrusion screws, glass dies.</p>	 
<p>T CARBIDE 3000</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>T Ni20 T Ni20 G21 UM-55-CG</p>	<p>Flexible rod for hardfacing by oxy-gas welding. Consist of a small diameter pure nickel core wire thickly coated tungsten carbides in a Ni-Cr-B-Si matrix. The weld metal is a heterogeneous metal composed of tungsten carbides (W₂C, WC) distributed in a hard and tough matrix. Shows extremely high abrasion resistance. It has got a quiet melting and good wetting. Especially used for hardfacing of mixers, crushing mills, die blades and heads, sand foundary equipment, drilling tricones.</p>	   <p>If required 1 Hour</p>

Typical Chemical Analysis of Welding Rod (%)	Hardness (HRc)	Shielding Gas	Dimension (mm)	Packing Weigth (kg) Box Type
C: 2.30	55	I1 (%100 Ar)	3.20 x 1000 5.00 x 1000	5.00 kg - Cardboard
Si: 1.00				
Mn: 0.50				
Cr: 30.00				
Ni: 2.20				
Fe: 2.50				
W: 12.50				
Co: 49.00				
C: 1.00	40	I1 (%100 Ar)	3.20 x 1000 4.00 x 1000 5.00 x 1000	5.00 kg - Cardboard
Si: 1.00				
Mn: 0.50				
Cr: 28.00				
Ni: 2.00				
Fe: 2.50				
W: 5.00				
Co: 60.00				
C: 1.40	45	I1 (%100 Ar)	3.20 x 1000 4.00 x 1000 5.00 x 1000	5.00 kg - Cardboard
Si: 1.00				
Mn: 0.10				
Cr: 30.00				
Ni: 2.00				
Fe: 2.50				
W: 8.00				
Co: 55.00				
C: 2.50	Matrix: 40-45 HRc SFTC: 3000 HV	I1 (%100 Ar)	5.00 x 450	2.50 kg - Cardboard
Si: 1.30				
Cr: 2.60				
Ni: 33.00				
B: 0.60				
W: 60.00				

GAS METAL ARC (MIG/MAG) WELDING WIRES

CONTENTS

GAS METAL ARC (MIG/MAG) WELDING WIRES

Unalloyed Steel MIG/MAG Welding Wires

Product Name	AWS / ASME SFA - 5.18	EN ISO 14341-A	TS EN ISO 14341-A	Page Number
MG 1	ER70S-3	G 38 3 C1 2Si G 38 3 M21 2Si	G 38 3 M21 2Si G 38 3 C1 2Si	83
MG 2	ER70S-6	G 42 3 C1 3Si1 G 42 4 M21 3Si1	G 42 3 C1 3Si1 G 42 4 M21 3Si1	83
MG 3	ER70S-6	G 46 4 C1 4Si1 G 46 4 M21 4Si1	G 46 4 C1 4Si1 G 46 4 M21 4Si1	83
MG 20	ER70S-6	G 42 3 C1 3Si1 G 42 4 M21 3Si1	G 42 3 C1 3Si1 G 42 4 M21 3Si1	83
MG 30	ER70S-6	G 46 4 C1 4Si1 G 46 4 M21 4Si1	G 46 4 C1 4Si1 G 46 4 M21 4Si1	83
MG 102	ER70S-2	G 42 3 C1 2Ti G 42 3 M21 2Ti	G 42 3 C1 2Ti G 42 3 M21 2Ti	83

Low-Alloyed, High Strength and Creep Resistant Steel MIG/MAG Welding Wires

Product Name	AWS / ASME SFA - 5.18	EN ISO 14341-A	TS EN ISO 14341-A	Page Number
MG 150	ER80S-Ni1	G 50 6 M21 3Ni1	G 50 6 M21 3Ni1	85
MG 150W	ER80S-G	G 42 2 M21 Z2NiCu	G 42 2 M21 Z2NiCu	85
MG 182	ER110S-G	G 69 6 M21 Mn4Ni1,5CrMo	G 69 6 M21 Mn4Ni1,5CrMo	85
MG 183	ER110S-G ER100S-G	G 69 4 M21 Mn3Ni1CrMo	G 69 4 M21 Mn3Ni1CrMo	87
MG 192	ER120S-G	G 89 6 M21 Mn4Ni2CrMo	G 89 6 M21 Mn4Ni2CrMo	87
MG 201	ER70S-A1 ER80S-G	G MoSi	G MoSi	87
MG 201A	ER80S-D2	G Z MnMo	G Z MnMo	87
MG 211	ER80S-G	G CrMo1Si	G CrMo1Si	87
MG 211A	ER80S-B2	G Z CrMo1Si	G Z CrMo1Si	89
MG 222	ER90S-G ~ER90S-B3	G CrMo2Si	G CrMo2Si	89

Stainless Steel MIG Welding Wires

Product Name	AWS / ASME SFA - 5.9	EN ISO 14343-A	TS EN ISO 14343-A	Page Number
MI 307Si	~ER307	G 18 8 Mn	G 18 8 Mn	87
MI 308LSi	ER308LSi	G 19 9 LSi	G 19 9 LSi	87
MI 309LSi	ER309LSi	G 23 12 LSi	G 23 12 LSi	89
MI 310	ER310	G 25 20	G 25 20	89
MI 312	ER312	G 29 9	G 29 9	89
MI 316LSi	ER316LSi	G 19 12 3 LSi	G 19 12 3 LSi	89
MI 347	ER347	G 19 9 Nb	G 19 9 Nb	89
MI 385	ER 385	G 20 25 5 Cu L	G 20 25 5 Cu L	91
MI 410	ER 410	G 13	G 13	91
MI 2209	ER2209	G 22 9 3 N L	G 22 9 3 N L	91

GAS METAL ARC (MIG/MAG) WELDING WIRES

Aluminium Alloy MIG Welding Wires

Product Name	AWS / ASME SFA - 5.10	EN ISO 18273-A	TS EN ISO 18273-A	Page Number
MAL 1100	ER1070 / ~ER1100	S Al 1070 (Al99.7)	S Al 1070 (Al99.7)	95
MAL 4043	ER4043	S Al 4043 (AlSi5)	S Al 4043 (AlSi5)	95
MAL 4047	ER4047	S Al 4047A (AlSi12(A))	S Al 4047A (AlSi12(A))	95
MAL 5183	ER5183	S Al 5183 (AlMg4.5Mn0.7(A))	S Al 5183 (AlMg4.5Mn0.7(A))	95
MAL 5356	ER5356	S Al 5356 (AlMg5Cr(A))	S Al 5356 (AlMg5Cr(A))	95
MAL 5556	ER5556	S Al 5556 (AlMg5Mn1Ti(A))	S Al 5556 (AlMg5Mn1Ti(A))	97

Copper Alloy MIG Welding Wires

Product Name	AWS / ASME SFA - 5.7	EN ISO 24373-A	TS EN ISO 24373-A	Page Number
MCU Sn	ERCu	S Cu 1898 (CuSn1)	S Cu 1898 (CuSn1)	99
MCU Sn6	~ERCuSn-A	S Cu 5180A (CuSn6P)	S Cu 5180A (CuSn6P)	99
MCU Al8	ERCuAl-A1	S Cu 6100 (CuAl7)	S Cu 6100 (CuAl7)	99
MCU Si3	ERCuSi-A	S Cu 6560 (CuSi3Mn1)	S Cu 6560 (CuSi3Mn1)	99

Nickel Alloy MIG Welding Wires

Product Name	AWS / ASME SFA - 5.14	EN ISO 18274-A	TS EN ISO 18274-A	Page Number
MNI 425	ERNiCrMo-3	SNi 6625 (NiCr22Mo9Nb)	SNi 6625 (NiCr22Mo9Nb)	97

Hardfacing MIG/MAG Welding Wires

Product Name	EN ISO 14700-A	TS EN ISO 14700-A	DIN 8555*	Page Number
MH 361	S Fe8	S Fe8	MSG 6-GZ-60-GPS	97

*This standard is no longer valid. Added for informational purposes.

GAS METAL ARC (MIG/MAG) WELDING WIRES


Unalloyed Steel MIG/MAG Welding Wires

Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>MG 1</p> <p>AWS/ASME SFA - 5.18 ER70S-3 EN ISO 14341 - A G 38 3 C1 2Si EN ISO 14341 - A G 38 3 M21 2Si TS EN ISO 14341 - A G 38 3 C1 2Si TS EN ISO 14341 - A G 38 3 M21 2Si DIN M. No. 1.5125</p>	<p>Unalloyed wire electrode for GMA (MIG/MAG) welding of unalloyed steels by using CO₂ or mixed gases, depending on thickness of the base metal. Characterized by a reduced slag formation and smooth welding deposit. Particularly suitable for welding of galvanized and pre-paint steels, welding unalloyed steels in pipe-lines, boilers and tank construction. Suitable also welding thin metal plates and repair welds. A thin and homogeneous copper coating increases electrical conductivity and protects the wire from using.</p>	 
<p>MG 2</p> <p>AWS/ASME SFA - 5.18 ER70S-6 EN ISO 14341 - A G 42 4 M21 3Si1 EN ISO 14341 - A G 42 3 C1 3Si1 TS EN ISO 14341 - A G 42 4 M21 3Si1 TS EN ISO 14341 - A G 42 3 C1 3Si1 DIN M. No. 1.5125</p>	<p>Unalloyed wire electrode for GMA (MIG/MAG) welding of general structural steels, pipe steels, and cast steels using CO₂ or mixed shielding gases, depending on thickness of the base metal. Generally used in steel construction, shipbuilding, machine, tank, boiler production, automotive industry. Preheating is required, depending on the plate thickness and carbon equivalent of the base metal. A thin and homogeneous copper coating increases electrical conductivity and protects the wire from rusting.</p>	 
<p>MG 3</p> <p>AWS/ASME SFA - 5.18 ER70S-6 EN ISO 14341 - A G 46 4 M21 4Si1 EN ISO 14341 - A G 46 4 C1 4Si1 TS EN ISO 14341 - A G 46 4 M21 4Si1 TS EN ISO 14341 - A G 46 4 C1 4Si1 DIN M. No. 1.5130</p>	<p>Unalloyed wire electrode for GMA (MIG/MAG) welding of general structural steels, pipes and cast steels by using CO₂ or mixed shielding gases can be used depending on thickness of the base metal. Generally used in steel construction, machine, tank, boiler production. Preheating is required, depending on the plate thickness and carbon equivalent of the base metal. A thin and homogeneous copper coating increases electrical conductivity and protects the wire from rusting.</p>	 
<p>MG 20</p> <p>AWS/ASME SFA - 5.18 ER70S-6 EN ISO 14341 - A G 42 4 M21 3Si1 EN ISO 14341 - A G 42 4 C1 3Si1 TS EN ISO 14341 - A G 42 4 M21 3Si1 TS EN ISO 14341 - A G 42 4 C1 3Si1 DIN M. No. 1.5125</p>	<p>Non-copper coated and unalloyed GMA (MIG/MAG) wire electrode, especially produced for welding without spatter or very low level of spatter. Suitable for welding of general structural steels, boiler steels, pipe steels and cast steels. Due to its special coating provides stable arc and no spatter especially with mixed shielding gases which can be used depending on the thickness. Generally preferred in robotic applications, due to its high welding performance without spatter and cleaning needs. Also provides cost advantages in cleaning after welding, torch spare part consumptions like, contact tip, spiral, driving wheel, anti-spatter spray. Due to these advantages preferably used in automotive, machine and steel furniture production.</p>	 
<p>MG 30</p> <p>AWS/ASME SFA - 5.18 ER70S-6 EN ISO 14341 - A G 46 4 M21 4Si1 EN ISO 14341 - A G 46 4 C1 4Si1 TS EN ISO 14341 - A G 46 4 M21 4Si1 TS EN ISO 14341 - A G 46 4 C1 4Si1 DIN M. No. 1.5130</p>	<p>Non-copper coated and unalloyed GMA (MIG/MAG) wire electrode, especially produced for welding without spatter or very low level of spatter. Suitable for welding of general structural steels, boiler steels, pipe steels and cast steels. Due to its special coating provides stable arc and no spatter especially with mixed shielding gases which can be used depending on the thickness. Generally preferred in robotic applications due to its high welding performance without spatter and cleaning needs. Also provides cost advantages in cleaning after welding, torch spare part consumptions like, contact tip, spiral, driving wheel, anti-spatter spray. Due to these advantages preferably used in automotive, machine and steel furniture production.</p>	 




Typical Chemical Analysis of Welding Wire (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Shielding Gas	Diameter (mm)	Packing Weight (kg) Packing Type
C: 0.07	With M21 Shielding Gas				C1 (%100 CO ₂)		
	420	520	30	-30°C: 80	M20 (Ar + %5-15 CO ₂)	0.80	1 kg - D100
Si: 0.70					M21 (Ar + %15-25 CO ₂)	1.00	5 kg - D200
	With C1 Shielding Gas				M24 (Ar + %5-15 CO ₂ + %0.5-3 O ₂)	1.20	12 kg - D300 (0.60 mm)
					M26 (Ar + %15-25 CO ₂ + %0.5-3 O ₂)	1.60	15 kg - K300MS / K300 / D300
Mn: 1.25	400	470	30	-30°C: 100			250 kg - Drum
C: 0.07	With M21 Shielding Gas				C1 (%100 CO ₂)	0.60	
	460	560	27	-30°C: 95	M20 (Ar + %5-15 CO ₂)	0.80	1 kg - D100
Si: 0.90					M21 (Ar + %15-25 CO ₂)	0.90	5 kg - D200
	With C1 Shielding Gas				M24 (Ar + %5-15 CO ₂ + %0.5-3 O ₂)	1.00	12 kg - D300 (0.60 mm)
					M26 (Ar + %15-25 CO ₂ + %0.5-3 O ₂)	1.20	15 kg - K300MS / K300 / D300
Mn: 1.45	430	540	29	-20°C: 90 -30°C: 70		1.40	18 kg - K300MS
						1.60	60 kg - Drum
						2.00	250 kg - Drum
C: 0.07	With M21 Shielding Gas				C1 (%100 CO ₂)	0.60	
	480	580	27	-30°C: 95	M20 (Ar + %5-15 CO ₂)	0.80	1 kg - D100
Si: 0.95					M21 (Ar + %15-25 CO ₂)	0.90	5 kg - D200
	With C1 Shielding Gas				M24 (Ar + %5-15 CO ₂ + %0.5-3 O ₂)	1.00	15 kg - K300MS / K300 / D300
					M26 (Ar + %15-25 CO ₂ + %0.5-3 O ₂)	1.20	60 kg - Drum
Mn: 1.70	460	570	30	-40°C: 70		1.40	250 kg - Drum
						1.60	
						2.00	
C: 0.07	With M21 Shielding Gas				C1 (%100 CO ₂)	0.80	
	460	560	27	-30°C: 95	M20 (Ar + %5-15 CO ₂)	0.90	1 kg - D100
Si: 0.90					M21 (Ar + %15-25 CO ₂)	1.00	5 kg - D200
	With C1 Shielding Gas				M24 (Ar + %5-15 CO ₂ + %0.5-3 O ₂)	1.20	15 kg - K300MS / K300 / D300
					M26 (Ar + %15-25 CO ₂ + %0.5-3 O ₂)	1.40	60 kg - Drum
Mn: 1.45	430	540	29	-20°C: 90 -30°C: 70		1.60	250 kg - Drum
C: 0.07	With M21 Shielding Gas				C1 (%100 CO ₂)	0.80	
	480	580	27	-30°C: 95	M20 (Ar + %5-15 CO ₂)	1.00	1 kg - D100
Si: 0.95					M21 (Ar + %15-25 CO ₂)	1.20	5 kg - D200
	With C1 Shielding Gas				M24 (Ar + %5-15 CO ₂ + %0.5-3 O ₂)	1.40	15 kg - K300MS / K300 / D300
					M26 (Ar + %15-25 CO ₂ + %0.5-3 O ₂)	1.60	60 kg - Drum
Mn: 1.70	460	570	30	-40°C: 70		1.20	250 kg - Drum

GAS METAL ARC (MIG/MAG) WELDING WIRES

Unalloyed Steel MIG/MAG Welding Wires

Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>MG 102</p> <p>AWS/ASME SFA - 5.18 ER70S-2 EN ISO 14341 - A G 42 3 M21 2Ti EN ISO 14341 - A G 42 3 C1 2Ti TS EN ISO 14341 - A G 42 3 M21 2Ti TS EN ISO 14341 - A G 42 3 C1 2Ti</p>	<p>Micro-alloyed wire electrode for GMA (MIG/MAG) welding of unalloyed and low-alloy steels. Characterized by a reduced slag formation and smooth welding deposit. Due to its Al and Ti micro-alloy content, particularly suitable for single pass welding of galvanized, pre-painted, rusty and dirty steels, welding low alloy steels in pipe-lines, boilers and tank production. Suitable also welding in thin metal plates and repair welds. CO₂ or mixed shielding gases can be used depending on the thickness of the base metal. A thin and homogeneous copper coating increases electrical conductivity and protects the wires from rusting.</p>	

Low-Alloyed, High Strength and Creep Resistant Steel MIG/MAG Welding Wires






Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>MG 150</p> <p>AWS/ASME SFA - 5.28 ER80S-Ni1 EN ISO 14341 - A G 50 6 M21 3Ni1 TS EN ISO 14341 - A G 50 6 M21 3Ni1</p>	<p>Low alloyed wire electrode for GMA (MIG/MAG) welding of steels, which are subjected to operating temperatures down to -60°C. Weld metal has high strength and high toughness. Suitable to use in petrochemical, chemical, oil/gas industries and off-shore platforms, especially welding of pipes, boilers, tanks and valves, pumps which are made of cast or forged steels.</p>	
<p>MG 150W</p> <p>AWS/ASME SFA - 5.18 ER80S-G EN ISO 14341 - A G 42 2 M21 Z2NiCu TS EN ISO 14341 - A G 42 2 M21 Z2NiCu</p>	<p>Low-alloyed GMA (MIG/MAG) welding wire designed for welding of weathering steels (like COR-TEN) with high mechanical properties. Due to nickel and copper alloys, it provides higher corrosion resistance than carbon steels. Suitable for welding in steel construction manufacturing such as bridge, stadium and steel construction.</p>	
<p>MG 182</p> <p>AWS/ASME SFA - 5.28 ER110S-G EN ISO 16834 - A G 69 6 M21 Mn4Ni1,5CrMo TS EN ISO 16834 - A G 69 6 M21 Mn4Ni1,5CrMo</p>	<p>Low alloyed wire electrode for GMA (MIG/MAG) welding of fine grained and high strength steels with yield strength of up to 690 N/mm². Weld metal exhibits good toughness properties down to -60°C. Especially used in high strength pipe-lines, earthmoving and mining equipments, trucks, mobile cranes, concrete pumps cranes and lift productions.</p>	

Typical Chemical Analysis of Welding Wire (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Shielding Gas	Diameter (mm)	Packing Weigth (kg) Packing Type
C: 0.04	460	530	25	-30°C: 60	C1 (%100 CO ₂) M20 (Ar + %5-15 CO ₂) M21 (Ar + %15-25 CO ₂)	0.60	1 kg - D100 5 kg - D200 15 kg - K300MS / K300 / D300 250 kg - Drum
Si: 0.50						0.80	
Mn: 1.10						0.90	
Ti: 0.13						1.00	
Zr: 0.08						1.20	
Al: 0.10						1.60	

Typical Chemical Analysis of Welding Wire (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Shielding Gas	Diameter (mm)	Packing Weigth (kg) Packing Type
C: 0.09	480	570	28	-60°C: 60	M21 (Ar + %15-25 CO ₂)	0.80	15 kg - K300MS
Si: 0.50						1.00	
Mn: 1.05						1.20	
Ni: 0.90	470	600	27	-20°C: 47	M21 (Ar + %15-25 CO ₂)	1.00	15 kg - K300MS
C: 0.09						1.20	
Si: 0.80							
Mn: 1.40							
Ni: 0.80							
Cu: 0.40							
C: 0.09	750	820	20	-60°C: 55	M21 (Ar + %15-25 CO ₂)	1.00	15 kg - K300MS
Si: 0.55						1.20	
Mn: 1.55							
Cr: 0.25							
Ni: 1.35							
Mo: 0.25							
Ti: 0.07							

GAS METAL ARC (MIG/MAG) WELDING WIRES





Low-Alloyed, High Strength and Creep Resistant Steel MIG/MAG Welding Wires

Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>MG 183</p> <p>AWS/ASME SFA - 5.28 ER110S-G AWS/ASME SFA - 5.28 ER100S-G EN ISO 16834 - A G 69 4 M21 Mn3Ni1CrMo TS EN ISO 16834 - A G 69 4 M21 Mn3Ni1CrMo</p>	<p>Low alloyed wire electrode for GMA (MIG/MAG) welding of fine grained and high strength steels with yield strength of up to 690 N/mm². Weld metal exhibits good toughness properties down to -40°C. Especially used in high strength pipe-lines, earthmoving and mining equipments, trucks, mobile cranes, concrete pumps cranes and lift productions.</p>	
<p>MG 192</p> <p>AWS/ASME SFA - 5.28 ER120S-G EN ISO 16834 - A G 89 6 M21 Mn4Ni2CrMo TS EN ISO 16834 - A G 89 6 M21 Mn4Ni2CrMo</p>	<p>Low alloyed wire electrode for GMA (MIG/MAG) welding of fine grained and high strength steels with yield strength of up to 960 N/mm². Weld metal exhibits good toughness properties down to -60°C. Especially used in earthmoving, mining equipments, trucks, mobile cranes, concrete pumps crane, lift and oilfield equipments productions.</p>	
<p>MG 201</p> <p>AWS/ASME SFA - 5.28 ER70S-A1 AWS/ASME SFA - 5.28 ER80S-G EN ISO 21952 - A G MoSi TS EN ISO 21952 - A G MoSi DIN M. No. 1.5424</p>	<p>Low alloyed wire electrode for GMA (MIG/MAG) welding of creep resistant boiler and pipe steels subjected to operating temperatures up to 500°C. Also suitable for joining C-Mn steels, which will be postweld heat treated. CO₂ or mixed shielding gases can be used depending on the thickness of the base metal. A thin and homogeneous copper coating increases electrical conductivity and protects the wire from rusting.</p>	
<p>MG 201A</p> <p>AWS/ASME SFA - 5.28 ER80S-D2 EN ISO 21952 - A G Z MnMo TS EN ISO 21952 - A G Z MnMo</p>	<p>Low alloyed wire electrode for GMA (MIG/MAG) welding of creep resistant boiler and pipe steels subjected to operating temperatures up to 530°C. Contains high level of deoxidizing (Mn and Si) elements to control porosity during welding. Welds are of X-ray quality. Also suitable for joining C-Mn steels to be postweld heat treated. Observe directions as to pre and post weld heat treatment of base material. CO₂ or mixed shielding gases can be used depending on the thickness of the base metal. A thin and homogeneous copper coating increases electrical conductivity and protects the wire from rusting.</p>	
<p>MG 211</p> <p>AWS/ASME SFA - 5.28 ER80S-G EN ISO 21952 - A G CrMo1Si TS EN ISO 21952 - A G CrMo1Si DIN M. No. 1.7339</p>	<p>Low-alloy wire electrode for GMA (MIG/MAG) welding of Cr-Mo alloyed creep resistant boiler and pipe steels subjected to operating temperatures up to 570°C. Also suitable for joining C-Mn steels to be postweld heat treated. Observe directions as to pre and post weld heat treatment of base material. CO₂ or mixed shielding gases can be used depending on the thickness of the base metal. A thin and homogeneous copper coating increases electrical conductivity and protects the wire from rusting.</p>	





Typical Chemical Analysis of Welding Wire (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Shielding Gas	Diameter (mm)	Packing Weigth (kg) Packing Type							
C: 0.09	710	780	19	-40°C: 65	M21 (Ar + %15-25 CO ₂)	1.00 1.20 1.60	15 kg - K300MS 400 kg - Bidon							
Si: 0.55														
Mn: 1.55														
Cr: 0.30														
Ni: 1.40														
Mo: 0.25														
C: 0.09	980	1050	15	-60°C: 50	M21 (Ar + %15-25 CO ₂)	1.00 1.20	15 kg - K300MS							
Si: 0.80														
Mn: 1.80														
Cr: 0.30														
Ni: 2.20														
Mo: 0.55														
C: 0.10	500	600	23	0°C: 50 20°C: 100	M21 (Ar + %15-25 CO ₂)	0.80 1.00 1.20 1.60	15 kg - K300MS							
Si: 0.60														
Mn: 1.20														
Mo: 0.50														
C: 0.09								520	600	22	0°C: 60 -20°C: 50	M21 (Ar + %15-25 CO ₂)	0.80 1.00 1.20 1.60	15 kg - K300MS
Si: 0.75														
Mn: 1.90														
Mo: 0.45														
C: 0.09	As Welded				M21 (Ar + %15-25 CO ₂)	0.80 1.00 1.20 1.60	15 kg - K300MS							
Si: 0.60	630	750	18	20°C: 80										
Mn: 1.00	After Heat Treatment (685°C 1 Hour)													
Cr: 1.20	500	600	28	20°C: 120										
Mo: 0.50														

GAS METAL ARC (MIG/MAG) WELDING WIRES

Low-Alloyed, High Strength and Creep Resistant Steel MIG/MAG Welding Wires

Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>MG 211A</p> <p>AWS/ASME SFA - 5.28 ER80S-B2 EN ISO 21952 - A G Z CrMo1Si TS EN ISO 21952 - A G Z CrMo1Si EN ISO 21952 - B G 55M 1CM EN ISO 21952 - B G 55C 1CM TS EN ISO 21952 - B G 55M 1CM TS EN ISO 21952 - B G 55C 1CM</p>	<p>Low-alloy wire electrode for GMA (MIG/MAG) welding of Cr-Mo alloyed creep resistant boiler and pipe steels subjected to operating temperatures up to 570°C. Contains high level of deoxidizing (Mn and Si) elements to control porosity during welding. Welds are of X-ray quality. Also suitable for joining C-Mn steels to be postweld heat treated. Observe directions as to pre and post weld heat treatment of base material. CO₂ or mixed shielding gases can be used depending on the thickness of the base metal. A thin and homogeneous copper coating increases electrical conductivity and protects the wire from rusting.</p>	 
<p>MG 222</p> <p>AWS/ASME SFA - 5.28 ER90S-G AWS/ASME SFA - 5.28 ~ER90S-B3 EN ISO 21952 - A G CrMo2Si TS EN ISO 21952 - A G CrMo2Si DIN M. No. 1.7384</p>	<p>Low-alloy wire electrode for GMA (MIG/MAG) welding of Cr-Mo alloyed creep resistant boiler and pipe steels subjected to operating temperatures up to 600°C. Also suitable for joining C-Mn steels to be postweld heat treated. Observe directions as to pre and post weld heat treatment of base material. CO₂ or mixed shielding gases can be used depending on the thickness of the base metal. A thin and homogeneous copper coating increases electrical conductivity and protects the wire from rusting.</p>	 

Stainless Steel MIG Welding Wires









Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>MI 307Si</p> <p>AWS/ASME SFA - 5.9 ~ER307 EN ISO 14343 - A G 18 8 Mn TS EN ISO 14343 - A G 18 8 Mn DIN M. No. 1.4370</p>	<p>Austenitic stainless steel wire electrode for GMA (MIG/MAG) welding of dissimilar steels, difficult to weld steels, armour plates, high manganese steels, rails, crossovers. Suitable also for depositing stress relaxing buffer layers on crack sensitive base metals and hardfacing jobs, e.g. crane wheel surfacing where high degree of pressure and dynamical loads exists. Weld metal has a high degree of corrosion resistance and resistant to operating temperatures up to 300°C and non-scaling up to 850°C. Observe welding procedures, preheating temperature and avoid high admixture of base metal.</p>	 
<p>MI 308LSi</p> <p>AWS/ASME SFA - 5.9 ER308LSi EN ISO 14343 - A G 19 9 LSi TS EN ISO 14343 - A G 19 9 LSi DIN M. No. 1.4316</p>	<p>Austenitic stainless steel welding wire for GMA (MIG/MAG) welding of unstabilized or stabilized corrosion resisting Cr-Ni steels tanks, pipes and equipments used in food beverage and pharmaceutical industry. Resistant to intergranular corrosion up to 350°C. Non-scaling up to 800°C, in air or oxidizing combustion gases.</p>	 

Typical Chemical Analysis of Welding Wire (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Shielding Gas	Diameter (mm)	Packing Weigth (kg) Packing Type
C: 0.09	As Welded						
Si: 0.55	600	720	21	20°C: 90	C1 (%100 CO ₂) M20 (Ar + %5-15 CO ₂) M21 (Ar + %15-25 CO ₂)	0.80	15 kg - K300MS
Mn: 0.55	After Heat Treatment (620°C 1 Hour)			1.00			
Cr: 1.35				1.20			
Mo: 0.50	570	670	23	20°C: 100			
C: 0.08	As Welded						
Si: 0,65	740	900	22	-20°C: 40 20°C: 50	C1 (%100 CO ₂) M20 (Ar + %5-15 CO ₂) M21 (Ar + %15-25 CO ₂)	1.00	15 kg - K300MS
Mn: 1.00	After Heat Treatment (720°C 1 Hour)			1.20			
Cr: 2.50				1.60			
Mo: 1.00	480	600	27	20°C: 150			

Typical Chemical Analysis of Welding Wire (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Shielding Gas	Diameter (mm)	Packing Weigth (kg) Packing Type
C: 0.07							
Si: 0.80					I1 (%100 Ar) M12 (Ar + %0.5-5 CO ₂) M13 (Ar + %0.5-3 O ₂) M14 (Ar + %0.5-5 CO ₂ + %0.5-3 O ₂)	1.00	15 kg - K300MS
Mn: 7.00	460	630	39	20°C: 90 -20°C: 60		1.20	
Cr: 18.00				1.60			
Ni: 8.00							
C: 0.01							
Si: 0.70					I1 (%100 Ar) M12 (Ar + %0.5-5 CO ₂) M13 (Ar + %0.5-3 O ₂) M14 (Ar + %0.5-5 CO ₂ + %0.5-3 O ₂)	0.60	1 kg - D100 5 kg - D200 15 kg - K300MS
Mn: 1.90	450	570	38	20°C: 100		0.80	
Cr: 20.00				1.00			
Ni: 9.50				1.20			
				1.60			

GAS METAL ARC (MIG/MAG) WELDING WIRES




Stainless Steel MIG Welding Wires

Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>MI 309LSi</p> <p>AWS/ASME SFA - 5.9 ER309LSi EN ISO 14343 - A G 23 12 LSi TS EN ISO 14343 - A G 23 12 LSi DIN M. No. 1.4332</p>	<p>Austenitic-ferritic wire electrode for GMA (MIG/MAG) welding of dissimilar joints of stainless steels to unalloyed or low-alloyed steels, subjected to operating temperatures up to 300°C. Suitable to use also as buffer layer on carbon steel before welding with 308 and 308L to reach 304 and 304L layer. Low carbon content increases resistance to intergranular corrosion.</p>	 
<p>MI 310</p> <p>AWS/ASME SFA - 5.9 ER310 EN ISO 14343 - A G 25 20 TS EN ISO 14343 - A G 25 20 DIN M. No. 1.4842</p>	<p>Fully austenitic stainless steel wire electrode for GMA (MIG/MAG) welding of heat resistant steels, containing approx. 25% chromium and 20% nickel, which are used in heat treatment and industrial furnaces and equipments, like cement and steel industries. Also suited for welding heat resistant and scaling resistant ferritic chromium steels, provided that corrosion attack by reducing sulphur-bearing combustion gases is not expected. Weld metal exhibits good toughness down to -196°C and non-scaling up to 1200°C.</p>	 
<p>MI 312</p> <p>AWS/ASME SFA - 5.9 ER312 EN ISO 14343 - A G 29 9 TS EN ISO 14343 - A G 29 9 DIN M. No. 1.4337</p>	<p>Austenitic-ferritic stainless steel wire electrode for GMA (MIG/MAG) welding of dissimilar steels and depositing buffer layers on ferritic steels. It features high resistance to cracking and toughness, is therefore suited for joining difficult to weld steels and depositing stress-relaxing buffer layers on crack sensitive base metals. Weld metal is non-scaling up to 1100°C. Especially used in die and tool repair, crack repairs in difficult to weld steels, gear teeth repair and rebuilding, buffer layer application on cutting blades. Suitable also for welding galvanized steel plates.</p>	 
<p>MI 316LSi</p> <p>AWS/ASME SFA - 5.9 ER316LSi EN ISO 14343 - A G 19 12 3 LSi TS EN ISO 14343 - A G 19 12 3 LSi DIN M. No. 1.4430</p>	<p>Austenitic stainless steel wire electrode for GMA (MIG) welding of unstabilized or stabilized corrosion resisting Cr-Ni-Mo steels. Resistant to intergranular corrosion up to 400°C. Especially used in welding chemical tanks, pipes and equipments which are used in chemical, petrochemical, paint, textile, paper and shipbuilding industries, etc.</p>	 
<p>MI 347</p> <p>AWS/ASME SFA - 5.9 ER347 EN ISO 14343 - A G 19 9 Nb TS EN ISO 14343 - A G 19 9 Nb DIN M. No. 1.4316</p>	<p>Stabilized austenitic stainless steel wire electrode for GMA (MIG/MAG) welding of unstabilized and stabilized corrosion resistant Cr-Ni steels, used in food, beverage, chemical and pharmaceutical industries. Stabilized with Nb (Niobium) and resistant to intergranular corrosion. Weld metal is suitable for operating temperatures of up to 400°C, non-scaling up to 800°C, in air and oxidizing combustion gases.</p>	 

Typical Chemical Analysis of Welding Wire (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Shielding Gas	Diameter (mm)	Packing Weight (kg) Packing Type
C: 0.01							
Si: 0.70					I1 (%100 Ar)		
Mn: 1.90	460	600	38	20°C: 100	M12 (Ar + %0.5-5 CO ₂)	1.00	15 kg - K300MS
Cr: 23.50					M13 (Ar + %0.5-3 O ₂)	1.20	
Ni: 13.50					M14 (Ar + %0.5-5 CO ₂ + %0.5-3 O ₂)	1.60	
C: 0.10							
Si: 0.40					I1 (%100 Ar)		
Mn: 1.60	440	600	28	-20°C: 120	M12 (Ar + %0.5-5 CO ₂)	0.80	15 kg - K300MS
Cr: 26.00					M13 (Ar + %0.5-3 O ₂)	1.00	
Ni: 21.00					M14 (Ar + %0.5-5 CO ₂ + %0.5-3 O ₂)	1.20	
C: 0.01							
Si: 0.40					I1 (%100 Ar)		
Mn: 1.80	550	740	25	20°C: 80	M12 (Ar + %0.5-5 CO ₂)	0.80	15 kg - K300MS
Cr: 30.00					M13 (Ar + %0.5-3 O ₂)	1.00	
Ni: 9.00					M14 (Ar + %0.5-5 CO ₂ + %0.5-3 O ₂)	1.20	
						1.60	
C: 0.02							
Si: 0.70					I1 (%100 Ar)		
Mn: 1.90	420	570	42	20°C: 65	M12 (Ar + %0.5-5 CO ₂)	0.80	5 kg - D200 15 kg - K300MS
Cr: 18.50					M13 (Ar + %0.5-3 O ₂)	1.00	
Ni: 11.50					M14 (Ar + %0.5-5 CO ₂ + %0.5-3 O ₂)	1.20	
Mo: 2.50						1.60	
C: 0.04							
Si: 0.40					I1 (%100 Ar)		
Mn: 1.40	430	620	32	20°C: 80	M12 (Ar + %0.5-5 CO ₂)	0.80	15 kg - K300MS
Cr: 19.50					M13 (Ar + %0.5-3 O ₂)	1.00	
Ni: 9.50					M14 (Ar + %0.5-5 CO ₂ + %0.5-3 O ₂)		
Nb: 0.70							

GAS METAL ARC (MIG/MAG) WELDING WIRES











Stainless Steel MIG Welding Wires

Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>MI 385</p> <p>AWS/ASME SFA - 5.9 ER385 EN ISO 14343 - A G 20 25 5 Cu L TS EN ISO 14343 - A G 20 25 5 Cu L DIN M. No. ~1.4539</p>	<p>Fully-austenitic stainless steel wire electrode for GMA (MIG/MAG) welding of unstabilized or stabilized corrosion resisting Cr-Ni-Mo alloyed stainless steels like 904L/1.4539. Especially used in flue gas desulphurization plants, fertilizer plants, sea water transfer fittings, petrochemical, paper and pulp industries, etc. Due to high Ni, Mo and low C content, weld metal has high resistant to intergranular, pitting, crevice and stress corrosion types in chloride containing solutions, phosphorus-, sulphur-, acetic-, formic acids, sea water.</p>	
<p>MI 410</p> <p>AWS/ASME SFA - 5.9 ER410 EN ISO 14343 - A G 13 TS EN ISO 14343 - A G 13 DIN M. No. 1.4006</p>	<p>Martensitic stainless steel wire for GMA (MIG/MAG) welding of martensitic stainless steels, heat resistant steels and cast steels which contain approx. 13% chromium. Suitable for joining and surfacing of gas, water and steam fan, fan blades and fittings subjected to corrosion, erosion and operating temperatures up to 450°C. Depending on type of base metal composition and thickness, preheating between 200 and 300°C, keeping the interpass temperature during welding and tempering between 700 and 750°C after welding are advisable.</p>	
<p>MI 2209</p> <p>AWS/ASME SFA - 5.9 ER2209 EN ISO 14343 - A G 22 9 3 N L TS EN ISO 14343 - A G 22 9 3 N L DIN M. No. ~1.4462</p>	<p>Duplex (ferritic-austenitic) stainless steel wire electrode for GMA (MIG/MAG) welding of duplex Cr-Ni-Mo stainless steels. Especially used in welding of acid tanks and pipes, in chemical, petrochemical, paper, shipbuilding and desalination industries. Suitable also for welding duplex stainless steels to carbon steels. The high strength and ductile weld metal exhibits good resistance to pitting, crevice corrosion and stress corrosion cracking in chloride-bearing media. Suitable for operating temperatures up to 250°C.</p>	

Typical Chemical Analysis of Welding Wire (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Shielding Gas	Diameter (mm)	Packing Weigth (kg) Packing Type
C: 0.01	380	550	39	20°C: 90 -196°C: 60	I1 (%100 Ar) M12 (Ar + %0.5-5 CO ₂) M13 (Ar + %0.5-3 O ₂) M14 (Ar + %0.5-5 CO ₂ + %0.5-3 O ₂)	1,20	15 kg - K300MS
Si: 0.40							
Mn: 1.80							
Cr: 20.00							
Ni:25.00							
Mo: 4.25							
Cu: 1.50							
C: 0.10	450	600	23	0°C: 30 20°C: 60	I1 (%100 Ar) M12 (Ar + %0.5-5 CO ₂) M13 (Ar + %0.5-3 O ₂) M14 (Ar + %0.5-5 CO ₂ + %0.5-3 O ₂)	1.00	15 kg - K300MS
Si: 0.30						1.20	
Mn: 0.50							
Cr: 12.50							
C: 0.01	580	770	30	-40°C: 90	I1 (%100 Ar) M12 (Ar + %0.5-5 CO ₂) M13 (Ar + %0.5-3 O ₂) M14 (Ar + %0.5-5 CO ₂ + %0.5-3 O ₂)	1.00	15 kg - K300MS
Si: 0.50						1.20	
Mn: 1.50							
Cr: 23.50							
Ni: 8.50							
Mo: 3.50							
N: 0.15							

GAS METAL ARC (MIG/MAG) WELDING WIRES



Aluminium Alloy MIG Welding Wires

Product Name and Standards	Applications and Properties	Polarity Welding Positions
MAL 1100 AWS/ASME SFA - 5.10 ~ER1100 AWS/ASME SFA - 5.10 ER1070 EN ISO 18273 S AI 1070 (Al99.7) TS 6204 EN ISO 18273 S AI 1070 (Al99.7) DIN M. No. 3.0259	Aluminium welding wire electrode for GMA (MIG) welding of pure aluminium base metals. Exhibits high corrosion resistance and has high electrical conductivity. Has color match with pure aluminium base metals.	 
MAL 4043 AWS/ASME SFA - 5.10 ER4043 EN ISO 18273 S AI 4043 (AlSi5) TS EN ISO 18273 S AI 4043 (AlSi5) DIN M. No. 3.2245	5% Silicon containing aluminium wire electrode for GMA (MIG) welding of aluminium and aluminium alloys. Suitable for welding aluminium casting, containing up to 7% silicon and Al-Mg-Si alloys which are containing up to 2% Magnesium alloying element.	 
MAL 4047 AWS/ASME SFA - 5.10 ER4047 EN ISO 18273 S AI 4047A (AlSi12(A)) TS EN ISO 18273 S AI 4047A (AlSi12(A)) DIN M. No. 3.2585	12% Silicon containing aluminium alloy welding wire, for GMA (MIG) welding of aluminium-silicon (Al-Si) and aluminium-silicon-magnesium (Al-Si-Mg) alloy castings, having a Si content of up to 7% alloying elements.	 
MAL 5183 AWS/ASME SFA - 5.10 ER5183 EN ISO 18273 S AI 5183 (AlMg4.5Mn0.7(A)) TS EN ISO 18273 S AI 5183 (AlMg4.5Mn0.7(A)) DIN M. No. 3.3548	5% Magnesium and manganese containing aluminium alloy welding wire for GMA (MIG) welding of Al-alloys with high tensile strength requirements. Suitable for welding Al-Mg alloys and Al-Mg-Mn alloys.	 
MAL 5356 AWS/ASME SFA - 5.10 ER5356 EN ISO 18273 S AI 5356 (AlMg5Cr(A)) TS EN ISO 18273 S AI 5356 (AlMg5Cr(A)) DIN M. No. 3.3556	5% Magnesium containing aluminium welding wire for GMA (MIG) welding of Al-Mg alloys and Al-Mg-Si alloys. Very good corrosion resistance especially in sea water and gives excellent ductility.	 



Typical Chemical Analysis of Welding Wire (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Shielding Gas	Diameter (mm)	Packing Weight (kg) Packing Type
Al: 99.50	20	65	35	-	I1 (%100 Ar) I2 (%100 He) I3 (Ar + %0.5-95 He)	1.60 2.00	7.00 kg - K300MS
Si: 5.00							
Mn: 0.05	80	160	9	-	I1 (%100 Ar) I2 (%100 He) I3 (Ar + %0.5-95 He)	0.80 1.00 1.20 1.60 2.00	7.00 kg - K300MS
Al: 94.95							
Si: 12.00							
Al: 88.00	90	190	6	-	I1 (%100 Ar) I2 (%100 He) I3 (Ar + %0.5-95 He)	1.20 1.60	7.00 kg - K300MS
Mg: 4.75							
Mn: 0.60	125	270	23	-	I1 (%100 Ar) I2 (%100 He) I3 (Ar + %0.5-95 He)	1.00 1.20	7.00 kg - K300MS
Ti: 0.10							
Al: 94.55							
Mg: 4.75							
Cr: 0.10	110	240	26	-	I1 (%100 Ar) I2 (%100 He) I3 (Ar + %0.5-95 He)	0.80 1.00 1.20	7.00 kg - K300MS
Al: 95.15							

GAS METAL ARC (MIG/MAG) WELDING WIRES



Aluminium Alloy MIG Welding Wires

Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>MAL 5556</p> <p>AWS/ASME SFA - 5.10 ER5556 EN ISO 18273 S Al 5556 (AlMg5Mn1Ti(A)) TS EN ISO 18273 S Al 5556 (AlMg5Mn1Ti(A)) DIN M. No. ~3.3548</p>	<p>5% Magnesium containing aluminium welding wire for GMA (MIG) welding of Al-Mg alloys and Al-Mg-Zn alloys. Have a good corrosion resistance especially in sea water and gives excellent ductility.</p>	 

Nickel Alloy MIG Welding Wires

Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>MNI 425</p> <p>AWS/ASME SFA-5.14 ERNiCrMo-3 EN ISO 18274-A S Ni 6625 (NiCr22Mo9Nb) TS EN ISO 18274-A S Ni 6625 (NiCr22Mo9Nb) DIN M. No. 2.4831</p>	<p>Ni-Cr-Mo alloyed GMA (MIG) welding wire, depositing Ni-22Cr9Mo3,5Nb weld metal. Used for welding of highly corrosion resistant Ni-Cr-Mo alloys, like Alloy 625, 825 and similar alloys. Due to its good cryogenic toughness down to -196°C, preferred for welding of cryogenic nickel alloys, e.g. X1NiCrMoCuN25-20-7. In sulphur free atmospheres the weld metal is non-scaling up to 1200°C, in sulphurous atmospheres the weld metal can be used in service temperatures up to 500°C. It is also highly resistant stress corrosion cracking and pitting corrosion in phosphoric acid, organic acids, sea water and polluting environments. Weld metal is insensitive to cracking and very resistant to thermal shocks. Used for joining of dissimilar nickel alloys, joining dissimilar stainless steels, low alloyed steels to stainless steels or to nickel alloys, buffering of difficult to weld steels and repair welding of them.</p>	 

Hardfacing MIG/MAG Welding Wires

Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>MH 361</p> <p>EN 14700 S Fe8 TS EN 14700 S Fe8 DIN 8555 MSG 6-GZ-60-GPS DIN M. No. 1.4718</p>	<p>Gas metal arc (MIG/MAG) welding wire especially developed for hardfacing of parts subjected to high metal-to-metal friction, mineral abrasion and moderate impact. Weld metal can retain its hardness at high temperatures, till 600°C. Weld metal can be grinded and machined by diamond tools. A tough buffer layer with FCW 30 is recommended before hardfacing, if base metal has high carbon and low weldability. Heat treatment after hardfacing will decrease as-welded hardness.</p> <p>Typical Applications: Ceramic tile moulds, mixer blades, crushers, earth moving equipments, hot cut-offs, shear blades, dies for pressure casting, scraper blades, conveyors, rollers.</p>	 

Typical Chemical Analysis of Welding Wire (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Shielding Gas	Diameter (mm)	Packing Weight (kg) Packing Type
Mg: 4.90	130	290	28	-	I1 (%100 Ar) I2 (%100 He) I3 (Ar + %0.5-95 He)	1.00 1.20	7.00 kg - K300MS
Mn: 0.65							
Si: 0.05							
Cr: 0.07							
Cu: 0.01							
Ti: 0.07							
Fe: 0.11							
Zn: 0.006							
Al: 94.13							

Typical Chemical Analysis of Welding Wire (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Shielding Gas	Diameter (mm)	Packing Weight (kg) Packing Type
C: 0.01	460	720	40	20°C: 110 -196°C: 100	I1 (%100 Ar) I3 (Ar + %0.5-95 He)	1,20	15 kg - K300MS
Si: 0.05							
Mn: 0.05							
Cr: 22.20							
Ni: 65.00							
Mo: 8.70							
Nb: 3.65							
Ti: 0.20							
Fe: 0.14							

Typical Chemical Analysis of Welding Wire (%)	Hardness (HRC)	Shielding Gas	Diameter (mm)	Packing Weight (kg) Packing Type
C: 0.40	59	M12 (Ar + %0.5-5 CO2) M21 (Ar + %15-25 CO2)	1.00 1.20	15 kg - K300MS
Si: 2.40				
Mn: 0.35				
Cr: 8.60				
Fe: 88.25				

GAS METAL ARC (MIG/MAG) WELDING WIRES

Copper Alloy MIG Welding Wires

Product Name and Standards	Applications and Properties	Polarity Welding Positions
MCU Sn AWS/ASME SFA - 5.7 EN ISO 24373 TS EN ISO 24373 DIN M. No.	ERCu S Cu 1898 (CuSn1) S Cu 1898 (CuSn1) 2.1006	Tin alloyed copper wire electrode for GMA (MIG) welding of copper and low alloyed copper alloys. Particularly used in electric and heat conductor parts, which are made of pure copper. Suitable for welding oxygen-free copper and copper materials subject to high strain. Gives pore-free and easily machinable welding seams.
MCU Sn6 AWS/ASME SFA - 5.7 EN ISO 24373 TS EN ISO 24373 DIN M. No.	~ERCuSn-A S Cu 5180A (CuSn6P) S Cu 5180A (CuSn6P) 2.1022	6% Tin alloyed copper wire electrode for GMA (MIG) welding and surfacing of Cu-Sn (4 - 8 % Sn bronze), Cu-Zn (brass), and Cu-Sn-Zn-Pb alloys. Suitable for joining of copper alloys to steels, repair welding of cast bronzes and cladding on cast iron and steels. For large workpieces e.g. thicknesses exceeding 5 mm, a preheat at about 250°C is recommended.
MCU Al8 AWS/ASME SFA - 5.7 EN ISO 24373 TS EN ISO 24373 DIN M. No.	ERCuAl-A1 S Cu 6100 (CuAl7) S Cu 6100 (CuAl7) 2.0921	8% Aluminium alloyed copper wire electrode for GMA (MIG) welding of copper-aluminium (Cu-Al) alloys (aluminium-bronzes). Also suitable for surfacing of parts subjected to metal to metal wear under high compressive stresses or in the presence of corrosive agents (acids, sea water).
MCU Si3 AWS/ASME SFA - 5.10 EN ISO 24373 TS EN ISO 24373 DIN M. No.	ERCuSi-A S Cu 6560 (CuSi3Mn1) S Cu 6560 (CuSi3Mn1) 2.1461	3% Silicon alloyed copper wire electrode for GMA (MIG) welding of copper(Cu), Cu-Si (silicon bronze), Cu-Zn (brass) and as well as surfacing of unalloyed or medium alloyed steels or cast irons. Due to less Zn burn and corrosion resistant weld metal, suitable for joining of galvanized steels. Resulted Zn burn is less and weld metal is corrosion resistant in galvanized steels. For large workpieces e.g. thicknesses exceeding 5 mm, a preheat at about 250°C is recommended.

Typical Chemical Analysis of Welding Wire (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Shielding Gas	Diameter (mm)	Packing Weigth (kg) Packing Type
Si: 0.20							
Mn: 0.20							
Sn: 0.80	100	220	30	60	15-20	I1 (%100 Ar) I2 (%100 He) I3 (Ar + %0.5-95 He)	1.00 1.20 1.60 15 kg - D300
P: 0.01							
Cu: 98.79							
P: 0.20							
Sn: 6.50	160	260	20	80	6-7	I1 (%100 Ar) I2 (%100 He) I3 (Ar + %0.5-95 He)	1.00 1.20 15 kg - D300
Cu: 93.30							
Mn: 0.20							
Al: 8.00	200	430	40	100	7-8	I1 (%100 Ar) I2 (%100 He) I3 (Ar + %0.5-95 He)	1.00 1.20 1.60 15 kg - D300
Ni: 0.30							
Cu: 91.50							
Si: 2.90							
Mn: 0.80	120	350	40	80	3.5-4	I1 (%100 Ar) I2 (%100 He) I3 (Ar + %0.5-95 He)	0.80 1.00 15 kg - D300 1 kg - D100 5 kg - D200 200 kg - Drum
Cu: 96.30							

FLUX CORED ARC WELDING WIRES

FLUX CORED ARC WELDING WIRES

Unalloyed Steel Flux Cored Welding Wires

Product Name	AWS / ASME SFA - 5.18 / 5.20	EN ISO 17632-A	TS EN ISO 17632-A	Page Number
FCW 11	E71T-1C	T46 2 P C 1	T46 2 P C 1	103
FCW 11A	E71T-1C H4	T46 2 P C 1 H5	T46 2 P C 1 H5	103
FCW 12	E71T-1M	T46 2 P M 1	T46 2 P M 1	103
FCW 13	E71T-1M-1C	T 46 2 P C 1 H5	T 46 2 P C 1 H5	103
FCW 14	E71T-1C	T 46 3 P M 1 H5	T 46 3 P M 1 H5	103
FCW 16	E71T-1CJ E71T-9CJ	T46 2 P C 1	T46 2 P C 1	105
FCW 17	E71T-1MJ E71T-9MJ E71T-12MJ	T46 4 P C 1 T46 4 P M 1 H5 T46 4 M M 2 H5	T46 4 P C 1 T46 4 P M 1 H5 T46 4 M M 2 H5	105
FCW 21	E70C-6M H4			105
FCW 30	E70T-5C H4 E70T-5M H4	T42 4 B C 3 H5 T42 4 B M 3 H5	T42 4 B C 3 H5 T42 4 B M 3 H5	105
FCO 90	E71T-GS	-	-	105

Low Alloyed, High Strength and Creep Resistant Steel Flux Cored Welding Wires

Product Name	AWS / ASME SFA - 5.29	EN ISO 17632-A	TS EN ISO 17632-A/ TS EN ISO 17632-B	Page Number
FCW 140	E81T1-Ni1C	T46 4 1Ni P C 1	T46 4 1Ni P C 1	107
FCW 142	E81T1-Ni1M E81T-1 M21A6 Ni1	T46 4 1Ni P M 1 H5	T46 4 1Ni P M 1 H5	107
FCW 150W	E81T1-W2C	T553T1-1C A-NCC1	T553T1-1C A-NCC1	107
FCW 171	E81T-1 Ni2 C J	T50 6 2Ni P C 2 H5	T50 6 2Ni P C 2 H5	107
FCW 172	E81T-1 Ni2 M J	T50 6 2Ni P M 2 H5	T50 6 2Ni P M 2 H5	107
FCW 201	E81T1-A1C	T MoL P C 1 H5	T MoL P C 1 H5	109

Hardfacing Flux Cored Wires

Product Name	AWS / ASME SFA - 5.21	EN ISO 14700-A	TS EN ISO 14700-A	DIN 8555*	Page Number
FCO 250	-	T Fe9	T Fe9	MF 7-GF-200-KPR	109
FCH 325	-	T Fe 1	T Fe 1	MF 1-GF-M21/C1-250-P	109
FCO 330	-	T Fe1	T Fe1	MF 1-GF-300-P	109
FCH 330	-	T Fe1	T Fe1	MF 1-GF-300-P	111
FCH 335	-	T Fe1	T Fe1	MF 1-GF-350-P	111
FCH 340	-	T Fe1	T Fe1	MF 1-GF-400-P	111
FCH 355	-	T Z Fe2	T Z Fe2	MF 1-GF-55-P	111
FCO 356	-	T Fe8	T Fe8	MF 6-GF-55-PT	111

*This standard is no longer valid. Added for informational purposes.

FLUX CORED ARC WELDING WIRES

Hardfacing Flux Cored Wires

Product Name	AWS / ASME SFA - 5.21	EN ISO 14700-A	TS EN ISO 14700-A	DIN 8555*	Page Number
FCH 356	-	T Z Fe8	T Z Fe8	MF 6-GF-55-PT	113
FCH 360	-	T Fe8	T Fe8	MF 6-GF-60-GPT	113
FCH 361	-	T Fe8	T Fe8	MF 6-GF-60-GP	113
FCO 370	-	T Fe6	T Fe6	MF 6-GF-60-GP	113
FCH 371	-	T Z Fe8	T Z Fe8	MF 6-GF-60-GP	113
FCH 373	-	T Z Fe8	T Z Fe8	MF 6-GF-60-GP	115
FCO 415	-	T Fe7	T Fe7	MF 5-GF-45-C	115
FCH 415	-	T Fe7	T Fe7	MF 5-GF-45-C	115
FCO 510	-	~T Fe14	~T Fe14	MF 10-GF-60-CGRZ	115
FCO 512	-	~T Fe14	~T Fe14	MF 10-GF-65-GR	115
FCO 514	-	~T Fe14	~T Fe14	MF 10-GF-65-GR	117
FCO 528	-	~T Fe15	~T Fe15	MF 10-GF-65-GR	117
FCO 532	-	~T Fe15	~T Fe15	MF 10-GF-65-GR	117
FCO 540	-	T Fe16	T Fe16	MF 10-GF-65-GRZ	117
FCH 801	ERCCoCr-C	T Co3	T Co3	MF 20-GF-55-CGTZ	117
FCH 806	ERCCoCr-A	T Co2	T Co2	MF 20-GF-40-CTZ	119
FCH 812	ERCCoCr-B	T Co3	T Co3	MF 20-GF-45-CTZ	119

*This standard is no longer valid. Added for informational purposes.





Hardfacing SAW Wires

Product Name	EN ISO 14700-A	TS EN ISO 14700-A	DIN 8555*	Page Number
FCS 335	T Fe1	T Fe1	UP 1-GF-350-P	121
FCS 345	~T Fe1	~T Fe1	UP 1-GF-45-P	121
FCS 355	T Fe3	T Fe3	UP 6-GF-55-P	121
FCS 356	T Fe3	T Fe3	UP 6-GF-55-PT	121
FCS 415	T Fe7	T Fe7	UP 5-GF-40-(45)-C	121
FCS 417	~T Fe7	~T Fe7	UP 5-GF-45-(50)-C	123
FCS 420	~T Fe7	~T Fe7	UP 6-GF-50-C	123
FCS 421	~T Fe7	~T Fe7	UP 6 GF-50-(55)-C	123
FCS 430	~T Fe7	~T Fe7	UP 5-GF-200-C	123

*This standard is no longer valid. Added for informational purposes.

FLUX CORED ARC WELDING WIRES

Unalloyed Steel Flux Cored Welding Wires

Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>FCW 11</p> <p>AWS/ASME SFA - 5.20 E71T-1C EN ISO 17632-A T46 2 P C 1 TS EN ISO 17632-A T46 2 P C 1</p>	<p>Rutile type flux cored wire with fast-freezing slag. Especially designed for welding with CO₂ (carbondioxide) gas, in shipbuilding and steel construction. Owing to its easily controllable weld pool, electrode is well suited for positional welding with higher currents, resulting in increased deposition rates. Particularly suited for welding in the horizontal-vertical position, e.g. in tank welding. Electrode of 1.20 mm in diameter is also suitable for vertical-down welding. Low spatter loss, easy slag removal, finely ripped pore-free welds blending into base metal without undercut.</p>	 
<p>FCW 11A</p> <p>AWS/ASME SFA - 5.20 E71T-1C H4 EN ISO 17632-A T46 2 P C 1 H5 TS EN ISO 17632-A T46 2 P C 1 H5</p>	<p>Rutile type flux cored wire with fast-freezing slag. Especially designed for welding with CO₂ (carbondioxide) gas, in shipbuilding and steel construction. Owing to its easily controllable weld pool, electrode is well suited for positional welding with higher currents, resulting in increased deposition rates. Its special vacuum packing provides low diffusible hydrojen level in weld metal, in the case of proper handling and storage conditions. Electrode of 1.20 mm in diameter is also suitable for vertical-down welding. Low spatter loss, easy slag removal in the fillet and narrow grooves, finely ripped pore-free welds blending into base metal without undercut.</p>	 
<p>FCW 12</p> <p>AWS/ASME SFA - 5.20 E71T1-M EN ISO 17632-A T46 2 P M 1 TS EN ISO 17632-A T46 2 P M 1</p>	<p>Rutile type flux cored wire, especially designed for welding in steel construction, piping, machine fabrication and shipbuilding by using mix shielding gas. Owing to it's easily controllab- le weld pool and fast freezing slag particularly suited for welding in all position. Good gap-brid- ging property, low spatter loss, easy slag removal even in narrow grooves. Finely ripped pore-free welds blending into base metal without undercut.</p>	 
<p>FCW 13</p> <p>AWS/ASME SFA 5.20 E71T-1M AWS/ASME SFA 5.20 E71T-1C EN ISO 17632 - A T46 2 P C 1 H5 TS EN ISO 17632 - A T46 2 P C 1 H5 EN ISO 17632 - A T46 3 P M 1 H5 TS EN ISO 17632 - A T46 3 P M 1 H5</p>	<p>Rutile type flux cored wire, designed for welding in steel construction, piping, machine fabricati- on and shipbuilding by using M21-mix gas and CO₂ shielding gas. Owing to it's easily controllab- le weld pool and fast freezing slag particularly suited for welding in all position. Welding in all-position is easy with a wide parameter range, especially when using mixed gas. Good gap-bridging property, low spatter loss, easy slag removal even in narrow grooves. Finely ripped pore-free welds blending into base metal without undercut.</p>	 
<p>FCW 14</p> <p>AWS/ASME SFA - 5.20 E71T-1C EN ISO 17632 - A T46 2 P C 1 TS EN ISO 17632 - A T46 2 P C 1</p>	<p>Rutile type flux cored wire with very fast-freezing slag. Especially designed for welding with CO₂ (carbondioxide) gas, in shipbuilding and steel construction. Suitable to use in lower currents and there is no spatter in 20-24V. Owing to it's very easily controllable weld pool, electrode is well suited for positional welding with higher currents, resulting in increased deposition rates. Particularly suited for welding in the horizontal-vertical position, e.g. in tank welding. Electrode of 1.20 mm in diameter is also suitable for vertical-down welding. Low spatter loss, easy slag removal, finely ripped pore-free welds blending into base metal without undercut.</p>	 

Typical Chemical Analysis of All-Weld Metal (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Shielding Gas	Diameter (mm)	Packing Weight (kg) Packing Type
C: 0.04							
Si: 0.40	500	560	25	-20°C: 70	C1 (%100 CO ₂)	1.00 1.20 1.60 2.40	5 kg - D200 (Vacuum) 15 kg - D300 (Vacuum)
Mn: 1.50							
C: 0.04							
Si: 0.40	500	560	25	-20°C: 70	C1 (%100 CO ₂)	1.00 1.20	5 kg - D200 (Vacuum) 15 kg - D300 (Vacuum)
Mn: 1.50							
C: 0.05							
Si: 0.45	480	550	28	-20°C: 100	M21 (Ar + %15-25 CO ₂)	1.00 1.20 1.60	5 kg - D200 (Vacuum) 15 kg - D300 (Vacuum)
Mn: 1.45							
With C1 Shielding Gas							
C: 0.06	470	540	28	-30°C: 50 -20°C: 100	C1 (%100 CO ₂)	1.00 1.20 1.60	5 kg - D200 (Vacuum) 15 kg - D300 (Vacuum)
Si: 0.50							
Mn: 1.15							
With M21 Shielding Gas							
C: 0.06	530	620	25	-20°C: 100 -30°C: 80	M21 (Ar + %15-25 CO ₂)	1.00 1.20 1.60	5 kg - D200 (Vacuum) 15 kg - D300 (Vacuum)
Si: 0.60							
Mn: 1.40							
C: 0.05							
Si: 0.60	520	600	25	-20°C: 70	C1 (%100 CO ₂)	1.20 1.60	5 kg - D200 (Vacuum) 15 kg - D300 (Vacuum)
Mn: 1.50							

FLUX CORED ARC WELDING WIRES











Unalloyed Steel Flux Cored Welding Wires

Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>FCW 16</p> <p>AWS/ASME SFA - 5.20 E71T-1CJ AWS/ASME SFA - 5.20 E71T-9CJ EN ISO 17632-A T46 4 P C 1 TS EN ISO 17632-A T46 4 P C 1</p>	<p>Rutile type flux cored wire, which has high strength and designed for welding in all position. Suitable for welding fine grained structural steels and high strength shipbuilding steels in all position, where low heat input and less deformation are required. Has a stable and quite arc. Good gap-bridging property, low spatter loss, easy slag removal even in narrow grooves. Finely ripped pore-free welds blending into base metal without undercut.</p>	 
<p>FCW 17</p> <p>AWS/ASME SFA - 5.20 E71T-1MJ AWS/ASME SFA - 5.20 E71T-9MJ AWS/ASME SFA - 5.20 E71T-12MJ EN ISO 17632-A T46 4 P M 1 H5 TS EN ISO 17632-A T46 4 P M 1 H5</p>	<p>Rutile type flux cored wire, designed for welding applications which required good toughness values down to -40°C service temperatures, in steel construction, piping, machine fabrication, shipbuilding and especially offshore structures. Used with M21 mix shielding gas. Owing to its easily controllable weld pool and fast freezing slag particularly suited for welding in all position. Good gap-bridging property in thick sections, has low spatter loss, finely ripped pore-free welds blending into base metal without undercut. Easy slag removal even in fillet and narrow grooves.</p>	 
<p>FCW 21</p> <p>AWS/ASME SFA - 5.18 E70C-6M H4 EN ISO 17632-A T46 4 M M 2 H5 TS EN ISO 17632-A T46 4 M M 2 H5</p>	<p>Slagless metal powder cored electrode with outstanding welding properties in the short-arc and spray arc range. Almost spatter-free when welding in the spray-arc range with mixed gas. Good restriking, even with cold wire tip, thus being suitable for robot application. Characteristic features high deposition rate and welding speed, good side wall fusion, finely rippled welds, without undercutting into the base metal, not even on contaminated or corroded metal surfaces. Weldmetal has a little formation of silicates on surface, so that multi-pass welds can be made without cleaning. FCW 21 is well-suited for root-and positional welding and gap bridging, due to it's easily controlable weld pool in the short-arc range.</p>	 
<p>FCW 30</p> <p>AWS/ASME SFA-5.20 E70T-5M H4 AWS/ASME SFA-5.20 E70T-5C H4 EN ISO 17632-A T42 4 B M 3 H5 TS EN ISO 17632-A T42 4 B M 3 H5 EN ISO 17632-A T42 4 B C 3 H5 TS EN ISO 17632-A T42 4 B C 3 H5</p>	<p>Basic type flux cored wire for welding thick steel sections and dynamically loaded structures, where high toughness is required. Provides high mechanical properties and high crack resistant weld metal. Suitable to welding of boiler, tank, pressure vessel, heavy machine production and heavy constructions. Weld are metallurgically clean and are of X-ray quality. Suitable for welding high carbon steels and buffer application on worn parts before hardfacing.</p>	 
<p>FCO 90</p> <p>AWS/ASME SFA - 5.20 E71T-GS</p>	<p>Self-shielded (open-arc) flux cored wire, suitable for welding in all position. Used in outdoor welding of construction, iron-works, roof assembly jobs, repair welds in agricultural equipment and vehicles. Suitable for single pass welding in lap and butt joints of thin plates. Has a stable arc, easily controllable weld pool and easy slag removal.</p>	 

Typical Chemical Analysis of All-Weld Metal (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Shielding Gas	Diameter (mm)	Packing Weight (kg) Packing Type
C: 0.05							
Si: 0.30	510	580	27	-40°C: 70	C1 (%100 CO ₂)	1.00	5 kg - D200 (Vacuum) 15 kg - D300 (Vacuum)
Mn: 1.45						1.20	
Ni: 0.40						1.60	
C: 0.05							
Si: 0.50	520	580	28	-30°C: 100 -40°C: 80	M21 (Ar + %15-25 CO ₂)	1,2	5 kg - D200 (Vacuum) 15 kg - D300 (Vacuum)
Mn: 1.40							
Ni: 0.40							
C: 0.06							
Si: 0.60	500	580	25	-20°C: 100 -40°C: 80	M21 (Ar + %15-25 CO ₂)	1.00	5 kg - D200 15 kg - D300 250 kg - Drum
Mn: 1.60						1.20	
						1.40	
With M21 Shielding Gas							
C: 0.04	510	600	25	-40°C: 90	C1 (%100 CO ₂)	1.00	15 kg - D300 (Vacuum)
Si: 0.60						1.20	
Mn: 1.50						1.60	
With C1 Shielding Gas							
C: 0.04	450	520	29	-40°C: 100	M21 (Ar + %15-25 CO ₂)	2.40	
Si: 0.50							
Mn: 1.45							
C: 0.12							
Si: 0.20	490	600	20	-	-	0.80	1 kg - D100 5 kg - D200 15 kg - K300 MS
Mn: 0.80						0.90	
Al: 1.20						1.00	

FLUX CORED ARC WELDING WIRES


Low Alloyed, High Strength and Creep Resistant Steel Flux Cored Welding Wires

Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>FCW 140</p> <p>AWS/ASME SFA - 5.29 E81T1-Ni1C EN ISO 17632-A T46 4 1Ni P C 1 TS EN ISO 17632-A T46 4 1Ni P C 1</p>	<p>Rutile type flux cored wire, designed for welding fine grained structural steels. Successfully used in single and multi-run welding of especially in steel construction, bridge, offshore platform, shipbuilding and pipe laying. Owing to it's easily controllable weld pool and fast freezing slag suited for welding in all position easily. It's metal recovery provides ability of good gap bridging and filling property. Due to it's nickel content, weld metal has high yield and tensile strengths, therefore suitable to use weld fine grained structural steels at operating temperatures down to -40°C. Diffusible hydrogen content is 5 ml per 100 g deposited weld metal, so highly resistant to cold cracking. Has a stable and quite arc with low spatter loss. Has easily removable slag, generally self removed.</p>	 
<p>FCW 142</p> <p>AWS/ASME SFA - 5.29 E81T1-Ni1M EN ISO 17632 - A T46 4 1Ni P M 1 H5 TS EN ISO 17632 - A T46 4 1Ni P M 1 H5</p>	<p>Rutile type flux cored wire, designed for welding fine grained structural steels by using M21 mix shielding gas. Successfully used in single and multi-run welding in steel construction, bridge, offshore platform, shipbuilding and pipe laying. Owing to it's easily controllable weld pool and fast freezing slag, suited for welding in all position easily. It's metal recovery provides ability of good gap bridging and filling property. Because of nickel alloy, weld metal yield and tensile strength is high and weld metal is proper to use on fine grained steels at operating temperatures 450°C down to -40°C. Diffusible hydrogen content is 5 ml per 100 g deposited weld metal, so highly resistant to cold cracking. Has a stable and quite arc with low spatter loss. Has easily removable slag and generally self removed.</p>	 
<p>FCW 150W</p> <p>AWS/ASME SFA-5.29 E81T1-W2C EN ISO 17632-B T553T1-1C A-NCC1 TS EN ISO 17632-B T553T1-1C A-NCC1</p>	<p>Rutile type flux cored wire, which is especially designed for welding weathering steels (like COR-TEN steels), high strength and fine grained structural steels. Suitable for welding in steel construction in single and multi-run welding in all position. Owing to it's easily controllable weld pool and fast freezing slag particularly suited for welding in all position. Has a stable and quite arc with low spatter loss.</p>	 
<p>FCW 171</p> <p>AWS/ASME SFA-5.29 E81T-1 Ni2 C J EN ISO 17632 - A T50 6 2Ni P C 2 H5 TS EN ISO 17632 - A T50 6 2Ni P C 2 H5</p>	<p>Rutile type flux cored wire, designed for welding fine grained structural steels by using CO2 shielding gas. Successfully used in single and multi-pass welding in steel construction, offshore platform, shipbuilding and pipe laying. Provides weld metal with high toughness, down to -60°C. Diffusible hydrogen content is 5 ml per 100 g deposited weld metal, so highly resistant to cold cracking. Has a stable and quite arc with low spatter loss. Has easily removable slag and generally self removing.</p>	 
<p>FCW 172</p> <p>AWS/ASME SFA-5.29 E81T-1 Ni2 M J EN ISO 17632 - A T50 6 2Ni P M 2 H5 TS EN ISO 17632 - A T50 6 2Ni P M 2 H5</p>	<p>Rutile type flux cored wire, designed for welding fine grained structural steels by using M21 - mix shielding gas. Successfully used in single and multi-pass welding in steel construction, offshore platform, shipbuilding and pipe laying which need high strength and toughness at low temperatures. Provides weld metal with high toughness, down to -60°C. Diffusible hydrogen content is 5 ml per 100 g deposited weld metal, so highly resistant to cold cracking. Has a stable and quite arc without spatter. Has easily removable slag and generally self removing.</p>	 




Typical Chemical Analysis of All-Weld Metal (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Shielding Gas	Diameter (mm)	Packing Weigth (kg) Packing Type
C: 0.04							
Si: 0.40	520	590	25	-40°C: 80	C1 (%100 CO ₂)	1.20	5 kg - D200 (Vacuum)
Mn: 1.30						1.60	15 kg - D300 (Vacuum)
Ni: 1.00							
C: 0.06							
Si: 0.40	500	570	28	-40°C: 100	M21 (Ar + %15-25 CO ₂)	1,20	5 kg - D200 (Vacuum)
Mn: 1.25							15 kg - D300 (Vacuum)
Ni: 1.00							
C: 0.03							
Si: 0.55	550	620	22	-30°C: 30 -20°C: 60	C1 (%100 CO ₂)	1.00	5 kg - D200 (Vacuum)
Mn: 1.25						1.20	15 kg - D300 (Vacuum)
Cr: 0.50						1.60	
Ni: 0.65							
Cu: 0.40							
C: 0.05							
Si: 0.25	540	600	24	-50°C: 85 -60°C: 70	C1 (%100 CO ₂)	1,20	5 kg - D200 (Vacuum)
Mn: 1.10							15 kg - D300 (Vacuum)
Ni: 2.30							
C: 0.05							
Si: 0.20	520	590	26	-50°C: 85 -60°C: 70	M21 (Ar + %15-25 CO ₂)	1,20	5 kg - D200 (Vacuum)
Mn: 1.10							15 kg - D300 (Vacuum)
Ni: 2.20							

FLUX CORED ARC WELDING WIRES

Low Alloyed, High Strength and Creep Resistant Steel Flux Cored Welding Wires

Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>FCW 201</p> <p>AWS/ASME SFA - 5.29 E81T1-A1C EN ISO 17634-A T MoL P C 1 H5 TS EN ISO 17634-A T MoL P C 1 H5</p>	<p>Flux cored wire designed for welding boiler, pipe steels, steam generators and other equipments, subjected to operating temperatures up to 500°C. Suitable to use in all position welding and preferred to use where high mechanical properties and X-ray quality are required.</p>	<p>⊕ </p>

Hardfacing Flux Cored Wires











Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>FCO 250</p> <p>EN 14700 T Fe9 TS EN 14700 T Fe9 DIN 8555 MF 7-GF-200-KPR</p>	<p>Open-arc flux cored wire for the rebuilding and reclamation of heavy parts, made of carbon steels or 14% Mn steels. Due to its high crack resistance, it is successfully used for buffer layer application prior to hardfacing on crack sensitive parts. Weld metal is very resistant to pressure and impact. Machinable with carbide tipped tools.</p> <p>Typical Applications: Rebuilding and reclamation of railway rails and crossovers, mill shaft drive end, buffer layer on gyratory crusher mantles, re-pointing of shovel teeth, buffer layer on crawler tractor link prior to overlaying with more abrasion resistance and crack sensitive materials, rebuilding of rollers made of low alloy steels.</p>	<p>⊕ </p>
<p>FCH 325</p> <p>EN 14700 T Fe1 TS EN 14700 T Fe1 DIN 8555 MF 1-GF-M21-250-P DIN 8555 MF 1-GF-C1-250-P</p>	<p>Gas shielded flux cored wire, which is developed for hardfacing of parts, subjected to metal-to-metal friction wear (adhesion) and impact. The weld metal has medium hardness and machinable by chip forming, hardening is possible by flame or by induction hardening. Due to high toughness and high crack resistance, it is also suitable for buffer layer applications. Interpass temperature should not exceed 250°C, during welding.</p> <p>Typical Applications: Suitable for hardfacing rollers, railway rails and crossings, rolling mills, caterpillar track rolls and pads, gears, sprockets, shafts, crane rollers and mine car wheels.</p>	<p>⊕ </p>
<p>FCO 330</p> <p>EN 14700 T Fe1 TS EN 14700 T Fe1 DIN 8555 MF 1-GF-300-P</p>	<p>Open-arc flux cored wire which is developed for hardfacing of parts subjected to metal-to-metal friction wear (adhesion) and medium degree impacts. Due to its very tough and crack resistant weld metal, it is also used for buffer layer applications. As the weld metal has medium degree of hardness it can be machined by chip forming and flame or inductive hardening is possible. Interpass temperature should not exceed 250°C, during welding.</p> <p>Typical Applications: Hardfacing torque gears, gear wheels, shafts, pallet reels, crane wheels, pulleys, railway rails, crossings and switch points, rollers, caterpillar tracks, sprockets, track links, gears, shafts, pinion gears in sugar industry, screws in oil industry, crane drums and wheels, mine car wheels and sheaves.</p>	<p>⊕ </p>

Typical Chemical Analysis of All-Weld Metal (%)	Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO - V (J)	Shielding Gas	Diameter (mm)	Packing Weigth (kg) Packing Type
C: 0.03							
Si: 0.35	530	600	22	20°C: 90	C1 (%100 CO ₂)	1.20	5 kg - D200 (Vacuum)
Mn: 1.10						1.60	15 kg - D300 (Vacuum)
Mo: 0.40							

Typical Chemical Analysis of All-Weld Metal (%)	Hardness	Shielding Gas	Diameter (mm)	Packing Weigth (kg) Packing Type
C: 0.40	As Welded			
Si: 0.50	200 HB	-	1.60	15 kg - K300MS
Mn: 16.00			2.40	25 kg - K435
Cr: 12.00	After Work Hardening		2.80	200 - 250 kg - Drum
Fe: 71.10	450 HB			
C: 0.09				
Si: 0.60	250 HB	C1 (%100 CO ₂) M21 (Ar + %15-25 CO ₂)	1,60	15 kg - K300MS
Mn: 1.20				200 - 250 kg - Drum
Cr: 0.70				
C: 0.10				
Si: 0.75	300 HB	-	1.60	15 kg - K300MS
Mn: 1.00			2.40	25 kg - K435
Cr: 0.55			2.80	200 - 250 kg - Drum
Mo: 0.40				
Fe: 96.20				

FLUX CORED ARC WELDING WIRES











Hardfacing Flux Cored Wires

Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>FCH 330</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>T Fe1 T Fe1 MF 1-GF-300-P</p>	<p>Gas shielded flux cored wire which is developed for hardfacing of parts subjected to metal-to-metal friction wear (adhesion) and medium degree impacts. Due to its very tough and crack resistant weld metal, it is also used for buffer layer applications. As the weld metal has medium degree of hardness it can be machined by chip forming and flame or inductive hardening is possible. Interpass temperature should not exceed 250°C, during welding.</p> <p>Typical Applications: Hardfacing torque gears, gear wheels, shafts, pallet reels, crane wheels, pulleys, railway rails, crossings and switch points, rollers, caterpillar tracks, sprockets, track links, gears, shafts, pinion gears in sugar industry, screws in oil industry, crane drums and wheels, mine car wheels and sheaves.</p>	 
<p>FCH 335</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>T Fe1 T Fe1 MF 1-GF-350-P</p>	<p>Gas shielded flux cored wire, which is developed for hardfacing of parts, subjected to metal-to-metal friction wear (adhesion) and medium degree impacts. The weld metal is tough and free of cracks and therefore resistant to shocks and impacts. Weld metal is easily machinable by chip forming. Interpass temperature should not exceed 250°C, during welding.</p> <p>Typical Applications: Suitable for hardfacing rollers, railway rails and crossings, rolling mills, caterpillar track rolls and pads, gears, sprockets, shafts, crane rollers and mine car wheels.</p>	 
<p>FCH 340</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>T Fe1 T Fe1 MF 1-GF-400-P</p>	<p>Gas shielded flux cored wire, which is developed for hardfacing of parts, subjected to metal-to-metal friction wear (adhesion) and medium to high degree impacts. Weld metal can be machinable by chip forming by means of carbide tipped tools. Interpass temperature should not exceed 250°C, during welding.</p> <p>Typical Applications: Suitable for hardfacing rollers, idlers, gears, sprockets, shafts, crane rollers and mine car wheels.</p>	 
<p>FCH 355</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>T Z Fe2 T Z Fe2 MF 1-GF-55-P</p>	<p>Gas shielded, high alloyed, flux cored wire designed for hardfacing deposit with high hardness. Particularly suited for wearing parts subjected to metal to metal wear (adhesion) and high impact. Weld metal is tough, free of cracks and therefore resistant to shock and impacts. Weld metal deposit is only machinable by grinding or carbide tipped tools. If the base metal has high carbon and low weldability, a tough buffer layer with FCW 30 is recommended before hardfacing. Heat treatment after hardfacing will decrease as-welded hardness.</p> <p>Typical Applications: Hardfacing of feeding screws, conveyors and machine parts in brick and mining industries.</p>	 
<p>FCO 356</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>T Fe8 T Fe8 MF 6-GF-55-PT</p>	<p>Open-arc flux cored wire, which is developed for hardfacing of parts subjected of impact high compressive stresses and metal-to-metal wear. Provides martensitic weld metal with high hardness. Weld metal can be machined by grinding or by diamond cutting bits. It is recommended to apply a buffer layer with FCW 30 on base metals with high carbon and low weldability, before hardfacing. The deposit is heat treatable and forgeable.</p> <p>Typical Applications: Suitable for hardfacing of rope and cable sheaves, bed knives, steel mill rollers, crane wheels, forging dies.</p>	 

Typical Chemical Analysis of All-Weld Metal (%)	Hardness	Shielding Gas	Diameter (mm)	Packing Weigth (kg) Packing Type
C: 0.20	300 HB	C1 (%100 CO ₂) M21 (Ar + %15-25 CO ₂)	1.20 1.60 2.40	15 kg - K300MS 200 - 250 kg - Drum
Si: 0.50				
Mn: 1.30				
Cr: 1.60				
Fe: 96.40				
C: 0.20	350 HB	C1 (%100 CO ₂) M21 (Ar + %15-25 CO ₂)	1.20 1.60	15 kg - K300MS 200 - 250 kg - Drum
Si: 0.40				
Mn: 1.30				
Cr: 2.00				
Mo: 0.50				
Fe: 95.60	400 HB	M21 (Ar + %15-25 CO ₂)	1.20 1.60	15 kg - K300MS 200 - 250 kg - Drum
C: 0.20				
Si: 0.45				
Mn: 0.25				
Cr: 2.70				
Mo: 0.40	55 HRc	C1 (%100 CO ₂) M21 (Ar + %15-25 CO ₂)	1.20 1.60 2.40	15 kg - K300MS 200 - 250 kg - Drum
Fe: 96.00				
C: 0.40				
Si: 0.75				
Mn: 0.40				
Cr: 4.40	55 HRc	-	1.60 2.40 2.80	15 kg - K300MS 25 kg - K435 200 - 250 kg - Drum
Fe: 94.05				
C: 0.40				
Si: 0.50				
Mn: 1.50				
Cr: 5.70				
Mo: 1.50				
W: 1.30				
Ti: 0.70				
Fe: 88.40				

FLUX CORED ARC WELDING WIRES











Hardfacing Flux Cored Wires

Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>FCH 356</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>T Z Fe8 T Z Fe8 MF 6-GF-55-PT</p>	<p>Gas shielded hardfacing flux cored wire, which is developed for hardfacing of parts, subjected to impact, high compressive stresses and metal-to-metal wear. Provides martensitic weld metal with high hardness. Weld metal can be machined by grinding or by diamond cutting bits. It is recommended to apply a buffer layer with FCW 30 on base metals with high carbon and low weldability, before hardfacing. The deposit is heat treatable and forgeable.</p> <p>Typical Applications: Suitable for hardfacing of rope and cable sheaves, bed knives, steel mill rollers, crane wheels, forging dies.</p>	 
<p>FCH 360</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>T Fe8 T Fe8 MF 6-GF-60-GPT</p>	<p>Gas shielded, high alloyed, flux cored wire designed for hardfacing deposit with high hardness. Especially developed for hardfacing of parts subjected to high metal-to-metal wear and moderate impact. Weld metal can retain its hardness at high temperatures, till 600°C. Weld metal can be grinded and machined by diamond tools. Weld metal is resistant to cracking and shall not be welded more then 3 pass. A tough buffer layer with FCW 30 is recommended before hardfacing, if base metal has high carbon and low weldability. Heat treatment after hardfacing will decrease as-welded hardness.</p> <p>Typical Applications: Hardfacing hot cut offs, shear blades, dies for pressure casting, scraper blades, conveyors, rollers, crusher rolls and worn parts in agricultural equipments.</p>	 
<p>FCH 361</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>T Fe8 T Fe8 MF 6-GF-60-GP</p>	<p>Gas shielded, hardfacing flux cored wire especially developed for hardfacing of parts subjected to high metal-to-metal friction, mineral abrasion and moderate impact. Weld metal can retain it's hardness at high temperatures, till 600°C. Weld metal can be grinded and machined by diamond tools. A tough buffer layer with FCW 30 is recommended before hardfacing, if base metal has high carbon and low weldability. Heat treatment after hardfacing will decrease as-welded hardness.</p> <p>Typical Applications: Hardfacing of ceramic moulds, mixer blades, crushers, earth moving equipments, hot cut-offs, shear blades, dies for pressure casting, scraper blades, conveyors, rollers.</p>	 
<p>FCO 370</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>T Fe6 T Fe6 MF 6-GF-60-GP</p>	<p>Open-arc hardfacing flux cored wire which is resistant to heavy impact, gouging and grinding abrasion together with resistant to cracking. Weld metal deposit composed of a hard martensitic matrix and finely dispersed titanium carbides. Weld metal is machinable by grinding. Maximum deposit thickness depends upon application and procedure used.</p> <p>Typical Applications: Hardfacing of crusher cylinders, crusher hammers and mantels, agricultural tools, asphalt mixer blades, shovel bucket teeth and lips, bulldozer blades, cane knives and shredders, gyratory crusher mantles, bed knives and anvil in the wood pulp industry.</p>	 
<p>FCH 371</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>T Z Fe8 T Z Fe8 MF 6-GF-60-GP</p>	<p>Gas shielded flux cored wire for hardfacing of parts subjected to high metal to metal wear, abrasion and impact. Weld metal can retain it's hardness at high temperatures. The weld metal is resistant to cracking and highly resistant to impact and abrasion. In the case of thick overlays, it is recommended to use FCW 30 for build-up and buffer layers. The weld deposit contains hard phases in the form carbides. Machining is only possible by grinding or hot chip forming.</p> <p>Typical Applications: Hardfacing of roll type crushers, worm conveyors, scraper blades, dipper teeth etc.</p>	 

Typical Chemical Analysis of All-Weld Metal (%)	Hardness	Shielding Gas	Diameter (mm)	Packing Weigth (kg) Packing Type
C: 0.40	55 HRc	M13 (Ar + %0.5-3 O ₂) M21 (Ar + %15-25 CO ₂) C1 (%100 CO ₂)	1,60	15 kg - K300MS 200 - 250 kg - Drum
Si: 0.60				
Mn: 1.10				
Cr: 5.70				
Mo: 1.40				
W: 1.30				
Fe: 88.95				
C: 0.60	59 HRc	C1 (%100 CO ₂) M21 (Ar + %15-25 CO ₂)	1.20	15 kg - K300MS 200 - 250 kg - Drum
Si: 0.50			1.60	
Mn: 0.20			2.40	
Cr: 5.60				
Mo: 0.25				
V: 0.20				
Fe: 92.65				
C: 0.45	59 HRc	C1 (%100 CO ₂) M21 (Ar + %15-25 CO ₂)	1.20	15 kg - K300MS 200 kg - Drum
Si: 3.00			1.60	
Mn: 0.70				
Cr: 9.00				
Fe: 86.85				
C: 1.80	58 HRc	-	1.60	15 kg - K300MS 25 kg - K435 250 kg - Drum
Si: 0.60			2.40	
Mn: 1.00			2.80	
Cr: 7.00				
Mo: 1.30				
V: 0.15				
Fe: 82.15				
C: 0.90	59 HRc	M21 (Ar + %15-25 CO ₂)	1.20	15 kg - K300MS 200 kg - Drum
Si: 1.20			1.60	
Mn: 0.35				
Cr: 5.00				
Nb: 3.50				
Fe: 89.05				

FLUX CORED ARC WELDING WIRES

Hardfacing Flux Cored Wires

Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>FCH 373</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>T Z Fe8 T Z Fe8 MF 6-GF-60-GP</p>	<p>Gas shielded flux cored wire for hardfacing of parts, subjected to high metal to metal wear, abrasion and impact. Weld metal can retain it's hardness under high temperatures. The weld metal is resistant to cracking and also highly resistant to impact and abrasion. When thick hardfacing is necessary, it is recommended to use FCW 30 for build-up layers. The weld deposit contains hard carbides. Machining is possible only by grinding or hot chip forming.</p> <p>Typical Applications: Hardfacing of roll type crushers, worm conveyors, scraper blades, dipper teeth etc.</p>	 
<p>FCO 415</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>T Fe7 T Fe7 MF 5-GF-45-C</p>	<p>Open-arc flux cored wire for hardfacing of parts, subjected to metal to metal wear (adhesion), moderate impact, high thermal fatigue and corrosion at high temperatures. Especially designed for hardfacing and renovation of continuous casting rollers. Ferritic-martensitic weld metal contains Cr, Ni, Mo, V and Nb alloys. Has a very silent arc and provides smooth and easily machinable surface with no spatter. Thin slag is formed on the bead. Provides smooth and machinable surface.</p> <p>Typical Applications: Hardfacing of continuous casting rollers and similar rollers operating at high service temperatures.</p>	 
<p>FCH 415</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>T Fe7 T Fe7 MF 5-GF-45-C</p>	<p>Gas shielded flux cored wire for hardfacing of parts, subjected to metal-to-metal wear (adhesion), moderate impact, creep, thermal fatigue and corrosion at high temperatures. Especially designed for hardfacing and renovation of continuous casting rollers. Ferritic-martensitic weld metal contains Cr, Ni, Mo, V and Nb alloys. Has a very silent arc and provides smooth and easily machinable surface with no spatter.</p> <p>Typical applications: Hardfacing of continuous casting rollers and similar rollers operating at high service temperatures.</p>	 
<p>FCO 510</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>~T Fe14 ~T Fe14 MF 10-GF-60-CGRZ</p>	<p>Open-arc flux cored wire, depositing high chromium alloy designed for resisting high stress grinding abrasion with low impact. Especially used on earth moving equipments contact surfaces with soil and cement raw materials. Weld metal deposit is composed of an austenitic matrix and chromium carbides. Machinable only by grinding.</p> <p>Typical Applications: Hardfacing in wear plates, conveyors, bulldozer buckets and teeth.</p>	 
<p>FCO 512</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>~T Fe14 ~T Fe14 MF 10-GF-65-GR</p>	<p>Open-arc flux cored wire, which is developed for hardfacing of parts, subjected to especially high abrasion and low degree of impact. Weld metal has high hardness due to it's high chromium carbide content and machinable only by grinding. Transverse cracks, caused by high hardness level, do not have any negative effect on the abrasion resistance. Recommend to apply as maximum 3 passes.</p> <p>Typical Applications: Suitable for hardfacing of wear plates, bucket teeth and crusher parts of heavy construction equipments, transport augers, mixer fan blades and crushers which are made of carbon steels, low and high alloy steels or Ni-hard materials.</p>	 

Typical Chemical Analysis of All-Weld Metal (%)	Hardness	Shielding Gas	Diameter (mm)	Packing Weigth (kg) Packing Type
C: 1.35	58 HRc	M21 (Ar + %15-25 CO ₂)	1,60	15 kg - K300MS 250 kg - Drum
Si: 0.85				
Mn: 1.10				
Cr: 7.00				
Ni: 0.90				
Mo: 0.25				
Nb: 9.00				
W: 0.25				
Fe: 79.30				
C: 0.09	45 HRc	-	1.60 2.40	15 kg - K300 MS 25 kg - K435 250 kg - Drum
Si: 0.40				
Mn: 0.70				
Cr: 13.00				
Ni: 4.60				
Mo: 0.70				
Nb: 0.15				
V: 0.20				
Fe: 80.16				
C: 0.09	45 HRc	C1 (%100 CO ₂) M21 (Ar + %15-25 CO ₂)	1.60 2.40	15 kg - K300MS 250 kg - Drum
Si: 0.40				
Mn: 0.70				
Cr: 13.00				
Ni: 4.60				
Mo: 0.70				
Nb: 0.15				
V: 0.20				
Fe: 80.16				
C: 2.50	60 HRc	-	1.60 2.40 2.80	15 kg - K300 MS 25 kg - K435 250 kg - Drum
Si: 1.50				
Mn: 0.15				
Cr: 23.00				
Fe: 72.85				
C: 5.20	63 HRc	-	1.60 2.80	15 kg - K300 MS 25 kg - K435 250 kg - Drum
Si: 1.20				
Mn: 0.20				
Cr: 27.00				
Fe: 66.40				

FLUX CORED ARC WELDING WIRES





Hardfacing Flux Cored Wires

Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>FCO 514</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>~T Fe14 ~T Fe14 MF 10-GF-65-GR</p>	<p>Open-arc flux cored wire which is developed for hardfacing of wear plates and parts, subjected to high abrasion and low impact. Weld metal has high hardness due to its high chromium carbide content and machinable only by grinding. Transverse cracks, caused by high hardness level, do not have any negative effect on the abrasion resistance.</p> <p>Typical Applications: Suitable for hardfacing of wear plates, cement conveyor screws, bucket edge and teeth, crusher parts of heavy construction equipments, catalytic pipes.</p>	
<p>FCO 528</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>~T Fe15 ~T Fe15 MF 10-GF-65-GR</p>	<p>Open-arc flux cored wire which is designed to give extreme resistance to high stress and gouging abrasion and medium impact even at higher temperatures, up to 450°C. Weld metal deposit is composed of an austenitic matrix and Cr and Nb complex carbides so, will readily stress relief check crack which is not detrimental to abrasion resistance, but decrease impact resistance. Hardfacing shall not exceed 8 mm in height. Weld metal is machinable by grinding.</p> <p>Typical Applications: Hardfacing of grinders and presses in cement and brick industries, concrete pump seats, bucket teeth and lips on bucket-wheel excavators in coal and phosphate mines, brick and clay mill augers, wear plates and screens in the coal industry, bulldozer blades working in sand.</p>	
<p>FCO 532</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>~T Fe15 ~T Fe15 MF 10-GF-65-GR</p>	<p>Hardfacing open-arc flux cored wire which is developed for hardfacing of parts subjected to especially high gouging abrasion and low degree impact. Weld metal deposit is composed of an austenitic matrix and Cr and Nb complex carbides so, will readily stress relief check crack which is not detrimental to abrasion resistance, but decrease impact resistance. Weld metal has high hardness and excellent wear resistance even in single pass due to In order to have good results, maximum 2 passes shall be welded.</p> <p>Typical Applications: Suitable for hardfacing of pumps and mixer parts, conveyer screws, bulldozer blades, shovel bucket, lips and teeths, brick and clay mill augers, wear plates and screens in mineral, stone, sand and coal mines.</p>	
<p>FCO 540</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>T Fe16 T Fe16 MF 10-GF-65-GRZ</p>	<p>Open-arc flux cored wire, designed to resist high stress grinding abrasion and solid erosion at service temperatures up to 600°C. Deposits weld metal which contains Cr, Nb, Mo alloys with addition of W and V carbides. Hardfacing shall not exceed 6 mm in height. Weld metal is machinable by grinding. The deposit will readily stress relief check crack which is not detrimental to abrasion resistance.</p> <p>Typical Applications: Hardfacing wear plates, sinter plant parts, exhaust fan blades in pellet plants, pearlite crushers, bucket teeth and lips on bucket-wheel excavators in phosphate mines, boiler fan blades in sugar cane industry, burden area in blast furnace bells, wear plates in blast furnace bell's top charging systems.</p>	
<p>FCH 801</p> <p>AWS/ASME SFA 5.21 EN 14700 TS EN 14700 DIN 8555</p> <p>ERCCoCr-C T Co3 T Co3 MF 20-GF-55-CGTZ</p>	<p>Gas shielded, flux cored hardfacing wire which deposits Co-Cr-W alloy weld metal. Suitable to use in hardfacing of parts subjected to either the single or combined effect of heavy metal-to-metal wear or abrasion, high temperatures (ranging from 500°C to 900°C) and corrosive environments. Due to its very high toughness and shock resistance, also suitable to use on parts subjected to high impacts and thermal shocks.</p> <p>Typical Applications: Hardfacing of plastic extrusion screws, tools to cut paper, cardboard floor coverings, roofing, wood.</p>	

Typical Chemical Analysis of All-Weld Metal (%)	Hardness	Shielding Gas	Diameter (mm)	Packing Weigth (kg) Packing Type
C: 5.30	62 HRc	-	1.60 2.80	15 kg - K300 MS 25 kg - K435 250 kg - Drum
Si: 0.80				
Mn: 0.25				
Cr: 27.50				
B: 0.50				
Fe: 65.65				
C: 5.20	65 HRc	-	1.60 2.40 2.80	15 kg - K300 MS 25 kg - K435 250 kg - Drum
Si: 0.90				
Mn: 0.20				
Cr: 21.00				
Nb: 7.00				
Fe: 65.70				
C: 5.20	One Pass 65 HRc	-	1.60 2.40 2.80	15 kg - K300 MS 25 kg - K435 250 kg - Drum
Si: 0.90				
Mn: 0.20				
Cr: 21.00				
Nb: 7.00				
B: 1.00				
Fe: 64.70				
C: 5.00	64 HRc	-	1.60 2.40 2.80	15 kg - K300 MS 25 kg - K435 250 kg - Drum
Si: 0.55				
Mn: 0.20				
Cr: 22.00				
Mo: 6.40				
Nb: 6.00				
V: 0.70				
W: 1.60				
Fe: 57.55				
C: 2.50	55 HRc	M13 (Ar + %0.5-3 O ₂)	1.20 1.60	15 kg - K300 MS
Si: 1.00				
Mn: 0.50				
Ni: 2.00				
Cr: 30.00				
W: 11.00				
Fe: 3.50				
Co: 49.50				

FLUX CORED ARC WELDING WIRES






Hardfacing Flux Cored Wires

Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>FCH 806</p> <p>AWS/ASME SFA 5.21 EN 14700 TS EN 14700 DIN 8555</p> <p>ERCCoCr-A T Co2 T Co2 MF 20-GF-40-CTZ</p>	<p>Gas shielded, flux cored hardfacing wire which deposits Co-Cr-W alloy weld metal. Suitable to use in hardfacing of parts subjected to either the single or combined effect of: heavy metal-to-metal wear or abrasion, high temperatures (ranging from 500°C to 900°C) and corrosive environments. Due to its very high toughness and shock resistance, also suitable to use on parts subjected to high impacts and thermal shocks.</p> <p>Typical Applications: Hardfacing of blades for hot shearing, ingot tong ends, valves and valve seats, nozzles.</p>	 
<p>FCH 812</p> <p>AWS/ASME SFA 5.21 EN 14700 TS EN 14700 DIN 8555</p> <p>ERCCoCr-B T Co3 T Co3 MF 20-GF-45-CTZ</p>	<p>Gas shielded, flux cored hardfacing wire which deposits Co-Cr-W alloy weld metal. Suitable to use in hardfacing of parts subjected to either the single or combined effect of: heavy metal-to-metal wear or abrasion, high temperatures (ranging from 500°C to 900°C) and corrosive environments. Due to its very high toughness and shock resistance, also suitable to use on parts subjected to high impacts and thermal shocks.</p> <p>Typical Applications: Hardfacing of plastic extrusion screws, plastic, paper and wood cutting tools, saw blades and camshafts.</p>	 

Typical Chemical Analysis of All-Weld Metal (%)	Hardness	Shielding Gas	Diameter (mm)	Packing Weigth (kg) Packing Type
C: 1.20	42 HRc	M13 (Ar + %0.5-3 O ₂)	1.20 1.60 2.40	15 kg - K300 MS
Si: 1.00				
Mn: 0.80				
Ni: 2.50				
Cr: 28.00				
W: 4.50				
Fe: 3.50				
Co: 58.50				
C: 1.50	47 HRc	M13 (Ar + %0.5-3 O ₂)	1,2	15 kg - K300 MS
Si: 1.00				
Mn: 1.00				
Ni: 2.50				
Cr: 30.00				
W: 8.00				
Fe: 3.00				
Co: 53.00				

FLUX CORED ARC WELDING WIRES









Hardfacing SAW Flux Cored Wires

Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>FCS 335</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>T Fe1 T Fe1 UP 1-GF-350-P</p>	<p>Flux cored wire for submerged arc hardfacing of parts subjected to metal-to-metal friction wear (adhesion) and medium degree impacts. SHF 604 flux is used together with this wire for hardfacing applications. Weld metal is easily machinable by chip forming. Interpass temperature should not exceed 250°C, during welding.</p> <p>Typical Applications: Suitable for hardfacing rollers, railway rails and crossings, rolling mills, caterpillar track rolls and tracks, sprockets, shafts, crane rollers and idler and mine car wheels.</p>	
<p>FCS 345</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>~T Fe1 ~T Fe1 UP 1-GF-45-P</p>	<p>Flux cored wire for submerged arc hardfacing of parts subjected to metal-to-metal friction (adhesion) and medium degree impacts. SHF 604 flux is used together with this wire for hardfacing applications. Weld metal is easily machinable by chip forming. Interpass temperature should not exceed 250°C, during welding.</p> <p>Typical Applications: Suitable for hardfacing rollers, rolling mills, caterpillar track rolls and tracks, sprockets, shafts, crane rollers and idler and mine car wheels.</p>	
<p>FCS 355</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>T Fe3 T Fe3 UP 6-GF-55-P</p>	<p>Flux cored wire for submerged arc hardfacing of parts subjected to low stress abrasion with high compression stress and high impact. SHF 604 flux is the proper flux for hardfacing applications. Due to its high hardness weld metal is only machinable by grinding or carbide tipped tools.</p> <p>Typical Applications: Hardfacing of steel mill rolls, crane wheels, cable sheaves.</p>	
<p>FCS 356</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>T Fe3 T Fe3 UP 6-GF-55-PT</p>	<p>Flux cored wire for submerged arc welding, which is developed for hardfacing of parts subjected of impact high compressive stresses and metal-to-metal wear. Provides martensitic weld metal with high hardness. Weld metal can be machined by grinding or by diamond cutting bits. It is recommended to apply a buffer layer on base metals with high carbon and low weldability, before hardfacing. The deposit is heat treatable and forgeable.</p> <p>Typical Applications: Suitable for hardfacing of rope and cable sheaves, bed knives, steel mill rollers, crane wheels, forging dies.</p>	
<p>FCS 415</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>T Fe7 T Fe7 UP 5-GF-40 (45)-C</p>	<p>Flux cored wire for hardfacing of parts subjected to metal-to-metal wear (adhesion), moderate impact, creep, thermal fatigue and corrosion at high temperatures. Especially designed for hardfacing and renovation of continuous casting rollers. SHF 604 is the suitable flux for these hardfacing applications. Ferritic-martensitic weld metal contains Cr, Ni, Mo, V and Nb alloys. Provides smooth and easily machinable surface on stringer weld bead or weaving technique.</p> <p>Typical Applications: Hardfacing of continuous casting rollers and similar rollers operating at high service temperatures.</p>	

Typical Chemical Analysis of All-Weld Metal (%)	Welding Flux	Hardness	Diameter (mm)	Packing Weigth (kg) Packing Type
C: 0.09	SHF 604	350 HB	2.40 3.20	25 kg - K435 250 kg - Drum
Si: 0.50				
Mn: 1.50				
Cr: 2.90				
Mo: 0.50				
Fe: 94.51				
C: 0.20	SHF 604	450 HB	2.40 3.20	25 kg - K435 250 kg - Drum
Si: 0.70				
Mn: 1.75				
Cr: 3.60				
Mo: 0.60				
Fe: 93.15				
C: 0.30	SHF 604	55 HRc	1.60 2.40	25 kg - K435 250 kg - Drum
Si: 0.90				
Mn: 0.95				
Cr: 3.80				
Fe: 94.05				
C: 0.45	SHF 604	55 HRc	2.40 2.80	25 kg - K435 250 kg - Drum
Si: 0.40				
Mn: 1.25				
Cr: 5.80				
Mo: 1.60				
W: 1.60				
Fe: 88.90				
C: 0.08	SHF 604	42 HRc	2.40 3.20	25 kg - K435 250 kg - Drum
Si: 0.70				
Mn: 1.00				
Cr: 13.00				
Ni: 2.70				
Mo: 1.00				
Nb: 0.20				
V: 0.25				
Fe: 81.07				

FLUX CORED ARC WELDING WIRES

Hardfacing SAW Flux Cored Wires

Product Name and Standards	Applications and Properties	Polarity Welding Positions
<p>FCS 417</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>~T Fe7 ~T Fe7 UP 5-GF-45-(50)-C</p>	<p>Flux cored wire for hardfacing of parts subjected to metal-to-metal wear (adhesion), moderate impact, creep, thermal fatigue and corrosion at high temperatures. Especially designed for hardfacing and renovation of continuous casting rollers, where high hardness is required. SHF 604 is the suitable flux for these hardfacing applications. Ferritic-martensitic weld metal has higher level of hardness with respect to FCS 415 and weld metal contains Cr, Ni, Mo, V and Nb alloys. Provides smooth and easily machinable surface on stringer weld bead or weaving technique.</p> <p>Typical Applications: Hardfacing of continuous casting rollers and similar rollers operating at high service temperatures.</p>	 
<p>FCS 420</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>~T Fe7 ~T Fe7 UP 6-GF-50-C</p>	<p>Flux cored wire for submerged arc hardfacing of parts subjected to metal-to-metal wear (adhesion), moderate impact, thermal fatigue and corrosion at high temperatures. Especially designed for hardfacing and renovation of continuous casting rolls. SHF 604 flux is used together with this wire for hardfacing applications. Provides smooth and easily machinable surface on stringer weld bead or weaving technique.</p> <p>Typical Applications: Suitable for hardfacing of rolling rolls which are subjected to high operating temperatures and corrosion and rolls working on similar conditions in iron and steel works. Steel mill rollers, continuous casting rollers.</p>	 
<p>FCS 421</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>~T Fe7 ~T Fe7 UP 6-GF-50-(55)-C</p>	<p>Flux cored wire for submerged arc hardfacing of parts subjected to metal-to-metal wear (adhesion), moderate impact, thermal fatigue and corrosion at high temperatures. Especially designed for hardfacing and renovation of rolling rolls. SHF 604 flux is used together with this wire for hardfacing applications. Has higher level of hardness with respect to FCS 420. Provides smooth and easily machinable surface on stringer weld bead or weaving technique.</p> <p>Typical Applications: Suitable for hardfacing of rolling rolls which are subjected to high operating temperatures and corrosion and rolls working on similar conditions in iron and steel works. Steel mill rollers, continuous casting rollers.</p>	 
<p>FCS 430</p> <p>EN 14700 TS EN 14700 DIN 8555</p> <p>~T Fe7 ~T Fe7 UP 5-GF-200-C</p>	<p>Flux cored wire for submerged arc hardfacing and buffer layer application on parts subjected to metal-to-metal wear (adhesion), moderate impact, thermal fatigue and corrosion at high temperatures. Especially designed to be used as a buffer layer in new continuous casting rollers, before hardfacing, in order to reduce dilution and crack susceptibility. SHF 604 is the suitable flux for these hardfacing applications. Provides smooth and easily machinable surface on stringer weld bead or weaving technique.</p> <p>Typical Applications: Suitable for buffer layer in new continuous casting rolls, before hardfacing layers.</p>	 

Typical Chemical Analysis of All-Weld Metal (%)	Welding Flux	Hardness	Diameter (mm)	Packing Weigth (kg) Packing Type
C: 0.12	SHF 604	47 HRc	2.40 3.20	25 kg - K435 250 kg - Drum
Si: 0.80				
Mn: 1.10				
Cr: 13.00				
Ni: 3.00				
Mo: 1.00				
Nb: 0.25				
V: 0.25				
Fe: 81.07				
C: 0.20	SHF 604	50 HRc	2.40	25 kg - K435 250 kg - Drum
Si: 0.70				
Mn: 1.40				
Cr: 13.00				
Ni: 0.30				
Nb: 0.30				
Fe: 84.10				
C: 0.25	SHF 604	52 HRc	1.60 2.40 3.20	25 kg - K435 250 kg - Drum
Si: 0.80				
Mn: 1.30				
Cr: 13.00				
Ni: 0.35				
Nb: 0.30				
Fe: 84.00				
C: 0.03	SHF 604	200 HB	2.40 3.20	25 kg - K435 250 kg - Drum
Si: 0.70				
Mn: 1.30				
Cr: 17.00				
Fe: 80.97				

SUBMERGED ARC WELDING (SAW) WIRES AND FLUXES

SUBMERGED ARC WELDING (SAW) WIRES AND FLUXES

Unalloyed and Low-Alloyed Steel SAW Wires

Product Name	AWS/ASME SFA - 5.17/ 5.23	EN ISO 14171-A	TS EN ISO 14171-A	Page Number
SW 701	EL12	S1	S1	127
SW 702	EM12	S2	S2	128
SW 702Si	EM12K	S2Si	S2Si	129
SW 703Si	EH12K	S3Si	S3Si	130
SW 702Mo	EA2	S2Mo	S2Mo	131

Unalloyed and Low-Alloyed Steel SAW Fluxes

Product Name	EN ISO 14174	TS EN ISO 14174	Page Number
SF 104	S A AB 1	S A AB 1	132
SF 113	S A MS/CS 1	S A MS/CS 1	133
SF 124	S A AB 1	S A AB 1	134
SF 134	S A AB 1	S A AB 1	135
SF 204	S A AB 1	S A AB 1	136
SF 212	S A AR 1	S A AR 1	137
SF 304	S A AB 1	S A AB 1	138
SF 401	S A FB 1	S A FB 1	139
SF 414	S A AB 1	S A AB 1	140

Stainless Steel SAW Wires

Product Name	AWS / ASME SFA - 5.9	EN ISO 14343-A	TS EN ISO 14343-A	Page Number
SI 307	~ER307	S 18 8 Mn	S 18 8 Mn	141
SI 308L	ER308L	S 19 9 L	S 19 9 L	142
SI 309L	ER309L	S 23 12 L	S 23 12 L	143
SI 316L	ER316L	S 19 12 3 L	S 19 12 3 L	144
SI 347	ER347	S 19 9 Nb	S 19 9 Nb	145
SI 2209	ER2209	S 22 9 3 N L	S 22 9 3 N L	146

SUBMERGED ARC WELDING (SAW) WIRES AND FLUXES

Stainless Steel SAW Fluxes


Product Name	EN ISO 14174	TS EN ISO 14174	Page Number
SIF 501	S A FB 2 DC	S A FB 2 DC	147
SIF 502	S A CS 2 Cr DC	S A CS 2 Cr DC	148

Hardfacing SAW Fluxes

Product Name	EN ISO 14174	TS EN ISO 14174	Page Number
SHF 325	S A CS 3	S A CS 3	149
SHF 333	S A FB 3	S A FB 3	149
SHF 335	S A CS 3	S A CS 3	149
SHF 345	S A CS 3	S A CS 3	149
SHF 604	S A AB 1	S A AB 1	151

SUBMERGED ARC WELDING (SAW) WIRES AND FLUXES

Unalloyed and Low-Alloyed Steel SAW Wires

Product Name and Standards	Applications and Properties	Polarity Welding Positions
SW 701 AWS/ASME SFA - 5.17 EL 12 EN ISO 14171-A S1 TS EN ISO 14171-A S1	Solid, submerged arc welding wire, suitable for welding general structural steels, used in pressure vessel, pipe, shipbuilding and steel constructions. Copper coating increases electrical conductivity and resistance against rusting.	


Typical Chemical Analysis of Welding Wire (%)

	C	Si	Mn
SW 701	0.07	0.03	0.55

Welding Flux	Wire and Flux Combination Standards AWS/ASME SFA - 5.17 EN ISO 14171-A TS EN ISO 14171A	Typical Chemical Analysis of All-Weld Metal (%)	Typical Mechanical Properties of All-Weld Metal				Diameter and Packing Info. of Welding Wire	
			Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO-V (J)	Diameter (mm)	Packing Weight (kg) Packing Type
SF 104	F6A2-EL12	C: 0.05	410	480	30	-30°C: 50 -20°C: 85 0°C: 90	1.60 2.00 2.40 2.80 3.20 4.00 5.00	15 kg - K300 (1.60 mm) 25 kg - K435 200 kg - Drum 400 kg - Drum 600 kg - Drum 1000 kg - Drum
	S 38 2 AB S1	Si: 0.25						
	S 38 2 AB S1	Mn: 0.85						
SF 113	F7A2-EL12	C: 0.04	400	500	30	-20°C: 60 0°C: 70	1.60 2.00 2.40 2.80 3.20 4.00 5.00	15 kg - K300 (1.60 mm) 25 kg - K435 200 kg - Drum 400 kg - Drum 600 kg - Drum 1000 kg - Drum
	S 38 2 CS/MS S1	Si: 0.45						
	S 38 2 CS/MS S1	Mn: 1.45						
SF 212	F7AZ-EL12	C: 0.05	460	530	28	0°C: 30 20°C: 60	1.60 2.00 2.40 2.80 3.20 4.00 5.00	15 kg - K300 (1.60 mm) 25 kg - K435 200 kg - Drum 400 kg - Drum 600 kg - Drum 1000 kg - Drum
	S 42 A AR S1	Si: 0.65						
	S 42 A AR S1	Mn: 1.10						
SF 304	F6A0-EL12	C: 0.05	420	490	30	-30°C: 60 -20°C: 80 0°C: 100	1.60 2.00 2.40 2.80 3.20 4.00 5.00	15 kg - K300 (1.60 mm) 25 kg - K435 200 kg - Drum 400 kg - Drum 600 kg - Drum 1000 kg - Drum
	S 38 2 AB S1	Si: 0.25						
	S 38 2 AB S1	Mn: 0.90						

SUBMERGED ARC WELDING (SAW) WIRES AND FLUXES

Unalloyed and Low-Alloyed Steel SAW Wires

Product Name and Standards	Applications and Properties	Polarity Welding Positions
SW 702 AWS/ASME SFA - 5.17 EM 12 EN ISO 14171-A S2 TS EN ISO 14171-A S2	Solid, submerged arc welding wire, suitable for welding general structural steels with medium and high tensile strengths, used in pressure vessel, boiler, pipe, shipbuilding and steel constructions. Also suitable to use in combination with SHF 325, SHF 333, SHF 335 and SHF 345 hardfacing fluxes for hardfacing applications. Copper coating increases electrical conductivity and resistance against rusting.	


Typical Chemical Analysis of Welding Wire (%)

	C	Si	Mn
SW 702	0.09	0.08	1.00

Welding Flux	Wire and Flux Combination Standards AWS/ASME SFA - 5.17 EN ISO 14171-A TS EN ISO 14171A	Typical Chemical Analysis of All-Weld Metal (%)	Typical Mechanical Properties of All-Weld Metal				Diameter and Packing Info. of Welding Wire	
			Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO-V (J)	Diameter (mm)	Packing Weight (kg) Packing Type
SF 104	F7A2-EM12 S 42 2 AB S2 S 42 2 AB S2	C: 0.05 Si: 0.30 Mn: 1.10	420	500	28	-30°C: 45 -20°C: 65		
SF 113	F7A2-EM12 S 42 2 MS/CS S2 S 42 2 MS/CS S2	C: 0.04 Si: 0.40 Mn: 1.80	400	500	30	-20°C: 55 0°C: 65		
SF 124	F7A4-EM12 S 42 2 AB S2 S 42 2 AB S2	C: 0.05 Si: 0.20 Mn: 1.10	430	490	30	-40°C: 40 -20°C: 70		
SF 134	F7A4-EM12 S 42 2 AB S2 S 42 2 AB S2	C: 0.05 Si: 0.45 Mn: 1.45	440	530	30	-40°C: 50 -30°C: 90	1.60 2.00 2.40 3.20 4.00 5.00	15 kg - K300 (1.60 mm) 25 kg - K435 200 kg - Drum 400 kg - Drum 600 kg - Drum 1000 kg - Drum
SF 204	F7A2-EM12 S 42 3 AB S2 S 42 3 AB S2	C: 0.05 Si: 0.40 Mn: 1.40	435	510	30	-40°C: 50 -30°C: 70 -20°C: 90		
SF 212	F7AZ-EM12 S 42 A AR S2 S 42 A AR S2	C: 0.05 Si: 0.70 Mn: 1.35	480	560	28	0°C: 30 20°C: 70		
SF 304	F7A4-EM12 S 42 3 AB S2 S 42 3 AB S2	C: 0.05 Si: 0.25 Mn: 1.25	430	500	29	-40°C: 60 -30°C: 75 -20°C: 110		
SF 414	F7A6-EM12 S 38 5 AB S2 S 38 5 AB S2	C: 0.06 Si: 0.25 Mn: 1.40	410	510	30	-50°C: 65 -40°C: 100 -20°C: 120		

SUBMERGED ARC WELDING (SAW) WIRES AND FLUXES

Unalloyed and Low-Alloyed Steel SAW Wires

Product Name and Standards	Applications and Properties	Polarity Welding Positions
SW 702Si AWS/ASME SFA - 5.17 EM12K EN ISO 14171-A S2Si TS EN ISO 14171-A S2Si	Solid, submerged arc welding wire suitable for welding general structural steels with medium and high tensile strengths, used in pressure vessel, boiler, pipe, shipbuilding and steel constructions. Higher silicon content improves deoxidation of weld pool. Copper coating increases electrical conductivity and resistance against rusting.	


Typical Chemical Analysis of Welding Wire (%)

	C	Si	Mn
SW 702Si	0.09	0.25	1.10

Welding Flux	Wire and Flux Combination Standards AWS/ASME SFA - 5.17 EN ISO 14171-A TS EN ISO 14171A	Typical Chemical Analysis of All-Weld Metal (%)	Typical Mechanical Properties of All-Weld Metal				Diameter and Packing Info. of Welding Wire	
			Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO-V (J)	Diameter (mm)	Packing Weight (kg) Packing Type
SF 104	F7A2-EM12K S 42 2 AB S2Si S 42 2 AB S2Si	C: 0.05 Si: 0.50 Mn: 1.10	425	510	29	-30°C: 40 -20°C: 50 0°C: 80		
SF 113	F7A2-EM12K S 42 2 MS/CS S2Si S 42 2 MS/CS S2Si	C: 0.04 Si: 0.65 Mn: 1.90	450	550	30	-20°C: 50 0°C: 60		
SF 124	F7A4-EM12K S 42 3 AB S2Si S 42 3 AB S2Si	C: 0.05 Si: 0.30 Mn: 1.20	435	500	27	-40°C: 50 -30°C: 70 -20°C: 90		
SF 134	F7A4-EM12K S 42 3 AB S2Si S 42 3 AB S2Si	C: 0.05 Si: 0.60 Mn: 1.60	470	560	29	-40°C: 45 -30°C: 70 -20°C: 90	1.60 2.00	15 kg - K300 (1.60 mm) 25 kg - K435
SF 204	F7A4-EM12K S 42 3 AB S2Si S 42 3 AB S2Si	C: 0.06 Si: 0.55 Mn: 1.35	440	530	29	-40°C: 40 -30°C: 70	2.40 3.20 4.00	100 kg - K785 200 kg - Drum 400 kg - Drum 600 kg - Drum 1000 kg - Drum
SF 212	F7AZ-EM12K S 46 A AR S2Si S 46 A AR S2Si	C: 0.05 Si: 0.80 Mn: 1.40	490	570	28	0°C: 55 20°C: 80		
SF 304	F7A4-EM12K S 42 3 AB S2Si S 42 3 AB S2Si	C: 0.06 Si: 0.45 Mn: 1.40	460	530	28	-40°C: 50 -30°C: 70 -20°C: 90		
SF 401	F7A6-EM12K S 42 5 FB S2Si S 42 5 FB S2Si	C: 0.06 Si: 0.30 Mn: 1.15	425	520	30	-50°C: 70 -40°C: 90 -30°C: 110		
SF 414	F7A6-EM12K S 38 5 AB S2Si S 38 5 AB S2Si	C: 0.07 Si: 0.35 Mn: 1.45	420	520	30	-50°C: 70 -40°C: 110 -20°C: 140		

SUBMERGED ARC WELDING (SAW) WIRES AND FLUXES

Unalloyed and Low-Alloyed Steel SAW Wires

Product Name and Standards	Applications and Properties	Polarity Welding Positions
SW 703Si AWS/ASME SFA - 5.17 EH12K EN ISO 14171-A S3Si TS EN ISO 14171-A S3Si	Solid, submerged arc welding wire suitable for welding general structural steels with medium and high tensile strengths, used in pressure vessel, boiler, pipe, shipbuilding and steel constructions. Higher manganese and silicon content improves deoxidation of weld pool. Copper coating increases electrical conductivity and resistance against rusting.	


Typical Chemical Analysis of Welding Wire (%)

	C	Si	Mn
SW 703Si	0.09	0.30	1.65

Welding Flux	Wire and Flux Combination Standards AWS/ASME SFA - 5.17 EN ISO 14171-A TS EN ISO 14171A	Typical Chemical Analysis of All-Weld Metal (%)	Typical Mechanical Properties of All-Weld Metal				Diameter and Packing Info. of Welding Wire	
			Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO-V (J)	Diameter (mm)	Packing Weight (kg) Packing Type
SF 104	F7A5-EH12K	C: 0.06	470	550	28	-40°C: 60 -30°C: 75 -20°C: 90	1.60 2.00 2.40 3.20 4.00	25 kg - K435 100 kg - K785 600 kg - Drum 1000 kg - Drum
	S 46 4 AB S3Si	Si: 0.45						
	S 46 4 AB S3Si	Mn: 1.55						
SF 124	F7A4-EH12K	C: 0.06	440	550	30	-40°C: 70 -30°C: 90		
	S 42 4 AB S3Si	Si: 0.45						
	S 42 4 AB S3Si	Mn: 1.75						
SF 134	F7A5-EH12K	C: 0.07	475	575	30	-50°C: 50 -40°C: 70 -30°C: 100		
	S 46 4 AB S3Si	Si: 0.60						
	S 46 4 AB S3Si	Mn: 1.70						
SF 204	F7A4-EH12K	C: 0.06	510	610	28	-40°C: 60 -30°C: 100 -20°C: 120		
	S 46 3 AB S3Si	Si: 0.60						
	S 46 3 AB S3Si	Mn: 1.70						
SF 212	F8AZ-EH12K	C: 0.05	530	610	26	0°C: 40 20°C: 65		
	S 46 A AR S3Si	Si: 0.95						
	S 46 A AR S3Si	Mn: 1.70						
SF 304	F7A4-EH12K	C: 0.06	480	540	28	-40°C: 55 -30°C: 80 -20°C: 120		
	S 46 4 AB S3Si	Si: 0.65						
	S 46 4 AB S3Si	Mn: 1.75						
SF 401	F7A6-EH12K	C: 0.07	480	530	28	-50°C: 80 -40°C: 100 -30°C: 120		
	S 46 5 FB S3Si	Si: 0.30						
	S 46 5 FB S3Si	Mn: 1.60						
SF 414	F7A8-EH12K	C: 0.06	470	560	30	-60°C: 50 -50°C: 75 -40°C: 120		
	S 46 5 AB S3Si	Si: 0.35						
	S 46 5 AB S3Si	Mn: 1.65						

SUBMERGED ARC WELDING (SAW) WIRES AND FLUXES

Unalloyed and Low-Alloyed Steel SAW Wires

Product Name and Standards	Applications and Properties	Polarity Welding Positions
SW 702Mo AWS/ASME SFA - 5.23 EA2 EN ISO 14171-A S2Mo TS EN ISO 14171-A S2Mo	Mo-alloyed and solid, submerged arc welding wire suitable for welding general structural steels, low alloyed steels with medium and high tensile strengths, used in pressure vessel, boiler, tanks, pipe and heavy steel constructions. Copper coating increases electrical conductivity and resistance against rusting.	




Typical Chemical Analysis of Welding Wire (%)

	C	Si	Mn	Mo
SW 702Mo	0.10	0.15	1.10	0.50

Welding Flux	Wire and Flux Combination Standards AWS/ASME SFA - 5.23 EN ISO 14171-A TS EN ISO 14171A	Typical Chemical Analysis of All-Weld Metal (%)	Typical Mechanical Properties of All-Weld Metal				Diameter and Packing Info. of Welding Wire	
			Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO-V (J)	Diameter (mm)	Packing Weight (kg) Packing Type
SF 104	F7A2-EA2 S 46 2 AB S2Mo S 46 2 AB S2Mo	C: 0.05 Si: 0.40 Mn: 1.10 Mo: 0.50	480	560	26	-20°C: 50 0°C: 65		
SF 113	F8A2-EA2 S 46 2 MS/CS S2Mo S 46 2 MS/CS S2Mo	C: 0.04 Si: 0.50 Mn: 1.65 Mo: 0.45	515	590	28	-20°C: 50 0°C: 60		
SF 124	F8A2-EA2 S 46 2 AB S2Mo S 46 2 AB S2Mo	C: 0.07 Si: 0.25 Mn: 1.25 Mo: 0.40	520	590	26	-30°C: 40 -20°C: 55 0°C: 70		
SF 134	F8A4-EA2 S 46 3 AB S2Mo S 46 3 AB S2Mo	C: 0.05 Si: 0.45 Mn: 1.50 Mo: 0.40	520	640	26	-40°C: 35 -30°C: 55 -20°C: 70	1.60 2.00 2.40 3.20 4.00	15 kg - K300 (1.60 mm) 25 kg - K435 200 kg - Drum 400 kg - Drum 600 kg - Drum 1000 kg - Coil
SF 204	F8A4-EA2 S 46 2 AB S2Mo S 46 2 AB S2Mo	C: 0.06 Si: 0.45 Mn: 1.30 Mo: 0.40	520	610	28	-40°C: 50 -30°C: 60 -20°C: 90		
SF 212	F8AZ-EA2 S 50 A AR S2Mo S 50 A AR S2Mo	C: 0.05 Si: 0.75 Mn: 1.40 Mo: 0.45	590	670	26	20°C: 50 0°C: 35		
SF 304	F8A4-EA2 S 46 3 AB S2Mo S 46 3 AB S2Mo	C: 0.05 Si: 0.35 Mn: 1.40 Mo: 0.45	510	570	27	-40°C: 50 -30°C: 60 -20°C: 100		
SF 401	F8A5-EA2 S 46 4 AB S2Mo S 46 4 AB S2Mo	C: 0.07 Si: 0.20 Mn: 1.40 Mo: 0.40	500	570	28	-46°C: 50 -40°C: 70 -30°C: 90		
SF 414	F8A5-EA2 S 46 4 AB S2Mo S 46 4 AB S2Mo	C: 0.08 Si: 0.25 Mn: 1.30 Mo: 0.40	510	590	28	-40°C: 70 -30°C: 80 -20°C: 130		

SUBMERGED ARC WELDING (SAW) WIRES AND FLUXES

Unalloyed and Low-Alloyed Steel SAW Fluxes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
SF 104 EN ISO 14171 S A AB 1 TS EN ISO 14171 S A AB 1	Alumina-basic type, agglomerated submerged arc welding flux, which is designed for butt and fillet welding and for the single- and multi-pass butt welding of mild, medium and high tensile steels in shipbuilding and steel constructions. Provides good penetration in one-side-welding and two-side-welding processes. Has a high current carrying capacity and good operating characteristics both on alternative and direct currents. Very easy slag removal in fillet and V-groves. Smooth and clean weld beads blending into base metal. Suitable to use in steel construction, shipbuilding, tank, pressure vessel and boiler production.	   If required 2 Hour

Welding Wire	Wire and Flux Combination Standards AWS/ASME SFA - 5.23 EN ISO 14171-A TS EN ISO 14171A	Typical Chemical Analysis of All-Weld Metal (%)	Typical Mechanical Properties of All-Weld Metal				Packing Information of Welding Flux
			Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO-V (J)	
SW 701	F6A2-EL12 S 38 2 AB S1 S 38 2 AB S1	C: 0.05 Si: 0.25 Mn: 0.85	410	480	30	-30°C: 50 -20°C: 85 0°C: 90	25 kg - Kraft Pack 25 kg - Dry Pack 1000 kg - Big Pack
SW 702	F7A2-EM12 S 42 2 AB S2 S 42 2 AB S2	C: 0.05 Si: 0.30 Mn: 1.10	435	510	28	-30°C: 45 -20°C: 65	
SW 702Si	F7A2-EM12K S 42 2 AB S2Si S 42 2 AB S2Si	C: 0.05 Si: 0.50 Mn: 1.10	425	510	29	-30°C: 40 -20°C: 50 0°C: 80	
SW 703Si	F7A5-EH12K S 46 4 AB S3Si S 46 4 AB S3Si	C: 0.06 Si: 0.45 Mn: 1.55	460	540	28	-40°C: 60 -20°C: 90	
SW 702Mo	F8A2-EA2 S 46 2 AB S2Mo S 46 2 AB S2Mo	C: 0.05 Si: 0.40 Mn: 1.10 Mo: 0.50	480	560	26	-20°C: 50 0°C: 65	

SUBMERGED ARC WELDING (SAW) WIRES AND FLUXES




Unalloyed and Low-Alloyed Steel SAW Fluxes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
SF 113 EN ISO 14174 S A MS/CS 1 TS EN ISO 14174 S A MS/CS 1	Agglomerated, manganese-silicate type flux for welding general structural steels and pipe steels. Provides sound welds in steels containing low silicon and manganese. Especially suitable for fillet and groove welds in steel constructions, LPG cylinder, pressure vessel production, spirally welding of pipes. Suitable to use at high welding speeds with single and multi-wires. Possible to use both in alternative and direct currents. Good wetting properties blending into the base metal, very easy slag removal in fillet and V-grooves. Provides flat and nice weld profile without undercut.	 If required 2 Hour

Welding Wire	Wire and Flux Combination Standards AWS/ASME SFA - 5.23 EN ISO 14171-A TS EN ISO 14171A	Typical Chemical Analysis of All-Weld Metal (%)	Typical Mechanical Properties of All-Weld Metal				Packing Information of Welding Flux
			Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO-V (J)	
SW 701	F7A2-EL12 S 38 2 CS/MS S1 S 38 2 CS/MS S1	C: 0.04 Si: 0.45 Mn: 1.45	400	500	30	-20°C: 60 0°C: 70	25 kg - Kraft Pack 25 kg - Dry Pack 1000 kg - Big Pack
SW 702	F7A2-EM12 S 42 2 MS/CS S2 S 42 2 MS/CS S2	C: 0.04 Si: 0.40 Mn: 1.80	425	540	30	-20°C: 55 0°C: 65	
SW 702Si	F7A2-EM12K S 42 3 AB S2Si S 42 3 AB S2Si	C: 0.04 Si: 0.65 Mn: 1.90	450	550	30	-20°C: 50 0°C: 60	
SW 702Mo	F8A2-EA2 S 46 2 MS/CS S2Mo S 46 2 MS/CS S2Mo	C: 0.04 Si: 0.50 Mn: 1.65 Mo: 0.45	515	590	28	-20°C: 50 0°C: 60	

SUBMERGED ARC WELDING (SAW) WIRES AND FLUXES

Unalloyed and Low-Alloyed Steel SAW Fluxes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
SF 124 EN ISO 14174 S A AB 1 TS EN ISO 14174 S A AB 1	Alumina-basic type, agglomerated submerged arc welding flux, which is developed for single- and multi-wire (tandem) welding of butt and fillet joints in shipbuilding, steel constructions, storage tank and machine production. Suitable to use in single and multi pass welding in thick and thin sections. Due to it's metallurgically neutral characteristics, there is low Si and Mn pick-up from flux, it can be safely used in multi-pass applications in thick sections. Has a high current carrying capacity and possible to use both in alternative and direct currents. Provides bright and very clean weld surface appearance with easy slag removal in fillet joints and narrow V-groves.	   If required 2 Hour

Welding Wire	Wire and Flux Combination Standards AWS/ASME SFA - 5.23 EN ISO 14171-A TS EN ISO 14171A	Typical Chemical Analysis of All-Weld Metal (%)	Typical Mechanical Properties of All-Weld Metal				Packing Information of Welding Flux
			Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO-V (J)	
SW 702	F7A4-EM12 S 42 2 AB S2 S 42 2 AB S2	C: 0.05 Si: 0.20 Mn: 1.10	430	490	30	-40°C: 40 -20°C: 70	25 kg - Kraft Pack 25 kg - Dry Pack 1000 kg - Big Pack
SW 702Si	F7A4-EM12K S 42 3 AB S2Si S 42 3 AB S2Si	C: 0.05 Si: 0.30 Mn: 1.20	435	500	27	-40°C: 50 -30°C: 70 -20°C: 90	
SW 703Si	F7A4-EH12K S 42 4 AB S3Si S 42 4 AB S3Si	C: 0.06 Si: 0.45 Mn: 1.75	440	550	30	-40°C: 70 -30°C: 90	
SW 702Mo	F8A2-EA2 S 46 2 AB S2Mo S 46 2 AB S2Mo	C: 0.07 Si: 0.25 Mn: 1.25 Mo: 0.45	520	610	26	-30°C: 40 -20°C: 55 0°C: 70	

SUBMERGED ARC WELDING (SAW) WIRES and FLUXES

Unalloyed and Low-Alloyed Steel SAW Fluxes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
----------------------------	-----------------------------	--

SF 134

EN ISO 14174 S A AB 1
TS EN ISO 14174 S A AB 1

Alumina-basic type, agglomerated submerged arc welding flux, which is designed for butt and fillet welding and for the single- and multi-pass butt welding of mild, medium and high tensile steels in shipbuilding and steel constructions. Provides smooth and clean weld beads blending into base metal for fine grain structural steels and shipbuilding steels. Has a high current carrying capacity and good operating characteristics both on alternative and direct currents. Used are general structural welding, bridge fabrication, heavy equipment fabrication, and line pipe welding.






If required
2 Hour

Welding Wire	Wire and Flux Combination Standards AWS/ASME SFA - 5.23 EN ISO 14171-A TS EN ISO 14171A	Typical Chemical Analysis of All-Weld Metal (%)	Typical Mechanical Properties of All-Weld Metal				Packing Information of Welding Flux
			Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO-V (J)	
SW 702	F7A4-EM12 S 42 2 AB S2 S 42 2 AB S2	C: 0.05 Si: 0.45 Mn: 1.45	440	530	30	-40°C: 50 -30°C: 90 -20°C: 100	25 kg - Kraft Pack 25 kg - Dry Pack 1000 kg - Big Pack
SW 702Si	F7A4-EM12K S 42 3 AB S2Si S 42 3 AB S2Si	C: 0.05 Si: 0.60 Mn: 1.60	470	560	29	-40°C: 50 -30°C: 70 -20°C: 90	
SW 703Si	F7A5-EH12K S 46 4 AB S3Si S 46 4 AB S3Si	C: 0.07 Si: 0.55 Mn: 1.90	475	575	30	-50°C: 55 -40°C: 70 -30°C: 100	
SW 702Mo	F8A4-EA2 S 46 3 AB S2Mo S 46 3 AB S2Mo	C: 0.05 Si: 0.45 Mn: 1.50 Mo: 0.40	520	640	26	-40°C: 35 -30°C: 55 -20°C: 70	

SUBMERGED ARC WELDING (SAW) WIRES AND FLUXES

Unalloyed and Low-Alloyed Steel SAW Fluxes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
SF 204 EN ISO 14174 S A AB 1 TS EN ISO 14174 S A AB 1	Agglomerated semi-basic flux for welding carbon and low alloy steel in single or multipass technique and with single or multi-wire applications. Suitable for use in production of pressure vessel, pipe, boiler, tank, LPG bottles, steel construction and in shipbuilding. The weld metal, produced in combination with corresponding wire electrodes, offers good mechanical properties also at low temperatures. Good slag removal in fillet and groove welds. Possible to use both in alternative and direct currents.	   If required 2 Hour

Welding Wire	Wire and Flux Combination Standards AWS/ASME SFA - 5.23 EN ISO 14171-A TS EN ISO 14171A	Typical Chemical Analysis of All-Weld Metal (%)	Typical Mechanical Properties of All-Weld Metal				Packing Information of Welding Flux
			Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO-V (J)	
SW 702	F7A2-EM12 S 42 3 AB S2 S 42 3 AB S2	C: 0.05 Si: 0.40 Mn: 1.40	435	510	30	-40°C: 50 -30°C: 70 -20°C: 90	25 kg - Kraft Pack 25 kg - Dry Pack 1000 kg - Big Pack
SW 702Si	F7A4-EM12K S 42 3 AB S2Si S 42 3 AB S2Si	C: 0.06 Si: 0.55 Mn: 1.35	440	530	29	-40°C: 40 -30°C: 70	
SW 703Si	F7A4-EH12K S 46 3 AB S3Si S 46 3 AB S3Si	C: 0.06 Si: 0.60 Mn: 1.70	510	610	28	-40°C: 60 -30°C: 100 -20°C: 120	
SW 702Mo	F8A4-EA2 S 46 2 AB S2Mo S 46 2 AB S2Mo	C: 0.06 Si: 0.45 Mn: 1.30 Mo: 0.40	520	610	28	-40°C: 50 -30°C: 60 -20°C: 90	

SUBMERGED ARC WELDING (SAW) WIRES AND FLUXES

Unalloyed and Low-Alloyed Steel SAW Fluxes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
----------------------------	-----------------------------	--

SF 212

EN ISO 14174 S A AR 1
TS EN ISO 14174 S A AR 1

Rutile type, agglomerated submerged arc welding flux, which is designed for welding of at high speeds with excellent bead appearance. Generally used in thin plates in shipbuilding, pressure vessels, LPG Cylinders, small tanks, boiler, beams, thin walled pipes, tubes and lamp posts. Owing to Mn and Si alloys, make it suitable for carbon steel welding with single or multi-wires, in one and multi passes. Possible to use both in direct and in alternative currents. Slag is generally self releasing and slag removal is very easy in narrow fillet and root passes.






If required
2 Hour

Welding Wire	Wire and Flux Combination Standards AWS/ASME SFA - 5.23 EN ISO 14171-A TS EN ISO 14171A	Typical Chemical Analysis of All-Weld Metal (%)	Typical Mechanical Properties of All-Weld Metal				Packing Information of Welding Flux
			Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO-V (J)	
SW 701	F7AZ-EL12 S 42 A AR S1 S 42 A AR S1	C: 0.05 Si: 0.65 Mn: 1.10	460	530	28	0°C: 30 20°C: 60	25 kg - Kraft Pack 25 kg - Dry Pack 1000 kg - Big Pack
SW 702	F7AZ-EM12 S 42 A AR S2 S 42 A AR S2	C: 0.05 Si: 0.80 Mn: 1.35	480	560	28	0°C: 30 20°C: 70	
SW 702Si	F7AZ-EM12K S 46 A AR S2Si S 46 A AR S2Si	C: 0.05 Si: 0.80 Mn: 1.40	530	610	26	0°C: 55 20°C: 80	
SW 703Si	F8AZ-EH12K S 46 A AR S3Si S 46 A AR S3Si	C: 0.05 Si: 0.95 Mn: 1.70	530	610	26	0°C: 40 20°C: 65	
SW 702Mo	F8AZ-EA2 S 50 2 AB S2Mo S 50 2 AB S2Mo	C: 0.05 Si: 0.75 Mn: 1.40 Mo: 0.45	590	670	26	0°C: 35 20°C: 50	

SUBMERGED ARC WELDING (SAW) WIRES and FLUXES




Unalloyed and Low-Alloyed Steel SAW Fluxes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
SF 304 EN ISO 14174 S A AB 1 TS EN ISO 14174 S A AB 1	Alumina-basic type, agglomerated submerged arc welding flux, developed particularly for spiral and longitudinal welding of pipes. It gives the possibility of high-speed welding in the welding of thin and medium thick pipes by single or multi-wires (tandem/twin). Bead appearance is good. Especially in pipe welding, inner and outer welds are smooth and provide necessary penetration. It has high current carrying capacity and can be used in alternative and direct currents. Provides smooth weld beads, good weld bead appearance with high penetration.	   If required 2 Hour

Welding Wire	Wire and Flux Combination Standards AWS/ASME SFA - 5.23 EN ISO 14171-A TS EN ISO 14171A	Typical Chemical Analysis of All-Weld Metal (%)	Typical Mechanical Properties of All-Weld Metal				Packing Information of Welding Flux
			Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO-V (J)	
SW 701	F6A0-EL12 S 38 2 AB S1 S 38 2 AB S1	C: 0.05 Si: 0.25 Mn: 0.90	420	490	30	-30°C: 60 -20°C: 80 0°C: 100	25 kg - Kraft Pack 25 kg - Dry Pack 1000 kg - Big Pack
SW 702	F7A4-EM12 S 42 3 AB S2 S 42 3 AB S2	C: 0.05 Si: 0.25 Mn: 1.25	420	500	29	-40°C: 60 -30°C: 75 -20°C: 110	
SW 702Si	F7A4-EM12K S 42 3 AB S2Si S 42 3 AB S2Si	C: 0.06 Si: 0.45 Mn: 1.40	460	530	28	-40°C: 50 -30°C: 70 -20°C: 90	
SW 703Si	F7A4-EH12K S 46 4 AB S3Si S 46 4 AB S3Si	C: 0.06 Si: 0.65 Mn: 1.75	480	540	28	-40°C: 55 -30°C: 80 -20°C: 120	
SW 702Mo	F8A4-EA2 S 46 3 AB S2Mo S 46 3 AB S2Mo	C: 0.05 Si: 0.35 Mn: 1.40 Mo: 0.45	510	570	27	-40°C: 50 -30°C: 60 -20°C: 100	

SUBMERGED ARC WELDING (SAW) WIRES AND FLUXES




Unalloyed and Low-Alloyed Steel SAW Fluxes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>SF 401</p> <p>EN ISO 14174 S A FB 1 TS EN ISO 14174 S A FB 1</p>	<p>Fluoride-basic type, agglomerated submerged arc welding flux with high basicity, it is designed for the welding of high strength fine grained structural steels, cryogenic steels and steels, resistant to ageing. Generally used for the welding of thick sections in the offshore, wind tower, nuclear and pressure vessel industries. Provides very high toughness values at low temperatures, in combination with approved wires. Due to its high current carrying capacity and good operating characteristics both on alternative and direct currents, possible to use in one side welding and two side welding processes by single or multi-wires (tandem/twin). Owing to its neutral behaviour, it is advisable to use wire electrodes having higher manganese and silicon content in tandem and multi wire applications. Has high penetration, smooth weld beads with high X-ray quality.</p>	<p></p> <p></p> <p></p> <p>If required 2 Hour</p>

Welding Wire	Wire and Flux Combination Standards AWS/ASME SFA - 5.23 EN ISO 14171-A TS EN ISO 14171A	Typical Chemical Analysis of All-Weld Metal (%)	Typical Mechanical Properties of All-Weld Metal				Packing Information of Welding Flux
			Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO-V (J)	
SW 702Si	F7A6-EM12K S 42 5 FB S2Si S 42 5 FB S2Si	C: 0.06 Si: 0.30 Mn: 1.15	425	520	30	-50°C: 70 -40°C: 90 -30°C: 110	25 kg - Kraft Pack 25 kg - Dry Pack 1000 kg - Big Pack
SW 703Si	F7A6-EH12K S 46 5 FB S3Si S 46 5 FB S3Si	C: 0.07 Si: 0.30 Mn: 1.60	480	530	28	-50°C: 80 -40°C: 100 -30°C: 120	
SW 702Mo	F8A5-EA2 S 46 4 FB S2Mo S 46 4 FB S2Mo	C: 0.07 Si: 0.20 Mn: 1.40 Mo: 0.40	500	570	28	-46°C: 50 -40°C: 70 -30°C: 90	

SUBMERGED ARC WELDING (SAW) WIRES AND FLUXES

Unalloyed and Low-Alloyed Steel SAW Fluxes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
SF 414 EN ISO 14174 S A AB 1 TS EN ISO 14174 S A AB 1	Alumina- basic type, agglomerated submerged arc welding flux, which is designed for single or multi pass welding of butt and fillet joints in high strength steels. Especially designed for thick section welding in steel construction, wind tower, boiler and pressure vessel production. Provides high toughness values down to -50°C. Due to it's high current carrying capacity and good operating characteristics both on alternative and direct currents, possible to use in one side welding and two side welding processes by single or multi-wires (tandem/twin). Has high penetration and smooth weld beads with easy slag removal in fillet and V-groves.	   If required 2 Hour

Welding Wire	Wire and Flux Combination Standards AWS/ASME SFA - 5.23 EN ISO 14171-A TS EN ISO 14171A	Typical Chemical Analysis of All-Weld Metal (%)	Typical Mechanical Properties of All-Weld Metal				Packing Information of Welding Flux
			Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO-V (J)	
SW 702	F7A6-EM12 S 38 5 AB S2 S 38 5 AB S2	C: 0.06 Si: 0.25 Mn: 1.40	410	510	30	-50°C: 65 -40°C: 100 -20°C: 120	25 kg - Kraft Pack 25 kg - Dry Pack 1000 kg - Big Pack
SW 702Si	F7A6-EM12K S 38 5 AB S2Si S 38 5 AB S2Si	C: 0.07 Si: 0.35 Mn: 1.45	420	520	30	-50°C: 70 -40°C: 110 -20°C: 140	
SW 703Si	F7A8-EH12K S 46 5 AB S3Si S 46 5 AB S3Si	C: 0.06 Si: 0.35 Mn: 1.65	470	560	30	-60°C: 50 -50°C: 75 -40°C: 120	
SW 702Mo	F8A5-EA2 S 46 4 AB S2Mo S 46 4 AB S2Mo	C: 0.08 Si: 0.25 Mn: 1.30 Mo: 0.40	510	590	28	-40°C: 70 -30°C: 80 -20°C: 130	

SUBMERGED ARC WELDING (SAW) WIRES AND FLUXES

Stainless Steel SAW Wires

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>SI 307</p> <p>AWS/ASME SFA-5.9 ~ER307 EN ISO 14343-A S 18 8 Mn TS EN ISO 14343-A S 18 8 Mn DIN M. No. 1.4370</p>	<p>Austenitic stainless steel welding wire for submerged arc welding of dissimilar steels, difficult to weld steels, armour plates, high manganese steels, rails, crossovers. Suitable also for depositing stress relieving buffer layers on crack sensitive base metals and hardsurfacing, e.g. crane wheels, cutting blades and dies where high degree of pressure and dynamical loads exists. Weld metal is resistant to operating temperatures up to 300°C and non-scaling up to 850°C and also highly corrosion resistant. Used in combination with SIF 501 and SIF 502 submerged arc welding fluxes. Depending on chemical composition of base metal, proper welding procedure, preheating and interpass temperatures shall be applied by also avoiding high admixture of base metal.</p>	<p>⊕ ⊖</p>



Typical Chemical Analysis of Welding Wire (%)

	C	Si	Mn	Cr	Ni
SI 307	0.02	0.90	5.00	19.00	8.00

Welding Wire	Typical Chemical Analysis of All-Weld Metal (%)	Typical Mechanical Properties of All-Weld Metal				Diameter and Packing Info. of Welding Wire	
		Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO-V (J)	Diameter (mm)	Packing Weight (kg) Packing Type
SIF 501	C: 0.04 Cr: 18.50	410	600	42	-60°C: 50 20°C: 70	2.40 3.20	25 kg - K435
	Si: 0.85 Ni: 7.00 Mn: 5.50						
SIF 502	C: 0.04 Cr: 18.50	420	610	40	-60°C: 45 20°C: 60		
	Si: 0.90 Ni: 8.00 Mn: 5.00						

SUBMERGED ARC WELDING (SAW) WIRES AND FLUXES

Stainless Steel SAW Wires

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
SI 308L AWS/ASME SFA-5.9 ER 308L EN ISO 14343-A S 19 9 L TS EN ISO 14343-A S 19 9 L DIN M. No. 1.4316	Austenitic stainless steel welding wire for submerged arc welding of unstabilized or stabilized corrosion resisting Cr-Ni steels tanks, pipes and equipments, used in food, beverage and pharmaceutical industries. Used in combination with SIF 501 and SIF 502 submerged arc welding fluxes. Weld metal is resistant to intergranular corrosion up to 350°C. Non-scaling up to 800°C, in air or oxidizing combustion gases.	 

Typical Chemical Analysis of Welding Wire (%)

	C	Si	Mn	Cr	Ni
SI 308L	0.02	0.40	1.80	20.00	9.50

Welding Flux	Typical Chemical Analysis of All-Weld Metal (%)	Typical Mechanical Properties of All-Weld Metal				Diameter and Packing Info. of Welding Wire	
		Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO-V (J)	Diameter (mm)	Packing Weight (kg) Packing Type
SIF 501	C: 0.02 Cr: 18.00	380	530	38	-196°C: 50	2.40	25 kg - K435
	Si: 0.35 Ni: 9.00				-60°C: 70		
	Mn: 1.60				20°C: 90		
SIF 502	C: 0.02 Cr: 20.00	390	565	36	-196°C: 45	3.20	
	Si: 0.65 Ni: 9.50				-60°C: 60		
	Mn: 1.00				20°C: 80		

SUBMERGED ARC WELDING (SAW) WIRES AND FLUXES

Stainless Steel SAW Wires

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>SI 309L</p> <p>AWS/ASME SFA-5.9 ER 309L EN ISO 14343-A S 23 12 L TS EN ISO 14343-A S 23 12 L DIN M. No. 1.4332</p>	<p>Austenitic-ferritic wire electrode for submerged arc welding of stainless steels to unalloyed or low-alloyed steels, subjected to operating temperatures up to 300°C. Used in combination with SIF 501 and SIF 502 submerged arc welding fluxes. Low carbon content increases resistance to intergranular corrosion. Suitable to use also for buffer layer on carbon steel before welding with 308 and 308L to reach 304 and 304L surface layer.</p>	<p>⊕ ⊖</p>

Typical Chemical Analysis of Welding Wire (%)

	C	Si	Mn	Cr	Ni
SI 309L	0.02	0.40	1.80	24.50	13.50

Typical Mechanical Properties of All-Weld Metal

Diameter and Packing Info. of Welding Wire

Welding Flux	Typical Chemical Analysis of All-Weld Metal (%)		Typical Mechanical Properties of All-Weld Metal				Diameter and Packing Info. of Welding Wire	
			Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO-V (J)	Diameter (mm)	Packing Weight (kg) Packing Type
SIF 501	C: 0.02	Cr: 20.00	410	560	35	-196°C: 40	2.40	25 kg - K435
	Si: 0.40	Ni: 11.00				-60°C: 60		
	Mn: 1.75					20°C: 80		
SIF 502	C: 0.02	Cr: 20.50	410	560	34	-196°C: 30	3.20	
	Si: 0.75	Ni: 11.50				-60°C: 40		
	Mn: 1.45					20°C: 70		

SUBMERGED ARC WELDING (SAW) WIRES AND FLUXES

Stainless Steel SAW Wires

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>SI 316L</p> <p>AWS/ASME SFA-5.9 ER 316L EN ISO 14343-A S 19 12 3 L TS EN ISO 14343-A S 19 12 3 L DIN M. No. 1.4430</p>	<p>Austenitic stainless steel welding wire for submerged arc welding of unstabilized or stabilized high corrosion resisting Cr-Ni-Mo stainless steels. Used in combination with SIF 501 and SIF 502 submerged arc welding fluxes. Due to its low carbon content, resistant to intergranular corrosion up to 400°C. Especially used in welding tanks, pipes and equipments which are used in chemical, petrochemical, paint, paper and shipbuilding industries, etc.</p>	<p>⊕</p> <p>⊕</p>

Typical Chemical Analysis of Welding Wire (%)

	C	Si	Mn	Cr	Ni	Mo
SI 316L	0.02	0.40	1.80	18.50	12.00	2.70

Typical Mechanical Properties of All-Weld Metal

Diameter and Packing Info. of Welding Wire

Welding Flux	Typical Chemical Analysis of All-Weld Metal (%)		Typical Mechanical Properties of All-Weld Metal				Diameter and Packing Info. of Welding Wire	
			Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO-V (J)	Diameter (mm)	Packing Weight (kg) Packing Type
SIF 501	C: 0.02	Cr: 18.00	420	570	38	-196°C: 45	2.40	25 kg - K435
	Si: 0.35	Ni: 10.00				-60°C: 55		
	Mn: 1.65	Mo: 2.50				20°C: 75		
SIF 502	C: 0.02	Cr: 19.00	400	570	34	-196°C: 45	3.20	25 kg - K435
	Si: 0.70	Ni: 11.00				-60°C: 55		
	Mn: 1.25	Mo: 2.70				20°C: 70		

SUBMERGED ARC WELDING (SAW) WIRES AND FLUXES

Stainless Steel SAW Wires

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>SI 347</p> <p>AWS/ASME SFA-5.9 ER347 EN ISO 14343-A S 19 9 Nb TS EN ISO 14343-A S 19 9 Nb DIN M. No. 1.4551</p>	<p>Stabilized austenitic stainless steel welding wire for submerged arc welding of unstabilized and stabilized corrosion resisting Cr-Ni steels. Used in combination with SIF 501 and SIF 502 submerged arc welding fluxes. Generally used for welding pipes, tanks and equipments in food, beverage, chemical and pharmaceutical industries. Stabilized with Cb (Nb) and resistant to intergranular corrosion. Weld metal is suitable for operating temperatures of up to 400°C, non-scaling up to 800°C, in air and oxidizing combustion gases.</p>	<p>⊕ ⊖</p>

Typical Chemical Analysis of Welding Wire (%)

	C	Si	Mn	Cr	Ni	Nb
SI 347	0.04	0.40	1.40	19.50	9.50	0.60

Typical Mechanical Properties of All-Weld Metal

Diameter and Packing Info. of Welding Wire

Welding Flux	Typical Chemical Analysis of All-Weld Metal (%)		Typical Mechanical Properties of All-Weld Metal				Diameter and Packing Info. of Welding Wire	
			Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO-V (J)	Diameter (mm)	Packing Weight (kg) Packing Type
SIF 501	C: 0.04	Cr: 19.00	460	610	32	-196°C: 45	2.40	25 kg - K435
	Si: 0.35	Ni: 8.50				-60°C: 75		
	Mn: 1.50	Nb: 0.30				20°C: 90		
SIF 502	C: 0.04	Cr: 19.50	430	610	26	-196°C: 35	3.20	
	Si: 0.65	Ni: 9.00				-60°C: 55		
	Mn: 0.95	Nb: 0.35				20°C: 70		

SUBMERGED ARC WELDING (SAW) WIRES AND FLUXES

Stainless Steel SAW Wires

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>SI 2209</p> <p>AWS/ASME SFA-5.9 EN ISO 14343-A TS EN ISO 14343-A DIN M. No.</p> <p>ER 2209 S 22 9 3 NL S 22 9 3 NL ~1.4462</p>	<p>Dublex (ferritic-austenitic) stainless steel wire electrode for submerged arc welding of duplex Cr-Ni-Mo stainless steels. Used in combination with SIF 501 and SIF 502 submerged arc welding fluxes. Especially used in welding of acid tanks and pipes, in chemical, petrochemical, paper, shipbuilding and desalination industries. Suitable also for dissimilar welding of duplex stainless steels to carbon steels. High-strength and ductile weld metal exhibits good resistance to pitting, crevice corrosion and stress corrosion cracking in chloride-bearing media.</p>	<p>⊕</p> <p>⊕</p>

Typical Chemical Analysis of Welding Wire (%)

	C	Si	Mn	Cr	Ni	Mo	N
SI 2209	0.02	0.60	1.60	22.50	8.50	3.00	0.15

Typical Mechanical Properties of All-Weld Metal

Diameter and Packing Info. of Welding Wire

Welding Flux	Typical Chemical Analysis of All-Weld Metal (%)			Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)	Impact Energy ISO-V (J)	Diameter (mm)	Packing Weight (kg) Packing Type
SIF 501	C: 0.02	Cr: 22.00	N: 0.10	600	770	31	-60°C: 55 20°C: 80	3.20	25 kg - K435
	Si: 0.45	Ni: 8.00							
	Mn: 1.70	Mo: 2.50							
SIF 502	C: 0.02	Cr: 22.50	N: 0.12	590	760	28	-60°C: 35 20°C: 55	3.20	25 kg - K435
	Si: 0.75	Ni: 9.00							
	Mn: 1.10	Mo: 2.50							

SUBMERGED ARC WELDING (SAW) WIRES AND FLUXES




Stainless Steel SAW Fluxes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>SIF 501</p> <p>EN ISO 14174 S A FB 2 DC TS EN ISO 14174 S A FB 2 DC</p>	<p>Florite-basic type, agglomerated submerged arc welding flux, which is designed for butt and fillet welding stainless steel and corrosion resistance steels. It is also suitable to use in surfacing of stainless steels and unalloyed steels with stainless steel welding wire. Especially used for welding stainless steel storage tanks in chemical tankers, cryogenic tanks and pressure vessels. Provides good welding characteristics and easy slag removal even on medium and thick section welding. Weld bead is very smooth and pore free. Slag is generally self releasing.</p>	<p></p> <p></p> <p></p> <p>If required 2 Hour</p>

Welding Wire	Typical Chemical Analysis of All-Weld Metal (%)	Typical Mechanical Properties of All-Weld Metal				Impact Energy ISO-V (J)	Packing Information of Welding Flux
		Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)			
SI 307	C: 0.04 Cr: 18.50 Si: 0.85 Ni: 7.00 Mn: 5.50	410	600	42	-60°C: 50 20°C: 70	25 kg - Kraft Pack 25 kg - Dry Pack 1000 kg - Big Pack	
SI 308L	C: 0.02 Cr: 18.00 Si: 0.35 Ni: 9.00 Mn: 1.60	380	530	38	-196°C: 50 -60°C: 70 20°C: 90		
SI 309L	C: 0.02 Cr: 20.00 Si: 0.40 Ni: 11.00 Mn: 1.75	410	560	35	-196°C: 40 -60°C: 60 20°C: 80		
SI 316L	C: 0.02 Cr: 18.00 Si: 0.35 Ni: 10.00 Mn: 1.65 Mo: 2.50	420	570	38	-196°C: 45 -60°C: 55 20°C: 75		
SI 347	C: 0.04 Cr: 19.00 Si: 0.35 Ni: 8.50 Mn: 1.50 Nb: 0.30	460	610	32	-196°C: 45 -60°C: 75 20°C: 90		
SI 2209	C: 0.02 Cr: 22.00 Si: 0.45 Ni: 8.00 Mn: 1.70 Mo: 2.50 N: 0.10	600	770	31	-60°C: 55 20°C: 80		

SUBMERGED ARC WELDING (SAW) WIRES AND FLUXES








Stainless Steel SAW Fluxes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
SIF 502 EN ISO 14174 TS EN ISO 14174	S A CS 2 Cr DC S A CS 2 Cr DC Calcium-silicate type, agglomerated submerged arc welding flux, which is designed for butt and fillet welding stainless steel and corrosion resistance steels. It is also suitable to use in surfacing of stainless steels and unalloyed steels with stainless steel welding wire. Cr alloy content of the flux prevents Cr loss in stainless steel weld bead during welding. Provides good welding characteristics and easy slag removal even on thin section welding.	   If required 2 Hour

Welding Wire	Typical Chemical Analysis of All-Weld Metal (%)	Typical Mechanical Properties of All-Weld Metal				Impact Energy ISO-V (J)	Packing Information of Welding Flux
		Yield Strength (N/mm ²)	Tensile Strength (N/mm ²)	Elongation A5 (%)			
SI 307	C: 0.04 Cr: 19.00 Si: 0.90 Ni: 8.00 Mn: 5.00	420	610	40	-60°C: 50 20°C: 60	25 kg - Kraft Pack 25 kg - Dry Pack 1000 kg - Big Pack	
SI 308L	C: 0.02 Cr: 20.00 Si: 0.65 Ni: 9.50 Mn: 1.00	390	565	36	-196°C: 45 -60°C: 60 20°C: 80		
SI 309L	C: 0.02 Cr: 20.50 Si: 0.75 Ni: 11.50 Mn: 1.45	410	560	34	-196°C: 30 -60°C: 40 20°C: 70		
SI 316L	C: 0.02 Cr: 19.00 Si: 0.70 Ni: 11.00 Mn: 1.75 Mo: 2.70	400	570	34	-196°C: 45 -60°C: 55 20°C: 70		
SI 347	C: 0.04 Cr: 19.50 Si: 0.65 Ni: 9.00 Mn: 0.95 Nb: 0.35	430	610	26	-196°C: 35 -60°C: 55 20°C: 70		
SI 2209	C: 0.02 Cr: 22.50 Si: 0.75 Ni: 9.00 Mn: 1.10 Mo: 2.50 N: 0.12	590	760	28	-60°C: 35 20°C: 55		

SUBMERGED ARC WELDING (SAW) WIRES AND FLUXES




Hardfacing SAW Fluxes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>SHF 325</p> <p>EN ISO 14174 S A CS 3 TS EN ISO 14174 S A CS 3</p>	<p>Alloyed and agglomerated flux, which is designed for submerged arc hardfacing of parts subjected to metal to metal friction wear, moderate impart and low stress mineral abrasion. Provides weld metal with 225-300 HB hardness, when used with SW 702 wire electrode. Possible to use in direct current. Hardness and transfer of alloying elements to the weld metal depends on welding parameters used. For instance, optimum welding parameters for 4.00 mm wire electrode are about 600 A, 32 V, 50 cm/min. welding speed. Gives very smooth and clean weld bead surfaces, slag removal is very easy and generally slag is self releasing.</p> <p>Typical Applications: Suitable for hardfacing of machine gear parts, rails, supports rolls of caterpillars, pulleys, locomotive wheels, table and support rolls in iron and steel industry.</p>	   If required 2 Hour
<p>SHF 333</p> <p>EN ISO 14174 S A FB 3 TS EN ISO 14174 S A FB 3</p>	<p>Alloyed and agglomerated flux, which is designed for submerged arc hardfacing of parts subjected to metal to metal friction wear, moderate impart and low stress mineral abrasion. Provides weld metal with 300-350 HB hardness, when used with SW 702 wire electrode. Possible to use in direct current. Hardness and transfer of alloying elements to the weld metal depends on welding parameters used. Gives very smooth and clean weld bead surfaces, slag removal is very easy and generally slag is self releasing.</p> <p>Typical Applications: Hardfacing of track rollers, idlers, couplings, piston rod ends, earth moving equipment, rolls, mills, etc. the alloying effect to the flux depends, to a large degree, on the weld parameters chosen.</p>	   If required 2 Hour
<p>SHF 335</p> <p>EN ISO 14174 S A CS 3 TS EN ISO 14174 S A CS 3</p>	<p>Alloyed and agglomerated flux, which is designed for submerged arc hardfacing of parts subjected to metal to metal friction wear, moderate impart and low stress mineral abrasion. Provides weld metal with 325-400 HB hardness, when used with SW 702 wire electrode. Possible to use in direct current. Hardness and transfer of alloying elements to the weld metal depends on welding parameters used. Gives very smooth and clean weld bead surfaces, slag removal is very easy and generally slag is self releasing. For example; optimum welding parameters for wire with a diameter of 4mm 600A, 32 V and welding speed 50 cm/min.</p> <p>Typical Applications: Hardfacing of pinch rollers, table rolls, idlers, couplings, piston rod ends.</p>	   If required 2 Hour
<p>SHF 345</p> <p>EN ISO 14174 S A CS 3 TS EN ISO 14174 S A CS 3</p>	<p>Alloyed and agglomerated flux, which is designed for submerged arc hardfacing of parts subjected to metal to metal friction wear, moderate impart and low stress mineral abrasion. Provides weld metal with 400-475 HB hardness, when used with SW 702 wire electrode. Possible to use in direct current. Hardness and transfer of alloying elements to the weld metal depends on welding parameters used. Gives very smooth and clean weld bead surfaces, slag removal is very easy and generally slag is self releasing. For example; optimum welding parameters for wire with a diameter of 4mm 600A, 32 V and welding speed 50 cm/min.</p> <p>Typical Applications: Hardfacing of pinchrolls, sinter crushers etc.</p>	   If required 2 Hour

Typical Mechanical Properties of All-Weld Metal (%)	Welding Wire	Hardness	Packing Information of Welding Flux Packing Weigth (kg) Packing Type
C: 0.15	SW 702	225-300 HB 20-32 HRc	25 kg - Kraft Pack
Si: 0.60			
Mn: 1.50			
Cr: 1.00			
Mo: 0.25	SW 702	300-350 HB 32-35 HRc	25 kg - Kraft Pack
C: 0.15			
Si: 1.00			
Mn: 1.30			
Cr: 2.50	SW 702	325-400 HB 33-40 HRc	25 kg - Kraft Pack
C: 0.20			
Si: 0.65			
Mn: 1.50			
Cr: 2.00	SW 702	400-475 HB 43-49 HRc	25 kg - Kraft Pack
Mo: 0.45			
C: 0.25			
Si: 0.70			
Mn: 1.70			
Cr: 3.25	Mo: 0.40		

SUBMERGED ARC WELDING (SAW) WIRES AND FLUXES

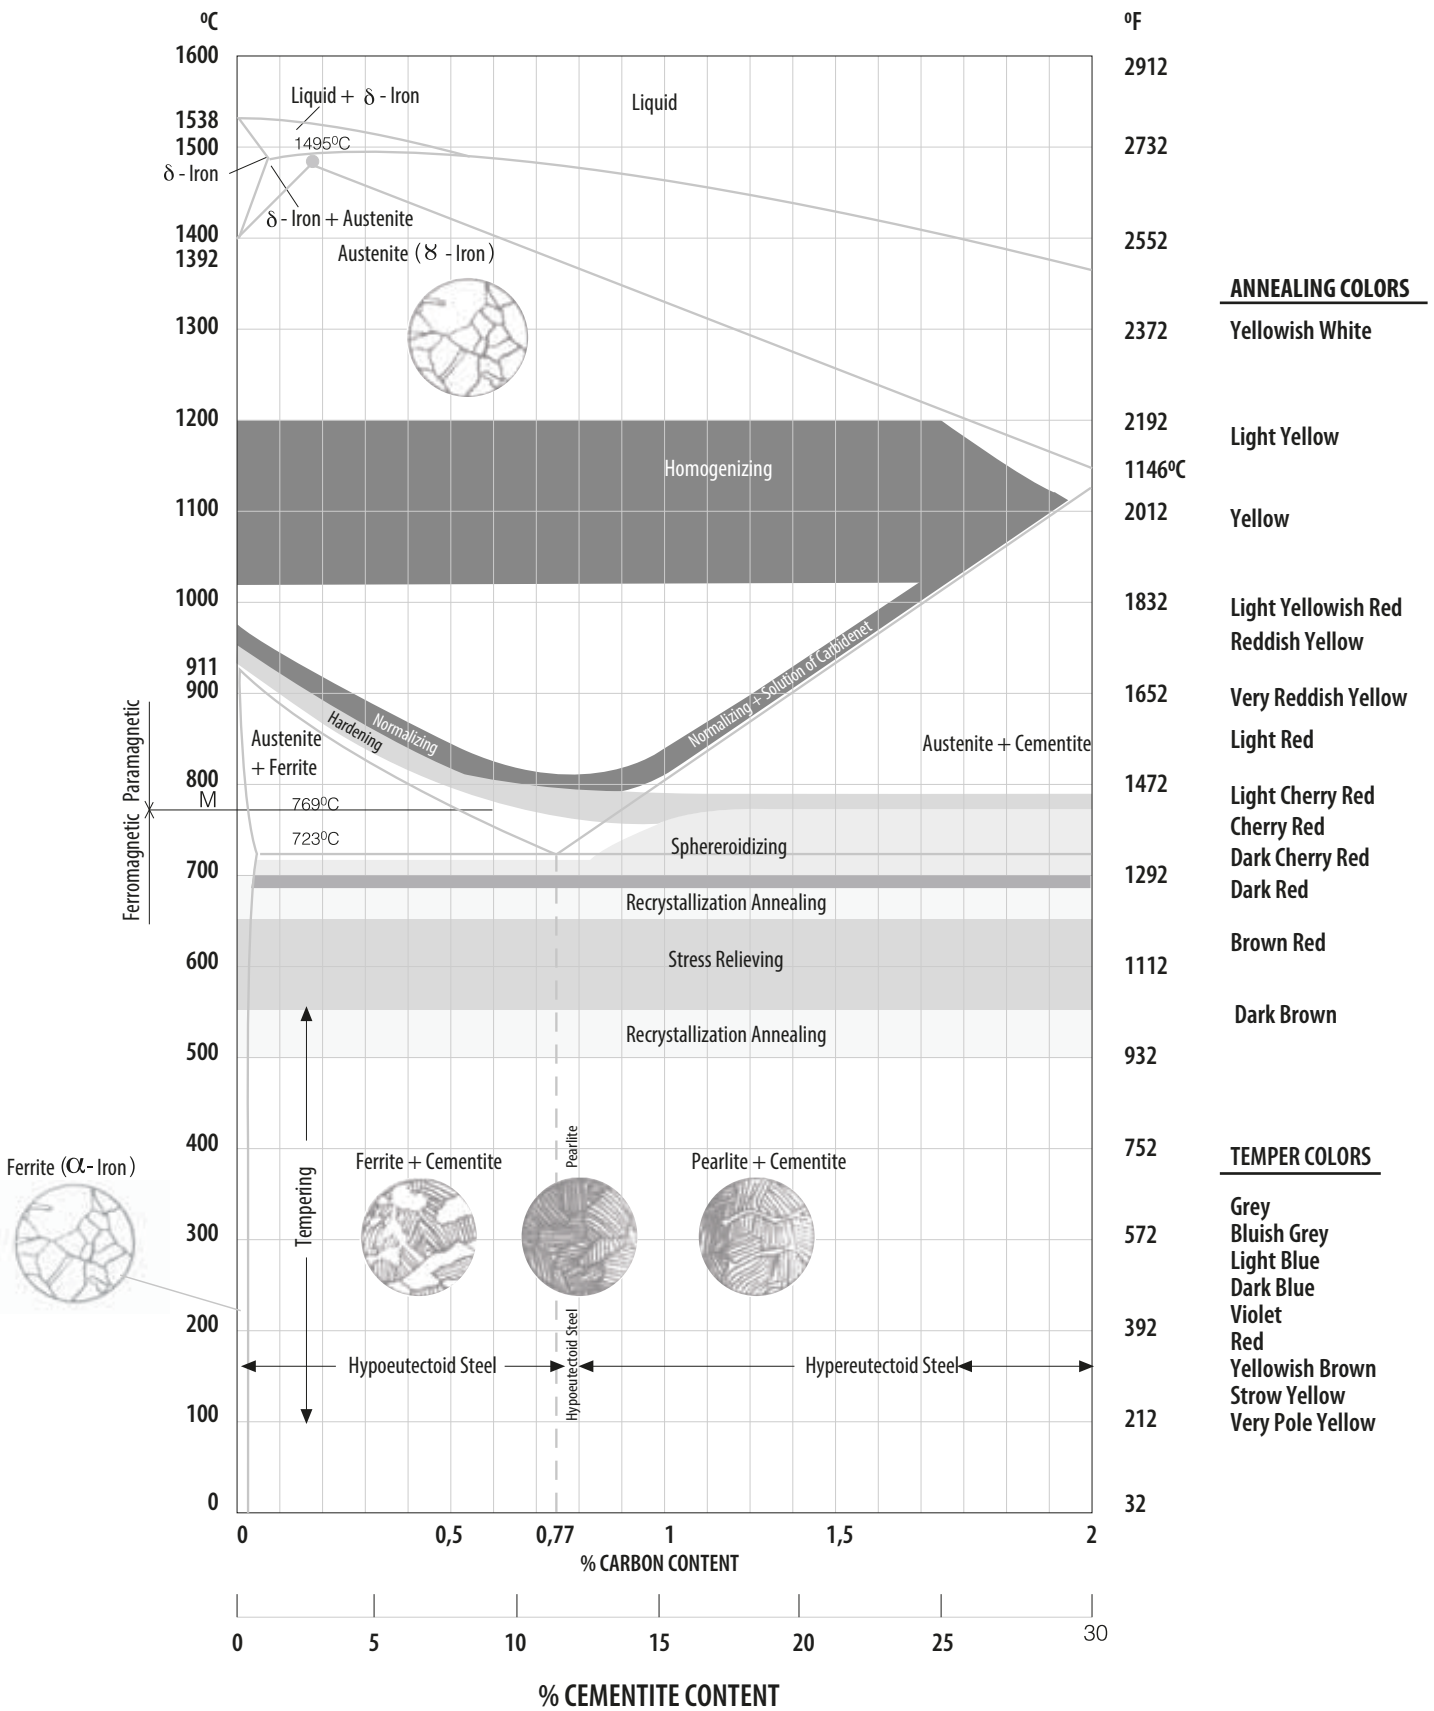
Hardfacing SAW Fluxes

Product Name and Standards	Applications and Properties	Polarity Welding Positions Re-drying Information
<p>SHF 604</p> <p>EN ISO 14174 S A AB 1 TS EN ISO 14174 S A AB 1</p>	<p>Agglomerated and unalloyed (neutral) submerged arc welding flux used for hardfacing purposes. Suitable for hardfacing of continuous casting rolls, table rolls, pinch rolls, drums, wheels and rails in combination with specially designed hardfacing flux cored wires. Possible to use both in alternative and direct currents in stringer bead and oscillation technique. Provides smooth weld bead without porosity and has a very easy slag removal.</p> <p>Typical Applications: Hardfacing of continuous casting and pinch rollers, table rolls, idlers, crane and train wheels, rails and drums.</p>	<p>    If required 2 Hour </p>

Welding Wire	Typical Chemical Analysis of All-Weld Metal (%)			Hardness	Packing Information of Welding Flux
					Packing Weight (kg) Packing Type
FCS 415	C: 0.08	Cr: 13.00	Nb: 0.20	42 HRc	25 kg - Kraft Pack
	Si: 0.70	Ni: 2.70	V: 0.25		
	Mn: 1.00	Mo: 1.00			
FCS 417	C: 0.12	Cr: 13.00	Nb: 0.25	47 HRc	
	Si: 0.80	Ni: 3.00	V: 0.25		
	Mn: 1.10	Mo: 1.00			
FCS 420	C: 0.20	Cr: 13.00		50 HRc	
	Si: 0.70	Ni: 0.30			
	Mn: 1.40	Nb: 0.30			
FCS 421	C: 0.25	Cr: 13.00		52 HRc	
	Si: 0.80	Ni: 0.35			
	Mn: 1.30	Nb: 0.30			
FCS 430	C: 0.03	Cr: 17.00		200 HB	
	Si: 0.70				
	Mn: 1.30				

APPENDIX

IRON-CARBON PHASE DIAGRAM- STEEL SECTION



PROPERTIES OF SOME IMPORTANT METALS

Alloy	Density (gr/cm ³)	Melting Point (°C)	Tensile Strength (N/mm ²)
Steel	7.7 - 7.85	1450 - 1520	340 - 1800
Grey Cast Iron	7.1 - 7.3	1150 - 1250	150 - 400
Austenitic Stainless Steels	7.8 - 7.9	1440 - 1460	600 - 800
Mg - Alloys	1.8 - 1.83	590 - 650	180 - 300
Al - Alloys	2.6 - 2.85	570 - 655	100 - 400
Zn - Alloys	5.7 - 7.2	380 - 420	140 - 300
Brass	8.25	900 - 950	250 - 600
Bronze	8.56 - 8.9	880 - 1040	200 - 300

EFFECTS OF ALLOY ELEMENTS ON THE PROPERTIES OF STEELS

Alloying Elements	Si	Mn*	Mn**	Cr	Ni*	Ni**	Al	W	V	Co	Mo	S	P
Hardness		↑	↓ ↓ ↓	↑ ↑	↑	↓ ↓	—	↑	↑	↑	↑	—	↑
Strength	↑	↑	↑	↑ ↑	↑	↑	—	↑	↑	↑	↑	—	↑
Yield Point	↑ ↑	↑	↓	↑ ↑	↑	↓	—	↑	↑	↑	↑	—	↑
Elongation	↓	~	↓ ↓ ↓	↓	~	↑ ↑ ↑	—	↓	~	↓	↓	↓	↓
Cross Section	~	~	~	↓	~	↑ ↑	↓	↓	~	↓	↓	↓	↓
Impact Resistance	↓	~	—	↓	~	↑ ↑ ↑	↓	—	↑	↓	↑	↓	↓ ↓ ↓ ↓
Elasticity	↑ ↑ ↑	↑	—	↑	—	—	—	—	↑	—	—	—	—
High Temperature Resist.	↑	~	—	↑	↑	↑ ↑ ↑	—	↑ ↑ ↑	↑ ↑	↑ ↑	↑ ↑	—	—
Cooling Speed	↓	↓	↓ ↓	↓ ↓ ↓	↓ ↓	↓ ↓	—	↓ ↓	↓	↑ ↑	↓ ↓	—	—
Carbide Formation	↓	~	—	↑ ↑	—	—	—	↑ ↑	↑ ↑ ↑ ↑	—	↑ ↑ ↑	—	—
Wear Resistance	↓ ↓ ↓	↓ ↓	—	↑	↓ ↓	—	—	↑ ↑ ↑	↑ ↑	↑ ↑ ↑	↑ ↑	—	—
Forging Property	↓	↑	↓ ↓ ↓	↓	↓	↓ ↓ ↓	↓ ↓	↓ ↓	↑	↓	↓	↓ ↓ ↓	↓ ↓ ↓
Machinability	↓	↓	↓ ↓ ↓	—	↓	↓ ↓ ↓	—	↓ ↓	—	~	↑	↑ ↑ ↑	↓ ↓ ↓
Oxidizing Tendency	↓	~	↓ ↓	↓ ↓ ↓	↓	↓ ↓	↓ ↓	↓ ↓	↓	↓	↑ ↑	—	↓ ↓
Corrosion Resistance	—	—	—	↑ ↑ ↑	—	↑ ↑	—	—	↑	—	—	↓	↑ ↑

* Ferritic Steels

** Austenitic Steels

↑ Increase ↓ Decrease ~ No Change — Not Important or Not Known

PRE-HEATING, INTERPASS TEMPERATURE AND COOLING RATE

The preheating temperature and interpass temperatures are important to prevent underbead cracking, hydrogen cracking, porosity, distortion, high hardness in HAZ, weld metal cracking, spalling, or stress failure of the part. Preheating temperature can be calculated by the carbon equivalent, C_{eq} , of the base metal.

C_{eq} for low alloy steels with alloy content :

$$C \leq \%0.5; Mn \leq \%1.0; Cr \leq \%1.0; Ni \leq \%3.5; Mo \leq \%0.6; Cu \leq \%1.0$$

$$C_{eq} = \%C + \%Mn/6 + (\%Cr + \%Mo + \%V)/5 + (\%Ni + \%Cu)/15$$

$$\text{Minimum Preheating Temperature (}^\circ\text{C)} = C_{eq} \times 200 + 20$$

Preheating temperature can also be calculated by using below equation, which also take into account the thickness of the base metal :

$$\text{Preheating Temperature (}^\circ\text{C)} = \sqrt{350 \times C_{eq} \times (1 + 0,005 \times d)} - 0,25$$

Carbon Equivalent (C_{eq})	Preheating Temperature Range ($^\circ\text{C}$)
$C_{eq} \leq 0.45$	No need under normal conditions
$0.46 \leq C_{eq} \leq 0.60$	100 - 200
$C_{eq} \geq 0.60$	200 - 350

It is essential that this temperature is obtained and maintained during the welding operation.

Manganese steels, on the other hand, becomes brittle if overheated above 260°C. Interpass temperatures shall be kept below 260°C during welding. As the temperature of the workpiece increase, it has to be let cool down before applying further hardfacing passes. On small parts, high localized heating shall be avoided by using a skip welding technique. Cast irons are extremely crack sensitive. The heat affected zone may be full of cracks even with high preheat temperatures.

Interpass Temperature is the temperature of the surface when welding all layers except first layer. It is just as important and should usually be as the preheat temperature.

Cooling Rate after welding affects wear resistance of some deposits, it is much more important for the control of spalling, cracking and distortion. Therefore a slow cooling rate may be required even if it reduces wear resistance.

Methods of controlling cooling rate include the following:

1. Preheating is the most effective way of slowing the cooling rate.
2. Heat input from welding slows cooling by the raising the temperature of the part.
3. Insulating the hot part immediately after welding with dry sand, lime, glass fibre blanket, etc. slows cooling. This method helps minimize residual cooling stresses, weld cracking and distortion but does not affect wear resistance of most deposits. Large parts pull heat away from the weld more quickly than small parts and they naturally cool the weld faster.

PRE-HEATING, INTERPASS TEMPERATURE AND COOLING RATE

Ceq	Electrode Diameter (mm)								
		Butt Weld				Filled Weld			
		6	12	25	50	6	12	25	50
0.35	3.25	*	*	*	*	*	*	*	100
	4.00	*	*	*	*	*	*	*	*
	5.00	*	*	*	*	*	*	*	*
0.40	3.25	*	*	*	150	*	*	100	200
	4.00	*	*	*	*	*	*	*	150
	5.00	*	*	*	*	*	*	*	100
0.45	3.25	*	*	150	250	*	100	250	300
	4.00	*	*	100	200	*	*	200	250
	5.00	*	*	*	150	*	*	100	200
0.50	3.25	*	*	250	350	*	150	350	(450)
	4.00	*	*	150	300	*	100	250	400
	5.00	*	*	100	200	*	*	200	350
0.55	3.25	*	150	400	(550)	100	300	(500)	**
	4.00	*	*	300	(450)	*	200	(450)	**
	5.00	*	*	150	350	*	100	350	(600)
0.60	3.25	150	400	**	**	350	**	**	**
	4.00	100	250	**	**	250	(600)	**	**
	5.00	*	100	(500)	(600)	150	300	(600)	**
0.65	3.25	300	**	**	**	**	**	**	**
	4.00	200	350	**	**	**	**	**	**
	5.00	*	150	(600)	**	200	(600)	**	**
0.70	3.25	400	**	**	**	**	**	**	**
	4.00	300	500	**	**	**	**	**	**
	5.00	200	400	**	**	400	(600)	**	**
0.75	5.00	400	500	**	**	(600)	**	**	**

* Preheating is not necessary.

** Necessary preheating temperatures for practical applications is too high.

Preheating Temperature (°C): Carbon Equivalent (Ceq), depends on material thickness and electrode diameter.

Formulation to calculate the preheating temperature are generally applied to steel which are not post weld heat treated. Those formulation are taking in consideration, the chemical analysis (C, Mn, Cr, Ni, . . .), the thickness of the plate, the heat input, the type of coating, the type of the weldment.

The target is to remain with a ferric structure, to avoid cold crack, due to a martensitic structure saturated of hydrogen generally located in in the heat affected zone. Hardness is generally limited at ~220HB.

For some steel, like ASTM A387 or similar, which require a PWHT at ~680°C preheating temperature, maximum interpass temperature, as well as heating and cooling conditions are generally specified in the engineering specifications. The aim is to have temper martensite after the PWHT. A too high interpass temperature will promote ferrite instead of martensite, and after the final PWHT the weldment will not reach the requested mechanical properties.

PRE-HEATING, INTERPASS TEMPERATURE AND COOLING RATE

In hardfacing, martensitic steel are used when deposit requirement is requested hardness, this requirement is mainly controlled by C and Cr content to reach the level is requested. Because of the quantities of carbide formers is present in the overlay, the majority of C is kept by carbide formation, and the usual formulation to calculate the preheat temperature is no more appropriated.

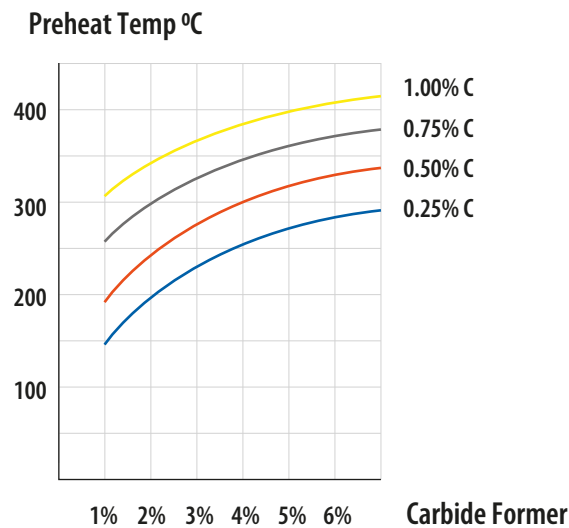


Fig. 1 / Practical Preheating Temperature °C

Practical preheating temperature are giving by table 1. After welding, the deposit will be followed directly by a post heating at least 300°C during 2-3 H to reduce the hydrogen content. Cooling will be very slow from post heating temperature up to 150°C. The purpose of the slow cooling is to favorize the diffusion of hydrogen, uniformization of the temperature before starting the martensite formation when crossing the Ms point. Soaking time at preheating temperature need to be high enough to have a uniform temperature through the full toughness of the piece.

The best is using the dilatometric curve of the deposit. When overlay is deposited below Ms temp, differential tempering are created in the area of the fusion line of subsequent bead, creating an uneven surface characteristic, thus corrugated surface can appear during machining or during service because of hardness and difference wear resistance

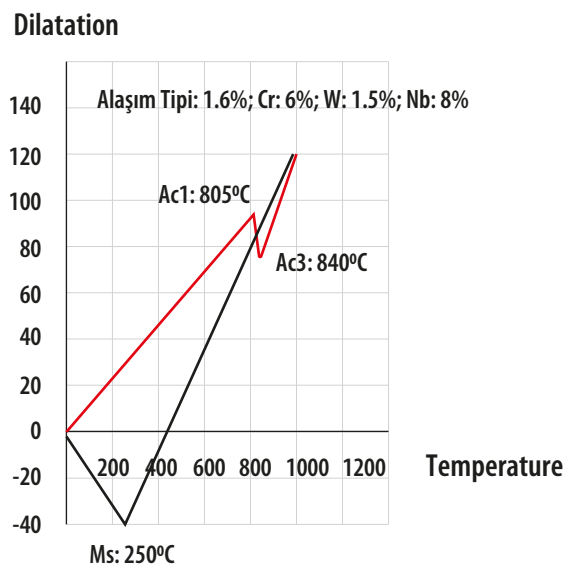


Fig. 2 / Dilatometric Curve

CARBON EQUIVALENT (CE) AND PRE-HEATING TEMPERATURE

The table shows the recommended preheating temperatures for a number of different metals which will be hardfaced with given filler metals.

Base Metal	Plate Thickness (mm)	Steel C _{eq} < 0,3 <180 HB (°C)	Low Alloy C _{eq} < 0,3 - 0,6 200-300 HB (°C)	Tool Steel C _{eq} < 0,6 - 0,8 300-400 HB (°C)	Chromium Steel Cr: 5-12 % 300-500 HB (°C)	Chromium Steel Cr > 12 % 200-300 HB (°C)	Stainless Steel 18/8 Cr/Ni approx. 200 HB (°C)	Manganese Steel %14 mn 250-500 HB (°C)
Low Alloy 200-300 HB	t ≤ 20	-	100	150	150	100	-	-
	20 < t ≤ 60	-	150	200	250	200	-	-
	t > 60	100	180	250	300	200	-	-
Tool Steel 300-450 HB	t ≤ 20	-	100	180	200	100	-	-
	20 < t ≤ 60	-	125	250	250	200	-	A
	t > 60	125	180	300	350	250	-	A
12 % Cr Steel 300-500 HB	t ≤ 20	-	150	200	200	150	-	X
	20 < t ≤ 60	100	200	275	300	200	150	X
	t > 60	200	150	350	376	250	200	X
Stainless Steel 18/8 Cr/Ni 200 HB	t ≤ 20	-	-	-	-	-	-	-
	20 < t ≤ 60	-	100	125	150	200	-	-
	t > 60	-	150	200	250	200	100	-
14 % Mn Steel 200 HB	t ≤ 20	-	-	-	X	X	-	-
	20 < t ≤ 60	-	-	B-100	X	X	-	-
	t > 60	-	-	B-100	X	X	-	-
Co-Based Type 6 40 HRc	t ≤ 20	100	200	250	200	200	100	X
	20 < t ≤ 60	300	400	B-450	400	350	400	X
	t > 60	400	400	B-500	B-500	400	400	X
Carbide Type 1* 55 HRc	t ≤ 20	-	A	A	A	A-	A	A
	20 < t ≤ 60	-	100	200	B-200	B-200	A	A
	t > 60	A	200	250	B-200	B-200	A	A

*1 : Maximum two layers of weld metal. (Relief cracking is normal)

- : No preheating or preheating < 100°C.

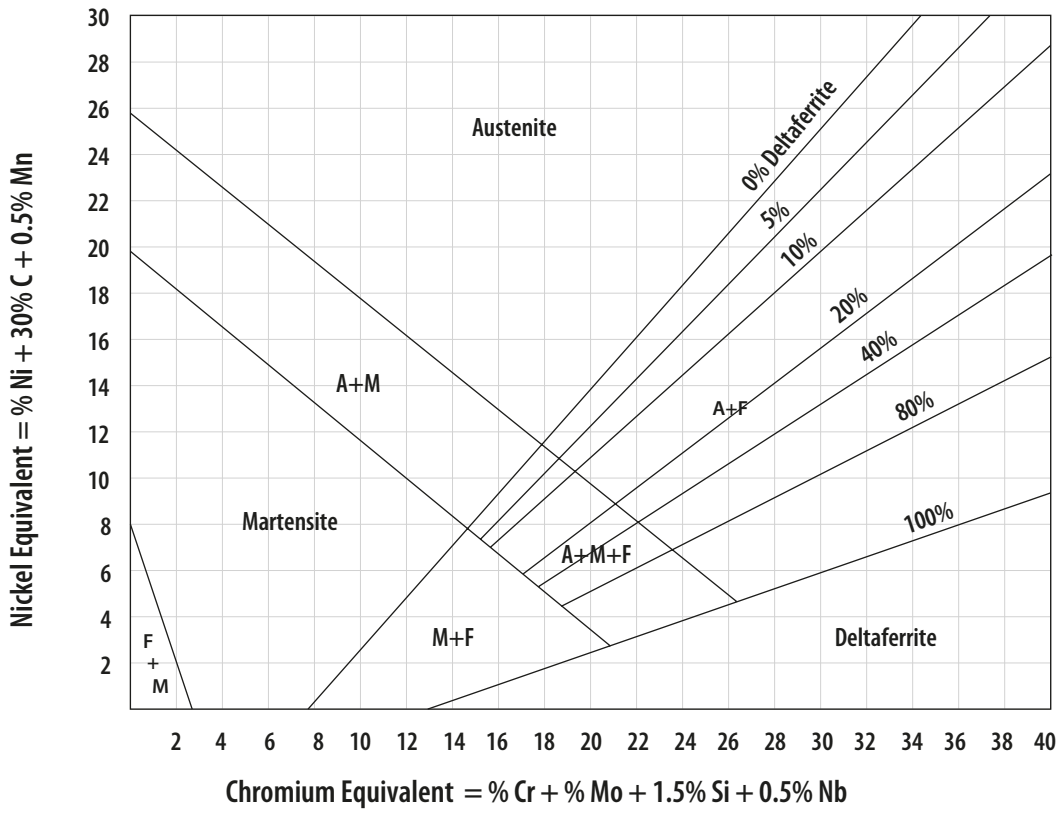
X : Used very rarely or not at all.

A: Preheating when large areas are surfaced.

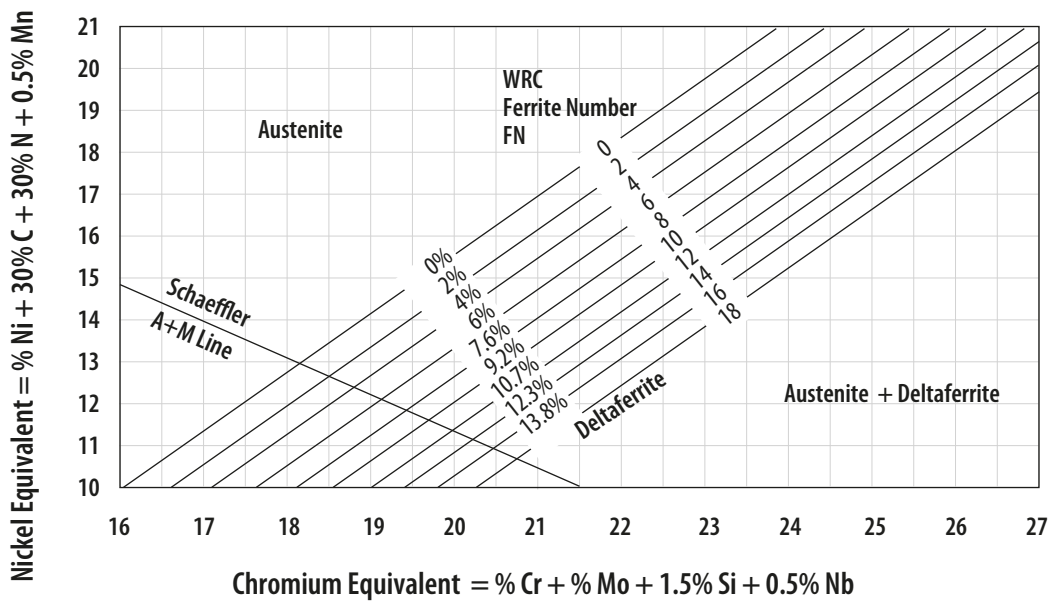
B: To prevent cracking, use a buffer layer of tough stainless weld metal.

SCHAEFFLER DIAGRAM

The upper limits of the alloying elements in stainless steel for the Schaeffler diagram that is used to determine the microstructure of weld metal:
 C: % 0.2, Mn: % 4.0, Si: % 1.0, Mo: % 3.0, Nb: % 1.5



DELONG DIAGRAM



TS EN ISO 14175

Symbol		Components in Nominal Percentage of Volume					
Main Group	Sub Group	Oxidizing		Inert		Reducing	Low Reactivity
		CO ₂	O ₂	Ar	He	H ₂	N ₂
I	1			100			
	2				100		
	3			Rest	0.5 ≤ He ≤ 95		
M1	1	0.5 ≤ CO ₂ ≤ 5		Rest ^a		0.5 ≤ H ₂ ≤ 5	
	2	0.5 ≤ CO ₂ ≤ 5		Rest ^a			
	3		0.5 ≤ O ₂ ≤ 3	Rest ^a			
	4	0.5 ≤ CO ₂ ≤ 5	0.5 ≤ O ₂ ≤ 3	Rest ^a			
M2	0	5 < CO ₂ ≤ 15		Rest ^a			
	1	15 < CO ₂ ≤ 25		Rest ^a			
	2		3 < O ₂ ≤ 10	Rest ^a			
	3	0.5 ≤ CO ₂ ≤ 5	3 < O ₂ ≤ 10	Rest ^a			
	4	5 < CO ₂ ≤ 15	0.5 ≤ O ₂ ≤ 3	Rest ^a			
	5	5 < CO ₂ ≤ 15	3 < O ₂ ≤ 10	Rest ^a			
	6	15 < CO ₂ ≤ 25	0.5 ≤ O ₂ ≤ 3	Rest ^a			
	7	15 < CO ₂ ≤ 25	3 < O ₂ ≤ 10	Rest ^a			
M3	1	25 < CO ₂ ≤ 50		Rest ^a			
	2		10 < O ₂ ≤ 15	Rest ^a			
	3	25 < CO ₂ ≤ 50	2 < O ₂ ≤ 10	Rest ^a			
	4	5 < CO ₂ ≤ 25	10 < O ₂ ≤ 15	Rest ^a			
	5	25 < CO ₂ ≤ 50	10 < O ₂ ≤ 15	Rest ^a			
C	1	100					
	2	Rest	0.5 ≤ O ₂ ≤ 30				
R	1			Rest ^a		0.5 ≤ H ₂ ≤ 15	
	2			Rest ^a		15 < H ₂ ≤ 50	
N	1				He		100
	2			Rest ^a	He		0.5 ≤ N ₂ ≤ 5
	3			Rest ^a	He		5 < N ₂ ≤ 50
	4			Rest ^a	He	0.5 ≤ H ₂ ≤ 10	0.5 ≤ N ₂ ≤ 5
	5				He	0.5 ≤ H ₂ ≤ 50	Rest
O	1		100				
Z	: Gas mixtures containing components not listed, or mixtures outside the composition ranges listed ^b						

^aFor the purpose of this classification, argon may be substituted partially or completely by helium^b


^bTwo gas mixtures with the same Z-classification may not be interchangeable.

Gas	Density	Condition
Carbondioxide (CO ₂)	1,84 kg/m ³	15°C, 1 atm
Argon (Ar)	1,70 kg/m ³	15°C, 1 atm
Oxygen (O ₂)	1,33 kg/m ³	15°C, 1 atm
Azot (N ₂)	0,96 kg/m ³	15°C, 1 atm
Helium (He)	0,16 kg/m ³	15°C, 1 atm


Shielding Gas Flow Rates in TIG Welding		
Stainless Steel - Mild Steel		
Tungsten Electrode Dia.	Nozzle	Gas Flow Rate
1.60 mm	6.00 - 8.00 mm	7 - 10 lt/min
2.00 mm	6.00 - 8.00 mm	7 - 10 lt/min
2.40 mm	6.00 - 12.00 mm	8 - 12 lt/min
3.20 mm	10.00 - 14.00 mm	10 - 14 lt/min
4.00 mm	10.00 - 14.00 mm	10 - 14 lt/min
Aluminum and Aluminum Alloys		
1.60 mm	8.00 - 12.00 mm	8 - 10 lt/min
2.40 mm	8.00 - 12.00 mm	10 - 12 lt/min
3.20 mm	10.00 - 14.00 mm	12 - 14 lt/min
4.00 mm	12.00 - 14.00 mm	12 - 16 lt/min

WELDING POSITIONS - EN ISO 6947 – ASME SEC. IX


Plate Butt Welding



Flat Position
PA / 1G




Horizontal Position
PC / 2G



Overhead Position
PE / 4G




Vertical Up Position
PF / 3G



Vertical Down Position
PG / 3G


Plate Fillet Welding




Flat Position
PA / 1F




Horizontal Vertical
Position
PB / 2F



Horizontal Overhead
Position
PD / 4F



Vertical Up Position
PF / 3F




Vertical Down Position
PG / 3F

Pipe Butt Welding



Pipe Rotating
Flat Position
PA / 1G



Pipe Fixed
Horizontal Position
PC / 2G



Pipe Fixed
Vertical Up Position
PH / 5G




Pipe Fixed
Vertical Down Position
PJ / 5G




Pipe Fixed as Angle of 45°
Inclined Position Welding Upwards
H-L045 / 6G

Pipe Fillet Welding




Pipe Rotating
Flat Position
PB / 1FR




Pipe Fixed
Horizontal Vertical
Position
PB / 2F



Pipe Fixed
Horizontal Overhead
Position
PDH / 4F




Pipe Fixed
Vertical Up
Position
PH / 5F




Pipe Fixed
Vertical Down
Position
PJ / 5F

Welding Positions



EN ISO 6947 : PA PB PC PD PE PF PG
 DIN 8560 : w h q hü ü s f
 All Positions



EN ISO 6947 : PA PB PC PD PE PF
 DIN 8560 : w h q hü ü s
 All Positions, Vertical-Down Conditionally



EN ISO 6947e : PA PB PC PD PE PF
 DIN 8560 : w h q hü ü s
 All Positions, Except Vertical-Down



EN ISO 6947 : PA PB PC PF
 DIN 8560 : w h q s
 All Positions, Except Vertical-Down and Overhead



EN ISO 6947 : PA PB
 DIN 8560 : w h
 Flat Butt and Fillet Welds Only




EN ISO 6947 : PA
 DIN 8560 : w
 Flat Butt Welds Only




EN ISO 6947 : PG
 DIN 8560 : f
 Vertical-Down Only


Welding Current and Polarity




Direct Current: (DC),
 Electrode Connected to Positive Pole




Direct Current: (DC),
 Electrode Connected to Negative or Positive Pole



Direct Current: (DC) Preferred,
 Electrode Connected to Positive Pole



Direct Current: (DC) Preferred,
 Electrode Connected to Negative or Positive Pole



Direct Current: (DC) Preferred,
 Electrode Connected to Negative Pole



Alterneative Current: (AC)



Direct Current: (DC) Preferred,
 Electrode Connected to Negative Pole

HARDNESS CONVERSION TABLE - EN 18265

Tensile Strength (N / mm ²)	Hardness			Tensile Strength (N / mm ²)	Hardness		
	Vickers (HV)	Brinell (HB)	Rockwell (HRC)		Vickers (HV)	Brinell (HB)	Rockwell (HRC)
320	100	95	-	1155	360	342	36.6
335	105	99.8	-	1190	370	352	37.7
350	110	105	-	1220	380	361	38.8
370	115	109	-	1255	390	371	39.8
385	120	114	-	1290	400	380	40.8
400	125	119	-	1320	410	390	41.8
415	130	124	-	1350	420	399	42.7
430	135	128	-	1385	430	409	43.6
450	140	133	-	1420	440	418	44.5
465	145	138	-	1455	450	428	45.3
480	150	143	-	1485	460	437	46.1
495	155	147	-	1520	470	447	46.9
510	160	152	-	1555	480	456	47.7
530	165	156	-	1595	490	466	48.4
545	170	162	-	1630	500	476	49.1
560	175	166	-	1665	510	485	49.8
575	180	171	-	1700	520	494	50.5
595	185	176	-	1740	530	504	51.1
610	190	181	-	1775	540	513	51.7
625	195	185	-	1810	550	523	52.3
640	200	190	-	1845	560	532	53.0
660	205	195	-	1880	570	542	53.6
675	210	199	-	1920	580	551	54.1
690	215	204	-	1955	590	561	54.7
705	220	209	-	1995	600	570	55.2
720	225	214	-	2030	610	580	55.7
740	230	219	-	2070	620	589	56.3
755	235	223	-	2105	630	599	56.8
770	240	228	20.3	2145	640	608	57.3
785	245	233	21.3	2180	650	618	57.8
800	250	238	22.2	-	660	-	58.3
820	255	242	23.1	-	670	-	58.8
835	260	247	24.0	-	680	-	59.2
850	265	252	24.8	-	690	-	59.7
865	270	257	25.6	-	700	-	60.1
880	275	261	26.4	-	720	-	61.0
900	280	266	27.1	-	740	-	61.8
915	285	271	27.8	-	760	-	62.5
930	290	276	28.5	-	780	-	63.3
950	295	280	29.2	-	800	-	64.0
965	300	285	29.8	-	820	-	64.7
995	310	295	31.0	-	840	-	65.3
1030	320	304	32.2	-	860	-	65.9
1060	330	314	33.3	-	880	-	66.4
1095	340	323	34.4	-	900	-	67.0
1125	350	333	35.5	-	920	-	67.5

METRIC CONVERSION COEFFICIENTS

Property	To Convert	To	Multiply By
Electrical Force	pound - force	N	4.448222
	kilogram - force	N	9.806650
Energy, Work, Heat, Impact Energy	N	lbf	0.2248089
	foot pound force	J	1.355818
	foot poundal	J	0.04214011
	btu	J	1054.35
	calorie (thermochemical)	J	4.184
	watt-hour	J	3600
Volume	in ³	m ³	0.00001638706
	ft ³	m ³	0.02831685
	yd ³	m ³	0.7645549
	in ³	mm ³	16387.06
	ft ³	mm ³	28316850
	in ³	L	0.01638706
	ft ³	L	28.31685
	gallon	L	3.785412
Travel Speed, Velocity (Linear)	in / min	m / sec	0.0004233333
	ft / dm	m / sec	0.00508
	in / min	mm / sec	0.4233333
	ft / min	mm / sec	5.08
	mil / h	km / h	1.609344
Heat Input	J / in	J / m	39.37008
	J / m	J / in	0.0254
Force	kilogram - force	N	9.80665
	pound - force	N	4.448222
Fracture Toughness	ksi • in ^{1/2}	MN • m ^{-3/2}	1.098855
	MN • m ^{-3/2}	ksi • in ^{1/2}	0.910038
Deposition Rate	lb / h	kg / h	0.45(appx.)
	kg / h	lb / h	2.2 (appx.)
Temperature	degree, celsius, t _c	K	t _k = t _c + 273.15
	degree, fahrenheit, t _f	K	t _k = (t _f + 459.67) / 1.8
	degree, rankine, t _r	K	t _k = t _r / 1.8
	degree, fahrenheit, t _f	°C	t _c = (t _f - 32) / 1.8
	kelvin, t _k	°C	t _c = t _k - 273.15
Thermal Conductivity	cal / [cm • s • °C]	W / [m • K]	418.4
Wire Feeding Speed	mm / sec	in / min	2.362205
Length	in	m	0.0254
	in	mm	25.4
	ft	m	0.3048
	ft	mm	304.8
	mm	in	0.03937008
	mm	ft	0.00328084
	yd	m	0.9144
	mil	m	1609.3
Density	pound mass / in ³	kg / m ³	27679.9
	pound mass / ft ³	kg / m ³	16.01846

METRIC CONVERSION COEFFICIENTS

Property	To Convert	To	Multiply By
Angle	deg	rad	0.01745329
	min	rad	0.0002908882
	sec	rad	0.000004848137
Mass, Weight	pound mass	kg	0.4535924
	metric ton	kg	1000
	ton (short, 2000 lb)	kg	907.1847
	slug	kg	14.5939
Current Density	A / in ²	A / mm ²	0.001550003
	A / mm ²	A / in ²	645.16
Flow Rate	ft ³ / h	L / min	0.4719475
	gallon / h	L / min	0.0630902
	gallon / min	L / min	3.785412
Area Dimension	in ²	m ²	0.00064516
	ft ²	m ²	0.09290304
	yd ²	m ²	0.8361274
	in ²	mm ²	645.16
	ft ²	mm ²	92903.04
	acre	m ²	4046.873
	mm ²	in ²	0.001550003
Pressure (Gas & Liquid)	psi	kPa	6.894757
	lb / ft ²	kPa	0.04788026
	N / mm ²	kPa	1000
	atmosphere	kPa	101.325
	kPa	psi	0.1450377
	kPa	lb / ft ²	20.88548
	kPa	N / mm ²	0.001
Pressure (Vacuum)	torr (mm Hg at 0°C)	Pa	133.322
	micron (µm Hg at 0°C)	Pa	0.1333220
	Pa	torr	0.00750064
	Pa	micron	7.50064
	bar	psi	14.50377
Tensile & Yield Strenght	psi	MPa	0.006894757
	ksi	MPa	6.894757
	lb / ft ²	MPa	0.00004788026
	N / mm ²	MPa	1
	MPa	psi	145.0377
	MPa	lb / ft ²	20885.43
	MPa	N / mm ²	1
Power	horsepower (550 ft lbf / s)	W	745.6999
	horsepower (electric)	W	746
	btu/min (thermochemical)	W	17.5725
	calorie / min (thermochemical)	W	0.06973333
	foot pound-force / min	W	0.02259697
Power Density	W / in ²	W / m ²	1550.003
	W / m ²	W / in ²	0.00064516
Electrical Resistivity	Ω • cm	Ω • m	0.01
	Ω • m	Ω • cm	100

PACKING INFORMATION

STICK ELECTRODES

Inner Cardboard Box



Box Type	Height (mm)	Width (mm)	Length (mm)	Average Weight (kg)
K350MW-1	18	61	352	1
M350 MW	41	62	352	2.50
B350	68	80	352	5.00
B450 MW	62	80	452	6.50
K300 MW	33	62	302	1.75
K350 MW	35	62	352	2.00
K400 MW	30	61	402	2.25
O350 MW	39	82	352	3.50

Vacuum Package



Box Type	Height (mm)	Width (mm)	Length (mm)	Average Weight (kg)
K250MW	34	62	252	1.50
K300MW	15	60	302	0.75
K350MW	34	62	352	2.00
M350MW-K	36	61	352	2.50
M400MW-K	34	62	402	2.50
M450MW-K	28	61	452	2.50

Plastic Box



Box Type	Height (mm)	Diameter (mm)	Average Weight (kg)
PS30-1	315	65	2.00
PS35-1	365	65	2.50
PS35-2	365	84	5.00
PS45-2	470	84	6.50

Box Type	Height (mm)	Width (mm)	Length (mm)	Average Weight (kg)
PL1-A	20	42	350	0.50
PL2-A	25	65	350	1.00

Tin Box



Box Type	Height (mm)	Diameter (mm)	Average Weight (kg)
T1-A	365	75	2.00

Box Type	Height (mm)	Width (mm)	Length (mm)	Average Weight (kg)
T1-S	90	90	355	8.00

PACKING INFORMATION

STICK ELECTRODES

Outer Cardboard Box



Box Type	Height (mm)	Width (mm)	Length (mm)	Average Weight (kg)
KK350MW-1	40	330	375	10.00
MK300P	150	222	325	7.50
MK350MW	92	200	365	15.00
MK350MW-P	75	225	375	7.50
BK350MW	65	258	365	15.00
BK350MW-P	88	272	375	15.00
BK450MW	71	260	465	19.50
KK300MW	110	205	330	15.75
KK350MW	116	205	380	18.00
KK400MW	105	200	430	20.25
OK350MW	88	263	373	21.00

GAS TUNGSTEN (TIG) and OXY-ACETYLENE WELDING RODS

Inner Tube Box



Box Type	Height (mm)	Diameter (mm)	Average Weight (kg)
T500MW	540	50	1.00 / 2.50
T1000MW	1040	50	2.50 / 5.00

Plastic Box



Box Type	Height (mm)	Width (mm)	Length (mm)	Average Weight (kg)
T1000MW-P	25	60	1005	2.50 / 5.00

Outer Cardboard Box



Box Type	Height (mm)	Width (mm)	Length (mm)	Average Weight (kg)
T500MW	54	206	534	4.00 / 10.00
T1000MW	54	206	1050	10.00 / 20.00
T1000MW-P	55	125	1010	10.00 / 20.00

PACKING INFORMATION

GAS METAL (MIG/MAG) AND FLUX CORED ARC WELDING WIRES

Spools & Boxes



Spool Type	Box Type	Inner Diameter (mm)	Outer Diameter (mm)	Net Weight (kg)
D100	M1	16.5	100	1
D200	M2	52	200	5
D300	M3	52	300	15-20
K300	M3	180	300	15
K300MS	M3	52	300	15-18

Drums



Drum Type	Height (mm)	Outer Diameter (mm)	Net Weight (kg)
DR60	240	517	60
DR250	830	517	250
DR400	1000	600	400

PACKING INFORMATION

SUBMERGED ARC WELDING (SAW) WIRES

Spools & Boxes



Spool Type	Box Type	Inner Diameter (mm)	Outer Diameter (mm)	Net Weight (kg)
K300MS	M3	52	300	15
K435	M4	300	435	25
K790	M5	550	790	100

Cage & Drums



Drum Type	Height (mm)	Outer Diameter (mm)	Net Weight (kg)
DR250	830	517	200
DR400	1000	600	400
DR600	950	650	600
Coil	1050	850	1000

SUBMERGED ARC WELDING FLUXES

Bags



Packing Type	Height (mm)	Width (mm)	Length (mm)	Average Weight (kg)
Kraft	100	380	560	25
Dry Pack	100	380	530	25
Big Pack	1250	910	910	1000

ALPHABETIC PRODUCT INDEX

Product Name	Page Number	Product Name	Page Number	Product Name	Page Number
EAL 1100	41	EI 347	37	ENI 422	43
EAL 4043	41	EI 347B	39	ENI 424	43
EAL 4047	41	EI 385	39	ENI 440	43
EC 900	55	EIS 307	29	ESA 20	9
ECUT	55	EIS 308	31	ESB 40	9
ECUT-S	55	EIS 309	33	ESB 42	9
ECU Sn7	43	EIS 309Mo	33	ESB 44	11
EH 245	47	EIS 410	39	ESB 45	11
EH 247	47	EIS 410NiMo	39	ESB 48	11
EH 250	47	EIS 430	39	ESB 50	11
EH 330	49	EIS 316	37	ESB 52	11
EH 340	49	EM 138	17	ESC 60	15
EH 350	49	EM 140	17	ESC 61	15
EH 360B	49	EM 150	17	ESC 70G	15
EH 360R	49	EM 150W	17	ESC 80G	15
EH 360Si	51	EM 160	17	ESC 90G	15
EH 380	51	EM 165	19	ESH 160B	13
EH 382	51	EM 170	19	ESH 160R	13
EH 384	51	EM 171	19	ESH 180R	13
EH 515	51	EM 172	19	ESR 11	7
EH 528	53	EM 175	19	ESR 12	7
EH 531	53	EM 176	21	ESR 13	7
EH 540	53	EM 180	21	ESR 14	7
EH 801	53	EM 181	21	ESR 30	9
EH 806	53	EM 201	21	ESR 35	9
EH 812	55	EM 202	21	FCH 325	109
EI 2209	41	EM 203	23	FCH 330	111
EI 307B	29	EM 206	23	FCH 335	111
EI 307R	29	EM 211	23	FCH 340	111
EI 308H	31	EM 212	23	FCH 355	111
EI 308L	29	EM 222	23	FCH 356	113
EI 308LB	29	EM 223	25	FCH 360	113
EI 308LRS	31	EM 235	25	FCH 361	113
EI 308Mo	31	EM 243	25	FCH 371	113
EI 309L	31	EM 251	25	FCH 373	115
EI 309LB	33	EM 253	25	FCH 415	115
EI 309LRS	33	EM 255	27	FCH 801	117
EI 309MoL	33	EM 285	27	FCH 806	119
EI 310	35	EM 295	27	FCH 812	119
EI 310B	35	EM 298	27	FCO 250	109
EI 312	35	ENI 400 (Ni)	45	FCO 330	109
EI 312RS	35	ENI 402 (Ni)	45	FCO 356	111
EI 316L	35	ENI 404 (Mo)	45	FCO 370	113
EI 316LB	37	ENI 406 (Mo)	45	FCO 415	115
EI 316LRS	37	ENI 412	45	FCO 510	115
EI 318	37	ENI 416 (NiFe)	47		

ALPHABETIC PRODUCT INDEX

Product Name	Page Number	Product Name	Page Number	Product Name	Page Number
FCO 512	115	MG 2	83	SW 702Mo	131
FCO 514	117	MG 20	83	SW 702Si	129
FCO 528	117	MG 201	87	SW 703Si	130
FCO 532	117	MG 201A	87	T CARBIDE 3000	79
FCO 540	117	MG 211	87	TAL 1100	75
FCO 90	105	MG 211A	89	TAL 4043	75
FCS 335	121	MG 222	89	TAL 4047	75
FCS 345	121	MG 3	83	TAL 5183	75
FCS 355	121	MG 30	83	TAL 5356	75
FCS 356	121	MH 361	97	TCU A18	77
FCS 415	121	MI 2209	93	TG 1	59
FCS 417	123	MI 307Si	89	TG 102	61
FCS 420	123	MI 308LSi	89	TG 150	61
FCS 421	123	MI 309LSi	91	TG 171	61
FCS 430	123	MI 310	91	TG 2	59
FCW 11	103	MI 312	91	TG 201	61
FCW 11A	103	MI 316LSi	91	TG 201A	63
FCW 12	103	MI 347	91	TG 211	63
FCW 13	103	MI 385	93	TG 211A	63
FCW 14	103	MI 410	93	TG 222	63
FCW 140	107	MNI 425	97	TG 222A	63
FCW 142	107	OG 1	59	TG 235	65
FCW 150W	107	OG 2	59	TG 285	65
FCW 16	105	SF 104	132	TG 295	65
FCW 17	105	SF 113	133	TG 3	59
FCW 171	107	SF 124	134	TH 801	79
FCW 172	107	SF 134	135	TH 806	79
FCW 201	109	SF 204	136	TH 812	79
FCW 21	105	SF 212	137	TI 2209	73
FCW 30	105	SF 304	138	TI 2594	73
MAL 1100	95	SF 401	139	TI 307Si	67
MAL 4043	95	SF 414	140	TI 308L	67
MAL 4047	95	SHF 325	149	TI 308LSi	67
MAL 5183	95	SHF 333	149	TI 309L	67
MAL 5356	95	SHF 335	149	TI 309LSi	67
MAL 5556	97	SHF 345	149	TI 310	67
MCU A18	99	SHF 604	151	TI 312	67
MCU Si3	99	SI 2209	146	TI 316L	69
MCU Sn	99	SI 307	141	TI 316LSi	69
MCU Sn6	99	SI 308L	142	TI 318	69
MG 1	83	SI 309L	143	TI 347	71
MG 102	85	SI 316L	144	TI 385	71
MG 150	85	SI 347	145	TI 410	71
MG 150W	85	SIF 501	147	TI 630	73
MG 182	85	SIF 502	149	TNI 422	77
MG 183	87	SW 701	127	TNI 425	77
MG 192	87	SW 702	128		

APPROVALS AND CERTIFICATES

Product Name	ABS	BV	CE	CWB	DB	DNV-GL	HAKC	LR	NK	RINA	RMRS	TL	TSE	TUV
EI 307B	-	-	√	-	√	-	-	-	-	-	-	-	√	√
EI 307R	-	-	√	-	-	-	-	-	-	-	-	-	-	√
EI 308L	-	-	√	√	-	-	√	-	-	-	-	-	√	√
EI 309L	-	√	√	√	√	√	-	-	-	-	-	-	-	√
EI 309MoL	-	-	-	-	-	-	-	-	-	-	-	-	√	√
EI 310	-	-	√	-	-	-	-	-	-	-	-	-	√	√
EI 312	-	-	√	-	-	-	-	-	-	-	-	-	-	√
EI 316L	-	√	√	√	-	√	-	-	-	-	-	-	√	√
EI 318	-	-	√	-	-	-	-	-	-	-	-	-	√	√
EI 347	-	-	√	-	-	-	-	-	-	-	-	-	√	√
EIS 307	-	-	-	-	-	-	-	-	-	-	-	-	√	-
EIS 308	-	-	-	-	-	-	-	-	-	-	-	-	√	-
EIS 309Mo	-	-	-	-	-	-	-	-	-	-	-	-	√	-
EIS 410	-	-	-	-	-	-	-	-	-	-	-	-	√	-
EIS 410NiMo	-	-	-	-	-	-	-	-	-	-	-	-	√	-
EM 140	-	-	√	-	-	-	-	-	-	-	-	-	√	√
EM 150	-	-	-	-	-	-	-	-	-	-	-	-	√	-
EM 170	-	-	√	-	-	-	-	-	-	-	-	-	√	√
EM 171	-	-	√	-	-	-	-	-	-	-	-	-	√	√
EM 176	-	-	√	-	-	-	-	-	-	-	-	-	-	√
EM 180	-	-	√	-	-	-	-	-	-	-	-	-	-	√
EM 201	-	-	√	-	-	-	-	-	-	-	-	-	-	√
EM 202	-	-	√	-	-	-	-	-	-	-	-	-	-	√
EM 211	-	-	√	-	-	-	-	-	-	-	-	-	-	√
EM 212	-	-	√	-	-	-	-	-	-	-	-	-	-	√
EM 222	-	-	√	-	-	-	-	-	-	-	-	-	-	√
EM 235	-	-	√	-	-	-	-	-	-	-	-	-	-	√
ESB 42	-	-	-	-	-	-	√	-	-	-	-	-	√	-
ESB 44	-	-	√	-	√	√	-	-	-	-	-	-	√	√
ESB 48	√	√	√	-	√	√	√	√	√	√	-	√	√	√
ESB 50	√	√	√	√	√	√	-	-	-	√	-	√	-	√
ESB 52	√	√	√	-	√	√	√	√	-	-	-	-	√	√
ESC 60	√	√	√	√	√	-	-	-	-	-	-	-	-	√
ESC 61	-	-	-	√	-	-	-	-	-	-	-	-	-	-



* You can visit our www.magmaweld.com/os website for our current approvals and certificates.

* Magmaweld Uluslararası Tic. A.Ş. reserves the right to modify its products without prior notice.

APPROVALS AND CERTIFICATES

Product Name	ABS	BV	CE	CWB	DB	DNV-GL	HAKC	LR	NK	RINA	RMRS	TL	TSE	TUV
ESC 70G	-	-	-	-	-	-	-	-	-	-	-	-	√	-
ESC 80G	-	-	-	-	-	-	-	-	-	-	-	-	√	-
ESH 160B	-	-	-	-	-	-	-	-	-	-	-	-	√	-
ESH 160R	-	-	√	-	-	-	-	-	-	-	-	-	-	√
ESH 180R	-	√	√	-	-	-	-	-	-	-	-	-	√	√
ESR 11	-	√	√	-	√	-	√	-	-	-	-	-	√	√
ESR 13	√	√	√	√	√	-	-	-	-	-	-	√	√	√
ESR 13M	-	-	√	-	-	-	-	-	-	-	-	-	-	√
ESR 30	-	-	-	-	-	-	-	-	-	-	-	-	√	-
ESR 35	-	-	√	-	√	-	-	-	-	-	-	-	-	√
FCW 11	√	√	√	-	√	√	√	√	√	√	√	√	-	√
FCW 12	-	-	√	-	-	√	-	√	-	-	-	√	-	√
FCW 13	√	-	-	√	√	√	-	-	√	√	-	√	-	√
FCW 14	-	√	-	-	-	-	-	-	-	-	-	-	-	-
FCW 140	-	-	-	-	-	-	√	-	-	√	√	-	-	-
FCW 16	-	-	-	-	-	√	-	-	-	-	-	-	-	-
FCW 171	-	-	-	-	-	-	-	-	-	-	√	-	-	-
FCW 21	-	-	√	√	√	√	-	-	-	-	-	-	-	√
FCW 30	-	-	√	-	-	-	-	-	-	-	-	√	-	√
MG 102	-	-	-	√	-	-	-	-	-	-	-	-	-	-
MG 2	√	-	√	√	√	√	√	-	-	√	-	√	√	√
MG 20	-	-	√	-	√	-	-	-	-	-	-	-	-	√
MG 201	-	-	√	-	-	-	-	-	-	-	-	-	-	√
MG 3	-	-	√	-	√	√	√	-	-	-	-	-	√	√
SF 104	√	√	√	-	-	√	-	-	√	-	-	√	-	√
SW 701	-	-	√	-	-	-	-	-	-	-	-	-	√	√
SW 702	√	√	√	-	-	√	-	-	√	-	-	√	√	√
SW 702Mo	-	-	√	-	-	-	-	-	-	-	-	-	√	√
SW 702Si	-	-	√	-	-	-	-	-	-	-	-	-	√	√
SW 703Si	-	-	√	-	-	-	-	-	-	-	-	-	-	√
TG 102	-	-	-	√	-	-	-	-	-	-	-	-	-	-
TG 2	-	√	√	√	√	√	-	-	-	-	-	-	-	√
TG 201	-	-	√	-	-	-	-	-	-	-	-	-	-	√
TI 309L	-	-	-	-	-	√	-	-	-	-	-	√	-	-
TI 316L	-	√	-	-	-	√	-	-	-	-	-	√	-	-



* You can visit our www.magmaweld.com/os website for our current approvals and certificates.

* Magmaweld Uluslararası Tic. A.Ş. reserves the right to modify its products without prior notice.

Non-Stop Welding Since 1957

Magmaweld is a developer & manufacturer of Stick Electrodes, MIG/MAG & TIG Wires, Flux Cored Wires, Submerged-Arc Wires and Fluxes, Welding Machines, Fume Extractors, Welding Ancillary Products and Robotic Automation Systems since 1957 in Turkey. 95% of its sales program is manufactured by the two factories in Manisa/Turkey.



(+90) 444 93 53
magmaweld.com
info@magmaweld.com